

**Ag<sub>2</sub>PdP<sub>2</sub>O<sub>7</sub>****Kosta Panagiotidis and Robert Glaum\***

Institut für Anorganische Chemie, Rheinische Friedrich-Wilhelms-Universität Bonn,  
Gerhard-Domagk-Strasse 1, D-53121 Bonn, Germany  
Correspondence e-mail: rglau@uni-bonn.de

Received 29 October 2008; accepted 18 November 2008

Key indicators: single-crystal X-ray study;  $T = 293\text{ K}$ ; mean  $\sigma(\text{Pd}-\text{O}) = 0.007\text{ \AA}$ ;  
 $R$  factor = 0.035;  $wR$  factor = 0.074; data-to-parameter ratio = 16.3.

Disilver(I) palladium(II) diphosphate, Ag<sub>2</sub>PdP<sub>2</sub>O<sub>7</sub>, is isotropic with Na<sub>2</sub>PdP<sub>2</sub>O<sub>7</sub>. It consists of infinite diphosphato-palladate(II) [Pd(P<sub>2</sub>O<sub>7</sub>)<sub>2/2</sub>]<sup>2-</sup> ribbons with the Pd<sup>II</sup> ion in an almost square-planar coordination ( $\bar{1}$  symmetry) and the P<sub>2</sub>O<sub>7</sub> group exhibiting 2 symmetry. The [Pd(P<sub>2</sub>O<sub>7</sub>)<sub>2/2</sub>]<sup>2-</sup> ribbons are linked by distorted [AgO<sub>6</sub>] octahedra. <sup>31</sup>P-MAS NMR studies on Ag<sub>2</sub>PdP<sub>2</sub>O<sub>7</sub> are in accordance with one independent site for phosphorus; its isotropic chemical shift  $\delta_{\text{iso}} = 21.5\text{ p.p.m.}$  is similar to that of Pd<sub>2</sub>P<sub>2</sub>O<sub>7</sub>.

**Related literature**

For related literature on palladium oxo-compounds, see: Arndt & Wickleder (2007); Dahmen *et al.* (1994); Laligant *et al.* (1991); Palkina *et al.* (1978); Panagiotidis *et al.* (2005b); Waser *et al.* (1953). For related literature on polyinary palladium phosphates, see: El Maadi *et al.* (2003); Laligant (1992a,b); Lii *et al.* (2004); For related literature on noble metal phosphates, see: Panagiotidis *et al.* (2005a, 2008). For background on chemical shift parameters, see: Moreno *et al.* (2002); Griffiths *et al.* (1986); Hayashi & Hayamizu (1989). For details of software used, see: Bak *et al.* (2000); Soose & Meyer (1980); Vosegaard *et al.* (2002).

**Experimental***Crystal data*

|   |  |
|---|--|
| Ag <sub>2</sub> PdP <sub>2</sub> O <sub>7</sub> | $V = 657.91\text{ (15)\AA}^3$            |
| $M_r = 496.10$                                  | $Z = 4$                                  |
| Monoclinic, C2/c                                | Mo $K\alpha$ radiation                   |
| $a = 15.739\text{ (2)\AA}$                      | $\mu = 9.08\text{ mm}^{-1}$              |
| $b = 5.7177\text{ (7)\AA}$                      | $T = 293\text{ (2)\text{K}}$             |
| $c = 8.187\text{ (1)\AA}$                       | $0.08 \times 0.05 \times 0.05\text{ mm}$ |
| $\beta = 116.75\text{ (1)}^\circ$               |  |

*Data collection*

|   |                                       |
|---|---------------------------------------|
| Enraf–Nonius CAD-4 diffractometer                               | 947 independent reflections           |
| Absorption correction: $\psi$ scan (North <i>et al.</i> , 1968) | 591 reflections with $I > 2\sigma(I)$ |
| $T_{\min} = 0.551$ , $T_{\max} = 0.631$                         | $R_{\text{int}} = 0.080$              |
| 1890 measured reflections                                       | 3 standard reflections                |
|   | frequency: 60 min                     |
|   | intensity decay: none                 |

*Refinement*

|                                 |  |
|---------------------------------|--|
| $R[F^2 > 2\sigma(F^2)] = 0.035$ | 58 parameters                                      |
| $wR(F^2) = 0.074$               | $\Delta\rho_{\text{max}} = 1.30\text{ e\AA}^{-3}$  |
| $S = 0.97$                      | $\Delta\rho_{\text{min}} = -1.14\text{ e\AA}^{-3}$ |
| 947 reflections                 |  |

Data collection: *CAD-4 EXPRESS* (Enraf–Nonius, 1994); cell refinement: *CAD-4 EXPRESS*; data reduction: *XCAD4* (Harms & Wocadlo, 1995); program(s) used to solve structure: *SHELXS97* (Sheldrick, 2008); program(s) used to refine structure: *SHELXL97* (Sheldrick, 2008); molecular graphics: *DIAMOND* (Brandenburg, 2008); software used to prepare material for publication: *WinGX* (Farrugia, 1999).

We thank Dr M. Schöneborn (University of Bonn) for the data collection. For the <sup>31</sup>P-MAS NMR measurement we thank Dr W. Hoffbauer (University of Bonn). A noble metal donation by UMICORE AG (Hanau–Wolfgang) is gratefully acknowledged.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: BR2086).

**References**

- Arndt, A. & Wickleder, M. S. (2007). *Eur. J. Inorg. Chem.* **27**, 4335–4339.
- Bak, M., Rasmussen, J. T. & Nielsen, N. C. (2000). *J. Magn. Reson.* **147**, 296–330.
- Brandenburg, K. (2008). *DIAMOND*. Crystal Impact GbR, Bonn, Germany.
- Dahmen, T., Rittner, P., Böger-Seidl, S. & Gruehn, R. (1994). *J. Alloys Compd.* **216**, 11–19.
- El Maadi, A., Bennazha, J., Réau, J. M., Boukhari, A. & Holt, E. M. (2003). *Mater. Res. Bull.* **38**, 865–874.
- Enraf–Nonius (1994). *CAD-4 EXPRESS*. Enraf–Nonius, Delft, The Netherlands.
- Farrugia, L. J. (1999). *J. Appl. Cryst.* **32**, 837–838.
- Griffiths, L., Root, A., Harris, R. K. & Parker, K. J. (1986). *J. Chem. Soc. Dalton Trans.* pp. 2247–2251.
- Harms, K. & Wocadlo, S. (1995). *XCAD4*. University of Marburg, Germany.
- Hayashi, S. & Hayamizu, K. (1989). *Bull. Chem. Soc. Jpn.* **62**, 3061–3068.
- Laligant, Y. (1992a). *Eur. J. Solid State Inorg. Chem.* **29**, 239–247.
- Laligant, Y. (1992b). *Eur. J. Solid State Inorg. Chem.* **29**, 83–94.
- Laligant, Y., Ferey, G. & Le Bail, A. (1991). *Mater. Res. Bull.* **26**, 269–275.
- Lii, K. H., Wang, S.-L. & Liao, F.-L. (2004). *Inorg. Chem.* **43**, 2499–2502.
- Moreno, B., Rodrigues, C. O., Bailey, B. N., Urbina, J. A., Moreno, S. N. J., Docampo, R. & Oldfield, E. (2002). *FEBS Lett.* **523**, 207–212.
- North, A. C. T., Phillips, D. C. & Mathews, F. S. (1968). *Acta Cryst.* **A24**, 351–359.
- Palkina, K. K., Maksimova, S. I., Lavrov, A. V. & Chalisova, N. A. (1978). *Dokl. Akad. Nauk SSSR*, **242**, 829–831.
- Panagiotidis, K. & Glaum, R. (2005a). *Phosphorus Res. Bull.* **19**, 77–84.
- Panagiotidis, K., Glaum, R., Schmedt auf der Günne, J. & Hoffbauer, W. (2008). *Z. Anorg. Allg. Chem.* **634**, 2922–2932.
- Panagiotidis, K., Glaum, R., Schmedt auf der Günne, J., Hoffbauer, W. & Görzel, H. (2005b). *Z. Anorg. Allg. Chem.* **631**, 2371–2376.
- Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.
- Soose, J. & Meyer, G. (1980). *SOS*. University of Giessen, Germany.
- Vosegaard, T., Malmendal, A. & Nielsen, N. C. (2002). *Monatsh. Chem.* **133**, 1555–1574.
- Waser, J., Levy, H. A. & Peterson, S. W. (1953). *Acta Cryst.* **6**, 661–663.

# supporting information

*Acta Cryst.* (2008). E64, i84 [doi:10.1107/S1600536808038518]

## Ag<sub>2</sub>PdP<sub>2</sub>O<sub>7</sub>

**Kosta Panagiotidis and Robert Glaum**

### S1. Comment

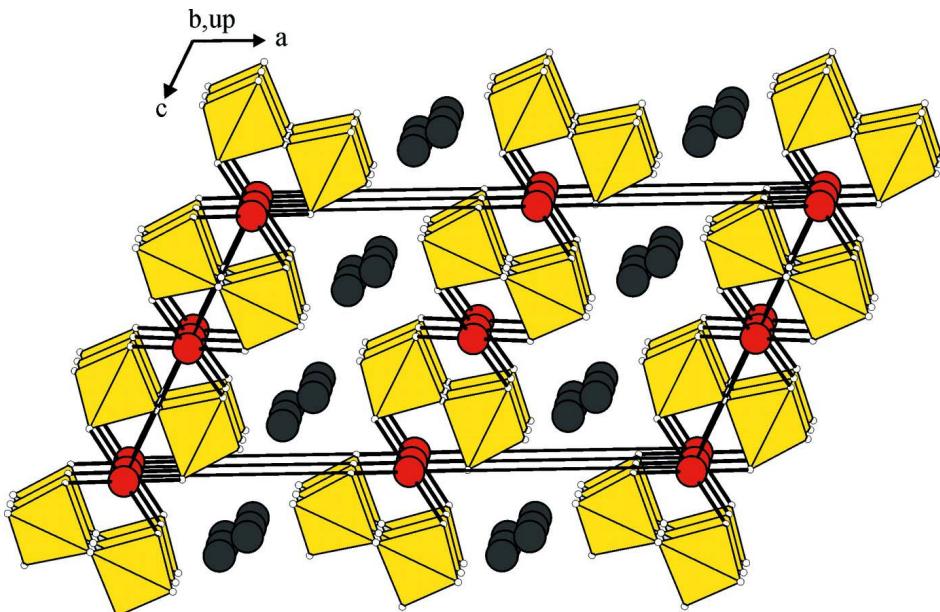

With the synthesis and crystal structure refinement of the first gold phosphate Au<sup>III</sup>PO<sub>4</sub> (Panagiotidis *et al.*, 2005a) and two modifications of Ir<sup>III</sup>(PO<sub>3</sub>)<sub>3</sub> (Panagiotidis *et al.*, 2008) we have widened the crystal chemical knowledge on anhydrous phosphates of the noble metals. Investigations in the ternary system Pd/P/O provided, apart from the already existing phosphates Pd(PO<sub>3</sub>)<sub>2</sub> (Palkina *et al.*, 1978) and Pd<sub>2</sub>P<sub>2</sub>O<sub>7</sub> (Panagiotidis *et al.*, 2005b), no evidence for further thermodynamically stable palladium phosphates. Due to our interest in network structures built from square-planar units [MO<sub>4</sub>] ( $M = \text{Pd}^{\text{II}}, \text{Au}^{\text{III}}$ ) and phosphate tetrahedra we focused therefore our search on polyinary palladium phosphates. Polyinary phosphates of divalent palladium are rare in literature. Up to now, only the compositions  $M^{\text{I}}_2\text{PdP}_2\text{O}_7$  ( $M = \text{Li}$  (Laligant, 1992a), Na (Laligant, 1992b), K (El Maadi *et al.*, 2003), K<sub>3.5</sub>Pd<sub>2.25</sub>(P<sub>2</sub>O<sub>7</sub>)<sub>2</sub> (El Maadi *et al.*, 2003) and Cs<sub>2</sub>Pd<sub>3</sub>(P<sub>2</sub>O<sub>7</sub>)<sub>2</sub> (Lii *et al.*, 2004) were reported. In Pd<sub>2</sub>P<sub>2</sub>O<sub>7</sub> itself, Li<sub>2</sub>PdP<sub>2</sub>O<sub>7</sub>, and Na<sub>2</sub>PdP<sub>2</sub>O<sub>7</sub> infinite ribbons [Pd(P<sub>2</sub>O<sub>7</sub>)<sub>2/2</sub>]<sup>2-</sup> are the characteristic structural motif. K<sub>2</sub>PdP<sub>2</sub>O<sub>7</sub> adopts a layer structure with the crystal chemical composition [Pd(P<sub>2</sub>O<sub>7</sub>)<sub>4/4</sub>]<sup>2-</sup>. The structures of K<sub>3.5</sub>Pd<sub>2.25</sub>(P<sub>2</sub>O<sub>7</sub>)<sub>2</sub> and Cs<sub>2</sub>Pd<sub>3</sub>(P<sub>2</sub>O<sub>7</sub>)<sub>2</sub> consist of [Pd<sup>II</sup>O<sub>4</sub>] and [P<sub>2</sub>O<sub>7</sub>] groups generating a three-dimensional framework.

According to our X-ray single-crystal study Ag<sub>2</sub>PdP<sub>2</sub>O<sub>7</sub> is isotropic to Na<sub>2</sub>PdP<sub>2</sub>O<sub>7</sub>. The unit cell contains four formula units Ag<sub>2</sub>PdP<sub>2</sub>O<sub>7</sub> with one crystallographically independent site for silver, palladium and phosphorus (Fig. 1). As in the crystal structures of PdO (Waser *et al.*, 1953),  $M\text{-Pd}^{\text{II}}\text{SO}_4$  (Dahmen *et al.*, 1994), Pd<sup>II</sup>(NO<sub>3</sub>)<sub>2</sub>(H<sub>2</sub>O)<sub>2</sub> (Laligant *et al.*, 1991), and Pd<sub>2</sub>P<sub>2</sub>O<sub>7</sub> the Pd<sup>2+</sup> ions show a square-planar coordination by oxygen. In Ag<sub>2</sub>PdP<sub>2</sub>O<sub>7</sub> palladium is coordinated in a chelating way by two [P<sub>2</sub>O<sub>7</sub>] groups. This coordination mode, with a, for such diphosphates typically observed, bridging angle  $\langle(\text{P}-\text{O}2-\text{P}) = 124.9^\circ$ , leads to the formation of corrugated ribbons [Pd(P<sub>2</sub>O<sub>7</sub>)<sub>2/2</sub>]<sup>2-</sup> (Fig. 2). These ribbons are linked by significantly distorted [Ag<sup>I</sup>O<sub>6</sub>] octahedra. Due to different crystal chemical environment of the four independent oxygen atoms, with O1 forming one bond to P and two to Ag, O2 forming two bonds to P and O3 and O4 forming one bond each to P, Pd and Ag, a radial distortion of the phosphate groups with one very short, two medium long and one elongated distance d(P—O) is observed. In accordance with the crystal structure of Ag<sub>2</sub>PdP<sub>2</sub>O<sub>7</sub> <sup>31</sup>P-MAS-NMR investigations (Varian Infinity Plus, 9.4 tesla-magnet, 2.5-mm MAS double resonance NMR probe, rotation frequency 3.0 kHz) show the presence of just one phosphorus site. Chemical shift parameters were determined by means of numerically calculated spectra (programme SIMPSION (Bak *et al.*, 2000), MINUIT routine in SIMPSION (Vosegaard *et al.*, 2002)) to  $\delta_{\text{iso}} = 21.5$  p.p.m.,  $\delta_{\text{aniso}} = 79.0$  p.p.m. and  $\eta = 0.87$ . The chemical shifts are reported in parts per million (p.p.m.) from the external standard 85% H<sub>3</sub>PO<sub>4</sub>. As in Pd<sub>2</sub>P<sub>2</sub>O<sub>7</sub> ( $\eta = 0.86$ ) and in contrast to other diphosphates (Moreno *et al.*, 2002; Griffiths *et al.*, 1986; Hayashi & Hayamizu, 1989) a remarkably high value for  $\eta$  is observed. The isotropical chemical shift of Ag<sub>2</sub>PdP<sub>2</sub>O<sub>7</sub> which is similar to the one observed for Pd<sub>2</sub>P<sub>2</sub>O<sub>7</sub> ( $\delta_{\text{iso}} = 28.3$  p.p.m.) is exceptionally high in comparison to  $\delta_{\text{iso}}$  values of diphosphates of the alkaline and alkaline earth metals (Moreno *et al.*, 2002; Griffiths *et al.*, 1986; Hayashi & Hayamizu, 1989). We attribute this observation to significant covalency in the Pd—O interaction.


**S2. Experimental**

Microcrystalline  $\text{Ag}_2\text{PdP}_2\text{O}_7$  was synthesized *via* a solid state reaction by heating an amorphous precursor for 24 h at  $T = 773$  K in air. The precursor was obtained by drying a mixture of 100.0 mg (0.94 mmol) palladium powder (99.99%, UMICORE AG, Hanau-Wolfgang) with an excess of conc. nitric acid and stoichiometric amounts of 319.2 mg  $\text{AgNO}_3$  (1.88 mmol) (p.A., Merck) and 18.8 ml  $\text{H}_3\text{PO}_4$  (0.1 M) at 423 K as a brownish powder.

Isothermal heating of 100.0 mg (0.82 mmol)  $\text{PdO}$ , 189.3 mg (0.82 mmol)  $\text{Ag}_2\text{O}$  (p.A. Merck) and 116.0 mg (0.41 mmol)  $\text{P}_4\text{O}_{10}$  (99%, Riedel de Häen) (addition of 8.0 mg  $\text{PdCl}_2$  as mineralizer) carried out in sealed and evacuated silica tubes at 773 K for seven days gave besides microcrystalline, single-phase  $\text{Ag}_2\text{PdP}_2\text{O}_7$  (eq. 1) also small amounts of yellow plate-like single crystals which were distributed over the whole ampoule.

**Figure 1**

Projection of the crystal structure of  $\text{Ag}_2\text{PdP}_2\text{O}_7$  along [010] with tetrahedral  $[\text{PO}_4]$  units (yellow),  $\text{Pd}^{2+}$  (red) and  $\text{Ag}^+$  grey (*DIAMOND v3.1f*).

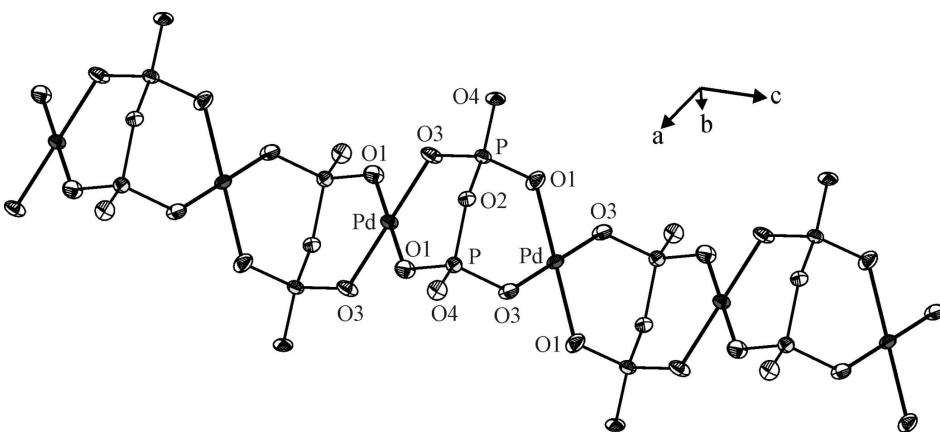

**Figure 2**

Diphosphato-palladate(II) ribbon  $[\text{Pd}(\text{P}_2\text{O}_7)_{2/2}]^{2-}$  along [001]. Thermal ellipsoids with 50% probability (*DIAMOND*, v3.1f).

**Disilver(I) palladium(II) diphosphate***Crystal data*

$\text{Ag}_2\text{PdP}_2\text{O}_7$   
 $M_r = 496.10$   
Monoclinic,  $C2/c$   
Hall symbol: -C 2yc  
 $a = 15.739 (2)$  Å  
 $b = 5.7177 (7)$  Å  
 $c = 8.187 (1)$  Å  
 $\beta = 116.75 (1)^\circ$   
 $V = 657.91 (15)$  Å<sup>3</sup>  
 $Z = 4$   
 $F(000) = 904$

The lattice parameters given were refined with the program SOS (Soose & Meyer, 1980), using 40 reflections from a Guinier IP photograph.

$D_x = 5.008 \text{ Mg m}^{-3}$   
Mo  $K\alpha$  radiation,  $\lambda = 0.71073$  Å  
Cell parameters from 40 reflections  
 $\theta = 6.3\text{--}34.3^\circ$   
 $\mu = 9.08 \text{ mm}^{-1}$   
 $T = 293$  K  
Prism, yellow  
 $0.08 \times 0.05 \times 0.05$  mm

*Data collection*

Enraf–Nonius CAD-4  
diffractometer  
Radiation source: fine-focus sealed tube  
Graphite monochromator  
Nonprofiled  $\omega$  scans  
Absorption correction:  $\psi$  scan  
(North *et al.*, 1968)  
 $T_{\min} = 0.551$ ,  $T_{\max} = 0.631$   
1890 measured reflections

947 independent reflections  
591 reflections with  $I > 2\sigma(I)$   
 $R_{\text{int}} = 0.080$   
 $\theta_{\max} = 29.9^\circ$ ,  $\theta_{\min} = 2.9^\circ$   
 $h = -22 \rightarrow 22$   
 $k = -8 \rightarrow 0$   
 $l = -11 \rightarrow 11$   
3 standard reflections every 60 min  
intensity decay: none

*Refinement*

Refinement on  $F^2$   
Least-squares matrix: full  
 $R[F^2 > 2\sigma(F^2)] = 0.035$   
 $wR(F^2) = 0.074$   
 $S = 0.97$   
947 reflections  
58 parameters  
0 restraints  
0 constraints  
Primary atom site location: structure-invariant  
direct methods

Secondary atom site location: difference Fourier  
map  
 $w = 1/[\sigma^2(F_o^2) + (0.0245P)^2]$   
where  $P = (F_o^2 + 2F_c^2)/3$   
 $(\Delta/\sigma)_{\max} < 0.001$   
 $\Delta\rho_{\max} = 1.30 \text{ e } \text{\AA}^{-3}$   
 $\Delta\rho_{\min} = -1.14 \text{ e } \text{\AA}^{-3}$   
Extinction correction: *SHELXL97* (Sheldrick, 2008),  $F_c^* = kFc[1 + 0.001xFc^2\lambda^3/\sin(2\theta)]^{-1/4}$   
Extinction coefficient: 0.00104 (17)

*Special details*

**Geometry.** All e.s.d.'s are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances and angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry.

**Refinement.** Refinement of  $F^2$  against ALL reflections. The weighted  $R$ -factor  $wR$  and goodness of fit  $S$  are based on  $F^2$ , conventional  $R$ -factors  $R$  are based on  $F$ , with  $F$  set to zero for negative  $F^2$ . The threshold expression of  $F^2 > \sigma(F^2)$  is used only for calculating  $R$ -factors(gt) *etc.* and is not relevant to the choice of reflections for refinement.  $R$ -factors based on  $F^2$  are statistically about twice as large as those based on  $F$ , and  $R$ -factors based on ALL data will be even larger.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters ( $\text{\AA}^2$ )

|     | <i>x</i>     | <i>y</i>     | <i>z</i>    | $U_{\text{iso}}^*/U_{\text{eq}}$ |
|-----|--------------|--------------|-------------|----------------------------------|
| Pd1 | 0            | 0            | 0           | 0.0145 (2)                       |
| Ag1 | 0.23426 (5)  | 0.85894 (13) | 0.79398 (9) | 0.0217 (2)                       |
| P1  | 0.10116 (14) | 0.3445 (4)   | 0.8422 (3)  | 0.0137 (4)                       |
| O1  | 0.8200 (4)   | 0.5226 (10)  | 0.5959 (7)  | 0.0177 (13)                      |
| O2  | 0            | 0.4744 (14)  | 0.75        | 0.0139 (16)                      |
| O3  | 0.8949 (4)   | 0.1859 (11)  | 0.8057 (7)  | 0.0220 (14)                      |
| O4  | 0.6031 (4)   | 0.2953 (11)  | 0.5045 (8)  | 0.0213 (14)                      |

Atomic displacement parameters ( $\text{\AA}^2$ )

|     | $U^{11}$   | $U^{22}$    | $U^{33}$   | $U^{12}$    | $U^{13}$   | $U^{23}$    |
|-----|------------|-------------|------------|-------------|------------|-------------|
| Pd1 | 0.0103 (4) | 0.0178 (5)  | 0.0135 (4) | -0.0012 (4) | 0.0036 (3) | 0.0055 (4)  |
| Ag1 | 0.0197 (4) | 0.0247 (4)  | 0.0171 (3) | -0.0044 (3) | 0.0050 (3) | -0.0017 (3) |
| P1  | 0.0111 (9) | 0.0152 (11) | 0.0146 (9) | -0.0028 (9) | 0.0055 (8) | 0.0003 (10) |
| O1  | 0.016 (3)  | 0.016 (3)   | 0.019 (3)  | 0.011 (3)   | 0.006 (2)  | 0.005 (3)   |
| O2  | 0.014 (4)  | 0.011 (4)   | 0.015 (4)  | 0           | 0.006 (3)  | 0           |
| O3  | 0.018 (3)  | 0.027 (4)   | 0.019 (3)  | -0.003 (3)  | 0.007 (3)  | 0.010 (3)   |
| O4  | 0.011 (3)  | 0.026 (4)   | 0.023 (3)  | 0.004 (3)   | 0.004 (2)  | -0.012 (3)  |

Geometric parameters ( $\text{\AA}$ ,  $^\circ$ )

|  |             |  |            |
|--|-------------|--|------------|
| Pd1—O4 <sup>i</sup>                        | 1.987 (5)   | P1—O4 <sup>x</sup>                         | 1.539 (6)  |
| Pd1—O4 <sup>ii</sup>                       | 1.987 (5)   | P1—O2                                      | 1.605 (4)  |
| Pd1—O3 <sup>iii</sup>                      | 2.007 (6)   | O1—P1 <sup>vii</sup>                       | 1.505 (6)  |
| Pd1—O3 <sup>iv</sup>                       | 2.007 (6)   | O1—Ag1 <sup>xi</sup>                       | 2.321 (5)  |
| Ag1—O1 <sup>v</sup>                        | 2.321 (5)   | O1—Ag1 <sup>vii</sup>                      | 2.436 (6)  |
| Ag1—O4 <sup>vi</sup>                       | 2.368 (6)   | O2—P1 <sup>xii</sup>                       | 1.605 (4)  |
| Ag1—O1 <sup>vii</sup>                      | 2.436 (6)   | O3—P1 <sup>vii</sup>                       | 1.537 (6)  |
| Ag1—Ag1 <sup>viii</sup>                    | 3.0427 (6)  | O3—Pd1 <sup>xiii</sup>                     | 2.007 (6)  |
| Ag1—Ag1 <sup>ix</sup>                      | 3.0427 (6)  | O4—P1 <sup>xiv</sup>                       | 1.539 (6)  |
| P1—O1 <sup>vii</sup>                       | 1.505 (6)   | O4—Pd1 <sup>xv</sup>                       | 1.987 (5)  |
| P1—O3 <sup>vii</sup>                       | 1.537 (6)   | O4—Ag1 <sup>xvi</sup>                      | 2.368 (5)  |
| O4 <sup>i</sup> —Pd1—O4 <sup>ii</sup>      | 180.0 (4)   | Ag1 <sup>viii</sup> —Ag1—Ag1 <sup>ix</sup> | 139.96 (5) |
| O4 <sup>i</sup> —Pd1—O3 <sup>iii</sup>     | 94.5 (2)    | O1 <sup>vii</sup> —P1—O3 <sup>vii</sup>    | 110.2 (3)  |
| O4 <sup>ii</sup> —Pd1—O3 <sup>iii</sup>    | 85.5 (2)    | O1 <sup>vii</sup> —P1—O4 <sup>x</sup>      | 111.6 (3)  |
| O4 <sup>i</sup> —Pd1—O3 <sup>iv</sup>      | 85.5 (2)    | O3 <sup>vii</sup> —P1—O4 <sup>x</sup>      | 112.4 (4)  |
| O4 <sup>ii</sup> —Pd1—O3 <sup>iv</sup>     | 94.5 (2)    | O1 <sup>vii</sup> —P1—O2                   | 109.8 (4)  |
| O3 <sup>iii</sup> —Pd1—O3 <sup>iv</sup>    | 180.0 (6)   | O3 <sup>vii</sup> —P1—O2                   | 106.6 (3)  |
| O1 <sup>v</sup> —Ag1—O4 <sup>vi</sup>      | 159.7 (2)   | O4 <sup>x</sup> —P1—O2                     | 106.0 (3)  |
| O1 <sup>v</sup> —Ag1—O1 <sup>vii</sup>     | 88.23 (19)  | P1 <sup>vii</sup> —O1—Ag1 <sup>xi</sup>    | 123.5 (3)  |
| O4 <sup>vi</sup> —Ag1—O1 <sup>vii</sup>    | 87.5 (2)    | P1 <sup>vii</sup> —O1—Ag1 <sup>vii</sup>   | 141.5 (3)  |
| O1 <sup>v</sup> —Ag1—Ag1 <sup>viii</sup>   | 116.60 (15) | Ag1 <sup>xi</sup> —O1—Ag1 <sup>vii</sup>   | 91.77 (19) |
| O4 <sup>vi</sup> —Ag1—Ag1 <sup>viii</sup>  | 77.30 (15)  | P1 <sup>xii</sup> —O2—P1                   | 124.9 (5)  |
| O1 <sup>vii</sup> —Ag1—Ag1 <sup>viii</sup> | 57.82 (14)  | P1 <sup>vii</sup> —O3—Pd1 <sup>xiii</sup>  | 128.7 (3)  |

|  |             |  |           |
|--|-------------|--|-----------|
| O1 <sup>v</sup> —Ag1—Ag1 <sup>ix</sup>   | 84.21 (15)  | P1 <sup>xiv</sup> —O4—Pd1 <sup>xv</sup>  | 126.2 (3) |
| O4 <sup>vi</sup> —Ag1—Ag1 <sup>ix</sup>  | 93.96 (16)  | P1 <sup>xiv</sup> —O4—Ag1 <sup>xvi</sup> | 127.8 (3) |
| O1 <sup>vii</sup> —Ag1—Ag1 <sup>ix</sup> | 161.97 (14) | Pd1 <sup>xv</sup> —O4—Ag1 <sup>xvi</sup> | 105.4 (2) |

Symmetry codes: (i)  $x-1/2, -y+1/2, z-1/2$ ; (ii)  $-x+1/2, y-1/2, -z+1/2$ ; (iii)  $x-1, y, z-1$ ; (iv)  $-x+1, -y, -z+1$ ; (v)  $x-1/2, -y+3/2, z+1/2$ ; (vi)  $x-1/2, y+1/2, z$ ; (vii)  $-x+1, y, -z+3/2$ ; (viii)  $-x+1/2, y-1/2, -z+3/2$ ; (ix)  $-x+1/2, y+1/2, -z+3/2$ ; (x)  $x-1/2, -y+1/2, z+1/2$ ; (xi)  $x+1/2, -y+3/2, z-1/2$ ; (xii)  $-x, y, -z+3/2$ ; (xiii)  $x+1, y, z+1$ ; (xiv)  $x+1/2, -y+1/2, z-1/2$ ; (xv)  $-x+1/2, y+1/2, -z+1/2$ ; (xvi)  $x+1/2, y-1/2, z$ .