

# Two-dimensional dysprosium(III) triiodate(V) dihydrate, $\text{Dy}(\text{IO}_3)_3(\text{H}_2\text{O})\cdot\text{H}_2\text{O}$

Wenxiang Chai,<sup>a\*</sup> Li Song,<sup>b</sup> Hongsheng Shi,<sup>a</sup> Laishun Qin<sup>a</sup> and Kangying Shu<sup>a</sup>

<sup>a</sup>College of Materials Science and Engineering, China Jiliang University, Hangzhou 310018, People's Republic of China, and <sup>b</sup>Department of Chemistry, Key Laboratory of Advanced Textile Materials and Manufacturing Technology of the Education Ministry, Zhejiang Sci-Tech University, Hangzhou 310018, People's Republic of China

Correspondence e-mail: wxchai\_cm@yahoo.com.cn

Received 1 July 2009; accepted 10 July 2009

Key indicators: single-crystal X-ray study;  $T = 293\text{ K}$ ; mean  $\sigma(\text{Dy}-\text{O}) = 0.008\text{ \AA}$ ;  $R$  factor = 0.038;  $wR$  factor = 0.109; data-to-parameter ratio = 16.0.

During our research into novel nonlinear optical materials using 1,10-phenanthroline as an appending ligand on lanthanide iodates, crystals of an infinite layered  $\text{Dy}^{\text{III}}$  iodate compound,  $\text{Dy}(\text{IO}_3)_3(\text{H}_2\text{O})\cdot\text{H}_2\text{O}$ , were obtained under hydrothermal conditions. The  $\text{Dy}^{\text{III}}$  cation has a dicapped trigonal prismatic coordination environment consisting of one water O atom and seven other O atoms from seven iodate anions. These iodate anions bridge the  $\text{Dy}^{\text{III}}$  cations into a two-dimensional structure. Through  $\text{O}-\text{H}\cdots\text{O}$  hydrogen bonds, all of these layers stack along [111], giving a supramolecular channel, with the solvent water molecules filling the voids.

## Related literature

For related materials with non-linear optical properties, see: Rosenzweig & Morosin (1966); Liminga *et al.* (1977); Ok & Halasyamani (2005). The method of preparation was based on  $\text{HIO}_3$ , which is different to the previous method of obtaining periodates (Douglas *et al.*, 2004; Assefa *et al.*, 2006). For noncentrosymmetric inorganic-organic framework structures synthesized from organic ligands, see: Sun *et al.* (2009). For related structures, see: Sun *et al.* (2009); Assefa *et al.* (2006); Douglas *et al.* (2004); Ok & Halasyamani (2005); Chen *et al.* (2005).

## Experimental

### Crystal data

$\text{Dy}(\text{IO}_3)_3\cdot\text{H}_2\text{O}\cdot\text{H}_2\text{O}$   
 $M_r = 723.23$   
 Triclinic,  $P\bar{1}$   
 $a = 7.15990(10)\text{ \AA}$   
 $b = 7.4292(1)\text{ \AA}$   
 $c = 10.64430(10)\text{ \AA}$

$\alpha = 95.161(12)^\circ$   
 $\beta = 104.858(7)^\circ$   
 $\gamma = 110.081(8)^\circ$   
 $V = 504.00(5)\text{ \AA}^3$   
 $Z = 2$   
 Mo  $K\alpha$  radiation

$\mu = 16.65\text{ mm}^{-1}$   
 $T = 293\text{ K}$

$0.16 \times 0.12 \times 0.06\text{ mm}$

### Data collection

Rigaku R-Axis RAPID diffractometer  
 Absorption correction: multi-scan (ABSCOR; Higashi, 1995)  
 $T_{\text{min}} = 0.136$ ,  $T_{\text{max}} = 0.435$   
 (expected range = 0.115–0.368)

3819 measured reflections  
 2260 independent reflections  
 2067 reflections with  $I > 2\sigma(I)$   
 $R_{\text{int}} = 0.027$

### Refinement

$R[F^2 > 2\sigma(F^2)] = 0.038$   
 $wR(F^2) = 0.109$   
 $S = 1.06$   
 2260 reflections  
 141 parameters  
 2 restraints

H atoms treated by a mixture of independent and constrained refinement  
 $\Delta\rho_{\text{max}} = 2.79\text{ e \AA}^{-3}$   
 $\Delta\rho_{\text{min}} = -3.20\text{ e \AA}^{-3}$

Table 1

Hydrogen-bond geometry ( $\text{\AA}$ ,  $^\circ$ ).

$D-H\cdots A$	$D-H$	$H\cdots A$	$D\cdots A$	$D-H\cdots A$
$\text{O}10-\text{H}10A\cdots\text{O}3^{\text{i}}$	0.80	2.29	2.873 (10)	131
$\text{O}10-\text{H}10B\cdots\text{O}9^{\text{j}}$	0.80	2.33	2.753 (11)	114
$\text{O}11-\text{H}11A\cdots\text{O}8^{\text{ii}}$	0.80	2.22	2.954 (11)	153
$\text{O}11-\text{H}11B\cdots\text{O}7^{\text{iii}}$	0.80	2.26	2.946 (11)	145

Symmetry codes: (i)  $x, y-1, z$ ; (ii)  $x, y-1, z+1$ ; (iii)  $-x, -y-1, -z$ .

Data collection: *PROCESS-AUTO* (Rigaku, 1998); cell refinement: *PROCESS-AUTO*; data reduction: *CrystalStructure* (Rigaku/MS, 2004); program(s) used to solve structure: *SHELXS97* (Sheldrick, 2008); program(s) used to refine structure: *SHELXL97* (Sheldrick, 2008) and *PLATON* (Spek, 2009; van der Sluis & Spek, 1990); molecular graphics: *SHELXTL* (Sheldrick, 2008); software used to prepare material for publication: *SHELXTL*.

The authors are grateful for financial support from the National Natural Science Foundation of China (project Nos. 50702054 and 20803070) and the Analysis and Testing Foundation of Zhejiang Province (project Nos. 2008F70034 and 2008F70053).

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: BR2111).

## References

- Assefa, Z., Ling, J., Haire, R. G., Albrecht-Schmitt, T. E. & Sykora, R. E. (2006). *J. Solid State Chem.* **179**, 3653–3663.  
 Chen, X. A., Xue, H. P., Chang, X. N., Zang, H. G. & Xiao, W. Q. (2005). *J. Alloys Compd.* **398**, 173–177.  
 Douglas, P., Hector, A. L., Levason, W., Light, M. E., Matthews, M. L. & Webster, M. (2004). *Z. Anorg. Allg. Chem.* **630**, 479–483.  
 Higashi, T. (1995). *ABSCOR*. Rigaku Corporation, Tokyo, Japan.  
 Liminga, R., Abrahams, S. C. & Bernstein, J. L. (1977). *J. Chem. Phys.* **67**, 1015–1023.  
 Ok, K. M. & Halasyamani, P. S. (2005). *Inorg. Chem.* **44**, 9353–9359.  
 Rigaku (1998). *PROCESS-AUTO*. Rigaku Corporation, Tokyo, Japan.  
 Rigaku/MS (2004). *CrystalStructure*. Rigaku/MS, The Woodlands, Texas, USA.  
 Rosenzweig, A. & Morosin, B. (1966). *Acta Cryst.* **20**, 758–761.  
 Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.

Sluis, P. van der & Spek, A. L. (1990). *Acta Cryst.* **A46**, 194–201.  
Spek, A. L. (2009). *Acta Cryst.* **D65**, 148–155.

Sun, Y.-G., Guo, M., Xiong, G., Jiang, B. & Wang, L. (2009). *Acta Cryst.* **E65**, i48.

## supporting information

*Acta Cryst.* (2009). E65, i61–i62 [doi:10.1107/S1600536809027068]

**Two-dimensional dysprosium(III) triiodate(V) dihydrate,  $\text{Dy}(\text{IO}_3)_3(\text{H}_2\text{O})\cdot\text{H}_2\text{O}$** 

Wenxiang Chai, Li Song, Hongsheng Shi, Laishun Qin and Kangying Shu

**S1. Comment**

In the 1970s, metal iodates have been extensively studied by Bell Laboratories not only for their nonlinear optical (NLO) properties but also for ferroelectric, piezoelectric and pyroelectric properties (Rosenzweig & Morosin, 1966; Liminga *et al.*, 1977). In attempts to prepare noncentrosymmetric structures of lanthanide iodates, about six anhydrous structure types have been reported, in addition to numerous hydrated structures ranging from hemihydrates to pentahydrates. (Assefa *et al.*, 2006). After comparing these structure types, herein, we find that the hydrated structures favor of adopting centrosymmetric structures. Then organic ligands are come into our view because they could form noncentrosymmetric inorganic–organic framework structures with metal ion. (Sun *et al.*, 2009). Here, we firstly report a infinite layered  $\text{Dy}^{\text{III}}$  iodate dihydrate synthesized from the hydrothermal reaction of  $\text{Dy}_2\text{O}_3$ ,  $\text{HIO}_3$  and 1,10-phenanthroline.

In the title compound, the  $\text{Dy}^{\text{III}}$  cation has dicapped trigonal prismatic coordination sphere. The coordination environments of the rare earth  $\text{Dy}^{\text{III}}$  cation consist of eight O atoms derived from seven iodate anions and one water molecule (see Fig. 1). And these seven iodates are classed two types, one is three 3-connected iodates (of I2) through three O atoms, and the other is four iodates 2-connected (of I1 or I3) through two O atoms. Then these iodate anions bridge Dy atoms into two dimensional structure. And between the adjacent layers, there are two types of hydrogen bonds, one is  $\text{O10}—\text{H10A}\cdots\text{O3}$  bond, the other is  $\text{O10}—\text{H10B}\cdots\text{O9}$  bond. Then through these hydrogen bonds, all of these layers stacking along [111] axis to give out of a supramolecular channel. And the solvent water molecules fill in the channels, and stick on the channel with two hydrogen bonds of  $\text{O11}—\text{H11A}\cdots\text{O8}$  and  $\text{O11}—\text{H11B}\cdots\text{O7}$ . (see Fig. 2) The hydrogen bonding data of lengths and angles are in the range of ordinary examples and have been examined by the *PLATON* program (Spek, 2009; van der Sluis & Spek, 1990).


**S2. Experimental**

All chemicals were obtained from commercial sources and were used as received. The title compound was handily synthesized by a hydrothermal reaction from iodic acid. To a 25 ml stainless steel Teflon-lined reaction vessel,  $\text{Dy}_2\text{O}_3$  (0.2 mmol, 75 mg),  $\text{HIO}_3$  (0.8 mmol, 141 mg), 1,10-phenanthroline (0.4 mmol, 80 mg) and 13 ml  $\text{H}_2\text{O}$  were added and stirred thoroughly for 1 h, then heated at 393 K for 2 d. After cooling down to room temperature, some colorless crystalline product (I) was obtained.

**S3. Refinement**


The structure was solved using direct methods and refined by full-matrix least-squares techniques. All non-hydrogen atoms were assigned anisotropic displacement parameters in the refinement. All H atoms were added at calculated positions and refined using a riding model. (Sheldrick, 2008). The maximum (2.79) and minimum (-3.20) in the difference electron density were found at 0.0198 0.3244 0.7024 [1.01 Å from DY1] and 0.2071 0.4512 0.7963 [0.60 Å from DY1], respectively.

The O6 has ADP max/min ratio 6.70. This result may be due to the packing of supramolecule.

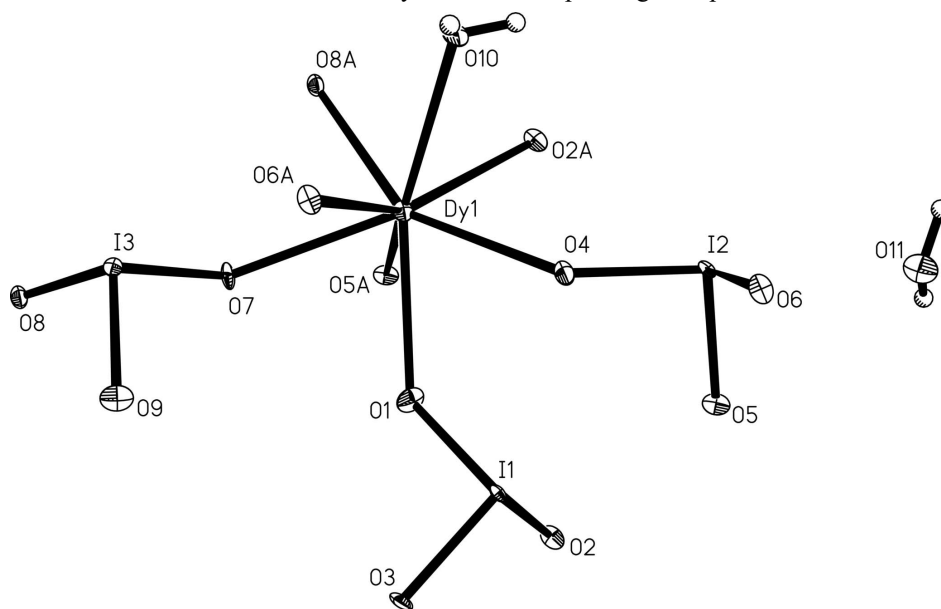

**Figure 1**

Structure and labeling of the title compound, with displacement ellipsoids drawn at the 30% probability level and H atoms shown as small spheres of arbitrary radii.

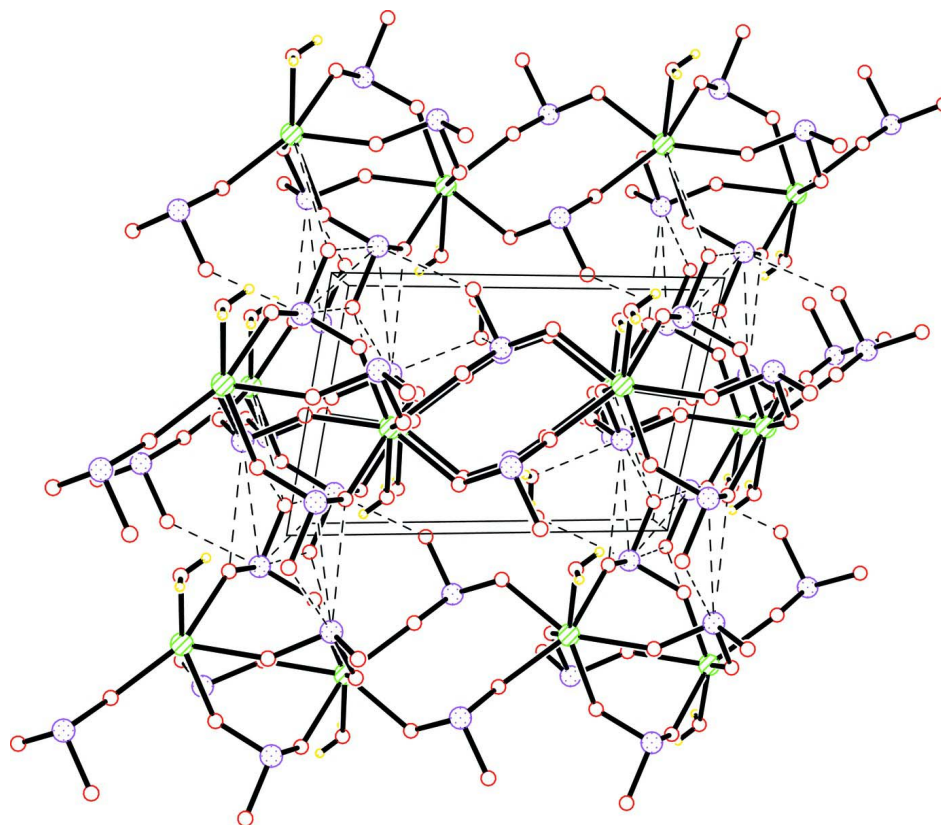**Figure 2**

The packing diagram viewed along the a-direction, Dy: green diagonal; I: purple inner dot; O: red; and H: small blue circles. And hydrogen bonds are denoted as dash lines.

### dysprosium(III) triiodate(V) dihydrate

#### Crystal data

$\text{Dy}(\text{IO}_3)_3 \cdot \text{H}_2\text{O} \cdot \text{H}_2\text{O}$

$M_r = 723.23$

Triclinic,  $P\bar{1}$

Hall symbol:  $-P\ 1$

$a = 7.1599\ (1)\ \text{\AA}$

$b = 7.4292\ (1)\ \text{\AA}$

$c = 10.6443\ (1)\ \text{\AA}$

$\alpha = 95.161\ (12)^\circ$

$\beta = 104.858\ (7)^\circ$

$\gamma = 110.081\ (8)^\circ$

$V = 504.00\ (5)\ \text{\AA}^3$

$Z = 2$

$F(000) = 634$

$D_x = 4.766\ \text{Mg m}^{-3}$

Mo  $K\alpha$  radiation,  $\lambda = 0.71075\ \text{\AA}$

Cell parameters from 1561 reflections

$\theta = 2.0\text{--}27.5^\circ$

$\mu = 16.65\ \text{mm}^{-1}$

$T = 293\ \text{K}$

Block, colourless

$0.16 \times 0.12 \times 0.06\ \text{mm}$

#### Data collection

Rigaku R-AXIS RAPID  
diffractometer

Radiation source: fine-focus sealed tube  
Graphite monochromator

Detector resolution:  $14.6306\ \text{pixels mm}^{-1}$

CCD profile fitting scans

Absorption correction: multi-scan  
(*ABSCOR*; Higashi, 1995)

$T_{\min} = 0.136$ ,  $T_{\max} = 0.435$

3819 measured reflections

2260 independent reflections

2067 reflections with  $I > 2\sigma(I)$

$R_{\text{int}} = 0.027$

$\theta_{\max} = 27.5^\circ$ ,  $\theta_{\min} = 3.2^\circ$   
 $h = -9 \rightarrow 9$

$k = -7 \rightarrow 9$   
 $l = -13 \rightarrow 13$

*Refinement*

Refinement on  $F^2$   
 Least-squares matrix: full  
 $R[F^2 > 2\sigma(F^2)] = 0.038$   
 $wR(F^2) = 0.109$   
 $S = 1.06$   
 2260 reflections  
 141 parameters  
 2 restraints  
 Primary atom site location: structure-invariant  
 direct methods  
 Secondary atom site location: difference Fourier  
 map

Hydrogen site location: inferred from  
 neighbouring sites  
 H atoms treated by a mixture of independent  
 and constrained refinement  
 $w = 1/[\sigma^2(F_o^2) + (0.0647P)^2 + 5.3292P]$   
 where  $P = (F_o^2 + 2F_c^2)/3$   
 $(\Delta/\sigma)_{\max} < 0.001$   
 $\Delta\rho_{\max} = 2.79 \text{ e } \text{\AA}^{-3}$   
 $\Delta\rho_{\min} = -3.20 \text{ e } \text{\AA}^{-3}$   
 Extinction correction: *SHELXL97* (Sheldrick,  
 2008),  $F_c^* = kF_c[1 + 0.001x F_c^2 \lambda^3 / \sin(2\theta)]^{-1/4}$   
 Extinction coefficient: 0.0126 (8)

*Special details*

**Geometry.** All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

**Refinement.** Refinement of  $F^2$  against ALL reflections. The weighted  $R$ -factor  $wR$  and goodness of fit  $S$  are based on  $F^2$ , conventional  $R$ -factors  $R$  are based on  $F$ , with  $F$  set to zero for negative  $F^2$ . The threshold expression of  $F^2 > \sigma(F^2)$  is used only for calculating  $R$ -factors(gt) *etc.* and is not relevant to the choice of reflections for refinement.  $R$ -factors based on  $F^2$  are statistically about twice as large as those based on  $F$ , and  $R$ -factors based on ALL data will be even larger.

*Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters ( $\text{\AA}^2$ )*

	<i>x</i>	<i>y</i>	<i>z</i>	$U_{\text{iso}}^*/U_{\text{eq}}$
Dy1	0.11491 (7)	-0.58338 (7)	-0.21096 (4)	0.01105 (18)
I1	0.30890 (8)	-0.14149 (8)	0.07303 (5)	0.00659 (18)
I2	0.28110 (8)	-0.63445 (8)	0.16834 (5)	0.00652 (18)
I3	0.27848 (9)	-0.26870 (9)	-0.45631 (6)	0.00862 (19)
O1	0.1496 (11)	-0.2711 (12)	-0.0929 (7)	0.0178 (15)
O2	0.0966 (11)	-0.1450 (11)	0.1365 (7)	0.0144 (14)
O3	0.3778 (11)	0.1033 (10)	0.0380 (7)	0.0134 (14)
O4	0.2940 (11)	-0.5350 (11)	0.0209 (7)	0.0155 (15)
O5	0.2291 (10)	-0.4405 (11)	0.2502 (7)	0.0131 (14)
O6	0.5556 (10)	-0.5510 (11)	0.2555 (7)	0.0121 (14)
O7	0.0908 (11)	-0.3710 (11)	-0.3699 (7)	0.0130 (14)
O8	0.1065 (11)	-0.1986 (11)	-0.5813 (7)	0.0125 (14)
O9	0.4335 (11)	-0.0352 (12)	-0.3515 (8)	0.0187 (16)
O10	0.2235 (12)	-0.8611 (12)	-0.2319 (8)	0.0185 (16)
H10A	0.198 (15)	-0.928 (9)	-0.179 (7)	0.028*
H10B	0.346 (4)	-0.8277 (13)	-0.221 (10)	0.028*
O11	0.2419 (13)	-0.7837 (13)	0.3943 (9)	0.0257 (18)
H11A	0.225 (3)	-0.897 (15)	0.3811 (19)	0.039*
H11B	0.144 (13)	-0.7725 (18)	0.412 (2)	0.039*

Atomic displacement parameters ( $\text{\AA}^2$ )

	$U^{11}$	$U^{22}$	$U^{33}$	$U^{12}$	$U^{13}$	$U^{23}$
Dy1	0.0094 (3)	0.0136 (3)	0.0131 (3)	0.00658 (19)	0.00455 (18)	0.00444 (19)
I1	0.0048 (3)	0.0061 (3)	0.0105 (3)	0.0031 (2)	0.0028 (2)	0.0041 (2)
I2	0.0040 (3)	0.0067 (3)	0.0111 (3)	0.0040 (2)	0.0027 (2)	0.0039 (2)
I3	0.0076 (3)	0.0109 (3)	0.0101 (3)	0.0063 (2)	0.0032 (2)	0.0026 (2)
O1	0.014 (3)	0.023 (4)	0.012 (3)	0.010 (3)	-0.004 (3)	-0.002 (3)
O2	0.011 (3)	0.014 (4)	0.022 (4)	0.006 (3)	0.009 (3)	0.007 (3)
O3	0.020 (3)	0.006 (3)	0.020 (4)	0.007 (3)	0.011 (3)	0.006 (3)
O4	0.019 (4)	0.013 (4)	0.014 (3)	0.006 (3)	0.005 (3)	0.006 (3)
O5	0.006 (3)	0.014 (4)	0.021 (4)	0.005 (3)	0.007 (3)	0.002 (3)
O6	0.001 (3)	0.016 (4)	0.018 (3)	0.002 (3)	0.003 (3)	0.007 (3)
O7	0.014 (3)	0.020 (4)	0.013 (3)	0.012 (3)	0.007 (3)	0.013 (3)
O8	0.014 (3)	0.013 (4)	0.013 (3)	0.005 (3)	0.007 (3)	0.006 (3)
O9	0.011 (3)	0.018 (4)	0.022 (4)	0.005 (3)	0.000 (3)	-0.002 (3)
O10	0.022 (4)	0.023 (4)	0.025 (4)	0.019 (3)	0.013 (3)	0.011 (3)
O11	0.022 (4)	0.022 (4)	0.034 (5)	0.007 (4)	0.012 (4)	0.005 (4)

Geometric parameters ( $\text{\AA}$ ,  $^\circ$ )

Dy1—O4	2.401 (7)	I2—O6	1.798 (6)
Dy1—O2 <sup>i</sup>	2.408 (7)	I2—O4	1.804 (7)
Dy1—O8 <sup>ii</sup>	2.412 (7)	I2—O5	1.812 (7)
Dy1—O6 <sup>iii</sup>	2.415 (6)	I3—O9	1.783 (8)
Dy1—O7	2.429 (6)	I3—O8	1.812 (7)
Dy1—O1	2.438 (8)	I3—O7	1.813 (7)
Dy1—O10	2.453 (7)	O2—Dy1 <sup>i</sup>	2.408 (7)
Dy1—O5 <sup>i</sup>	2.461 (6)	O5—Dy1 <sup>i</sup>	2.461 (6)
I1—O1	1.804 (7)	O6—Dy1 <sup>iii</sup>	2.415 (6)
I1—O2	1.809 (7)	O8—Dy1 <sup>ii</sup>	2.412 (7)
I1—O3	1.814 (7)		
O4—Dy1—O2 <sup>i</sup>	75.1 (2)	O7—Dy1—O10	126.1 (2)
O4—Dy1—O8 <sup>ii</sup>	149.7 (2)	O1—Dy1—O10	151.9 (2)
O2 <sup>i</sup> —Dy1—O8 <sup>ii</sup>	78.5 (2)	O4—Dy1—O5 <sup>i</sup>	112.2 (2)
O4—Dy1—O6 <sup>iii</sup>	90.6 (2)	O2 <sup>i</sup> —Dy1—O5 <sup>i</sup>	73.6 (2)
O2 <sup>i</sup> —Dy1—O6 <sup>iii</sup>	142.8 (2)	O8 <sup>ii</sup> —Dy1—O5 <sup>i</sup>	73.6 (2)
O8 <sup>ii</sup> —Dy1—O6 <sup>iii</sup>	101.7 (2)	O6 <sup>iii</sup> —Dy1—O5 <sup>i</sup>	142.8 (2)
O4—Dy1—O7	135.1 (3)	O7—Dy1—O5 <sup>i</sup>	72.9 (2)
O2 <sup>i</sup> —Dy1—O7	141.9 (2)	O1—Dy1—O5 <sup>i</sup>	69.4 (2)
O8 <sup>ii</sup> —Dy1—O7	75.1 (2)	O10—Dy1—O5 <sup>i</sup>	132.9 (3)
O6 <sup>iii</sup> —Dy1—O7	70.3 (2)	O1—I1—O2	96.8 (3)
O4—Dy1—O1	69.2 (2)	O1—I1—O3	97.2 (3)
O2 <sup>i</sup> —Dy1—O1	111.8 (3)	O2—I1—O3	97.7 (3)
O8 <sup>ii</sup> —Dy1—O1	136.0 (2)	O6—I2—O4	99.6 (3)
O6 <sup>iii</sup> —Dy1—O1	93.9 (3)	O6—I2—O5	97.8 (3)
O7—Dy1—O1	72.0 (2)	O4—I2—O5	95.5 (3)

O4—Dy1—O10	84.5 (3)	O9—I3—O8	99.4 (3)
O2 <sup>i</sup> —Dy1—O10	68.8 (3)	O9—I3—O7	101.4 (3)
O8 <sup>ii</sup> —Dy1—O10	72.1 (2)	O8—I3—O7	96.1 (3)
O6 <sup>iii</sup> —Dy1—O10	75.9 (3)		

Symmetry codes: (i)  $-x, -y-1, -z$ ; (ii)  $-x, -y-1, -z-1$ ; (iii)  $-x+1, -y-1, -z$ .

*Hydrogen-bond geometry (Å, °)*

<i>D—H...A</i>	<i>D—H</i>	<i>H...A</i>	<i>D...A</i>	<i>D—H...A</i>
O10—H10A...O3 <sup>iv</sup>	0.80	2.29	2.873 (10)	131
O10—H10B...O9 <sup>iv</sup>	0.80	2.33	2.753 (11)	114
O11—H11A...O8 <sup>v</sup>	0.80	2.22	2.954 (11)	153
O11—H11B...O7 <sup>i</sup>	0.80	2.26	2.946 (11)	145

Symmetry codes: (i)  $-x, -y-1, -z$ ; (iv)  $x, y-1, z$ ; (v)  $x, y-1, z+1$ .