

Acta Crystallographica Section E

Structure Reports

Online

ISSN 1600-5368

(E)-3-(Biphenyl-4-yl)-1-(3-bromophenyl)-prop-2-en-1-oneGrzegorz Dutkiewicz,^a C. S. Chidan Kumar,^b
H. S. Yathirajan,^b B. Narayana^c and Maciej Kubicki^{a*}^aDepartment of Chemistry, Adam Mickiewicz University, Grunwaldzka 6, 60-780 Poznań, Poland, ^bDepartment of Studies in Chemistry, University of Mysore, Manasagangotri, Mysore 570 006, India, and ^cDepartment of Studies in Chemistry, Mangalore University, Mangalagangotri 574 199, India
Correspondence e-mail: mkubicki@amu.edu.pl


Received 15 October 2009; accepted 21 October 2009

Key indicators: single-crystal X-ray study; $T = 295$ K; mean $\sigma(\text{C}-\text{C}) = 0.005$ Å; R factor = 0.035; wR factor = 0.085; data-to-parameter ratio = 13.3.

In the title compound, $\text{C}_{21}\text{H}_{15}\text{BrO}$, there are two planar rings connected through a conjugated double bond. As it crystallizes in a non-centrosymmetric space group it can be regarded as a good candidate for non-linear optical applications. The molecule adopts an *E* configuration and the $\text{C}-\text{C}=\text{C}-\text{C}$ torsion angle is $177.1(4)^\circ$. The overall conformation of the compound may be described by the values of dihedral angles between the approximately planar parts. The terminal rings are twisted by an angle of $51.52(9)^\circ$, while the biphenyl part is almost planar, the dihedral angle between the planes of the rings being $4.44(17)^\circ$. The unit cell has one long dimension, above 35 Å, characteristic also of a majority of related compounds. The molecules pack head-to-tail along this direction. $\text{C}-\text{H}\cdots\pi$ interactions are observed in the crystal structure.

Related literature

For applications of chalcones, see: Cho *et al.* (1996); Dinkova-Kostova *et al.*, (1998); Fichou *et al.* (1988); Liu *et al.* (2003); Nielson *et al.* (1998); Rajas *et al.* (2002); Sarojini *et al.* (2006). For related structures, see: Fischer *et al.* (2007a,b,c); Moorthi *et al.* (2007); Sarojini *et al.* (2007).

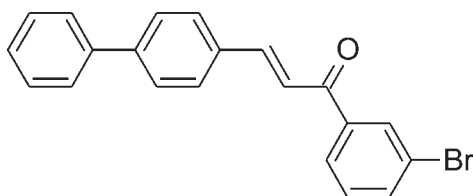

Experimental

Crystal data

| | |
|--|--|
| $\text{C}_{21}\text{H}_{15}\text{BrO}$ | $V = 1627.4(4) \text{ \AA}^3$ |
| $M_r = 363.24$ | $Z = 4$ |
| Orthorhombic, $Pca2_1$ | Mo $K\alpha$ radiation |
| $a = 6.092(1) \text{ \AA}$ | $\mu = 2.53 \text{ mm}^{-1}$ |
| $b = 7.295(1) \text{ \AA}$ | $T = 295 \text{ K}$ |
| $c = 36.619(2) \text{ \AA}$ | $0.4 \times 0.2 \times 0.2 \text{ mm}$ |

Data collection

| | |
|--|---|
| Oxford Diffraction Xcalibur Sapphire2 (large Be window) diffractometer | Diffraction, 2006) |
| Absorption correction: multi-scan (<i>CrysAlis Pro</i> ; Oxford) | $T_{\min} = 0.632$, $T_{\max} = 1.000$ |
| | 5236 measured reflections |
| | 2766 independent reflections |
| | 2209 reflections with $I > 2\sigma(I)$ |
| | $R_{\text{int}} = 0.022$ |

Refinement

| | |
|---------------------------------|--|
| $R[F^2 > 2\sigma(F^2)] = 0.035$ | H-atom parameters constrained |
| $wR(F^2) = 0.085$ | $\Delta\rho_{\max} = 0.25 \text{ e \AA}^{-3}$ |
| $S = 1.05$ | $\Delta\rho_{\min} = -0.45 \text{ e \AA}^{-3}$ |
| 2766 reflections | Absolute structure: Flack (1983), |
| 208 parameters | 1133 Friedel pairs |
| 1 restraint | Flack parameter: 0.059 (11) |

Table 1

Hydrogen-bond geometry (Å, °).

| $D-\text{H}\cdots A$ | $D-\text{H}$ | $\text{H}\cdots A$ | $D\cdots A$ | $D-\text{H}\cdots A$ |
|--|--------------|--------------------|-------------|----------------------|
| $\text{C3}-\text{H3}\cdots\text{Cg1}^{\text{i}}$ | 0.93 | 2.85 | 3.583 (5) | 137 |
| $\text{C6}-\text{H6}\cdots\text{Cg1}^{\text{ii}}$ | 0.93 | 2.78 | 3.516 (5) | 137 |
| $\text{C9}-\text{H9}\cdots\text{Cg2}^{\text{i}}$ | 0.93 | 2.87 | 3.544 (5) | 131 |
| $\text{C12}-\text{H12}\cdots\text{Cg2}^{\text{ii}}$ | 0.93 | 2.97 | 3.655 (5) | 131 |
| $\text{C21}-\text{H21}\cdots\text{Cg3}^{\text{iii}}$ | 0.93 | 2.83 | 3.505 (5) | 131 |

Symmetry codes: (i) $x + \frac{1}{2}, -y + 2, z$; (ii) $x - \frac{1}{2}, -y + 1, z$; (iii) $x - \frac{1}{2}, -y + 2, z$. Cg1 , Cg2 and Cg3 are the centroids of the $\text{C1}-\text{C6}$, $\text{C7}-\text{C12}$ and $\text{C17}-\text{C22}$ rings, respectively.

Data collection: *CrysAlis Pro* (Oxford Diffraction, 2006); cell refinement: *CrysAlis Pro*; data reduction: *CrysAlis Pro*; program(s) used to solve structure: *SIR92* (Altomare *et al.*, 1994); program(s) used to refine structure: *SHELXL97* (Sheldrick, 2008); molecular graphics: *Stereochemical Workstation Operation Manual* (Siemens, 1989); software used to prepare material for publication: *SHELXL97*.

CSC thanks the University of Mysore for research facilities.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: NK2009).

References

- Altomare, A., Casciarano, G., Giacovazzo, C., Guagliardi, A., Burla, M. C., Polidori, G. & Camalli, M. (1994). *J. Appl. Cryst.* **27**, 435.
 Cho, B. R., Je, J. T., Kim, H. S., Jean, S. J., Song, O. K. & Wang, C. H. (1996). *Bull. Korean Chem. Soc.* **17**, 693–695.
 Dinkova-Kostova, A. T., Abey-Gunawardana, C. & Talalay, P. (1998). *J. Med. Chem.* **41**, 5287–5296.
 Fichou, D., Watanabe, T., Takeda, T., Miyata, S., Goto, Y. & Nakayama, M. (1988). *Jpn. J. Appl. Phys.* **27**, 429–430.
 Fischer, A., Yathirajan, H. S., Ashalatha, B. V., Narayana, B. & Sarojini, B. K. (2007a). *Acta Cryst.* **E63**, o1349–o1350.
 Fischer, A., Yathirajan, H. S., Ashalatha, B. V., Narayana, B. & Sarojini, B. K. (2007b). *Acta Cryst.* **E63**, o1351–o1352.
 Fischer, A., Yathirajan, H. S., Ashalatha, B. V., Narayana, B. & Sarojini, B. K. (2007c). *Acta Cryst.* **E63**, o1353–o1354.

- Flack, H. D. (1983). *Acta Cryst.* **A39**, 876–881.
- Liu, M., Wilairat, P., Croft, S. L., Tan, A. L. C. & Go, M. I. (2003). *Bioorg. Med. Chem.* **11**, 2729–2738.
- Moorthi, S. S., Chinnakali, K., Nanjundan, S., Radhakrishnanan, S. & Fun, H.-K. (2007). *Acta Cryst.* **E63**, o692–o694.
- Nielson, S. F., Christensen, S. B., Cruciani, G., Kharazmi, A. & Liljefors, T. (1998). *J. Med. Chem.* **41**, 4819–4832.
- Oxford Diffraction (2006). *CrysAlis Pro*. Oxford Diffraction Ltd, Abingdon, England.
- Rajas, J., Paya, M., Domingues, J. N. & Ferrandiz, M. L. (2002). *Bioorg. Med. Chem. Lett.* **12**, 1951–1954.
- Sarojini, B. K., Narayana, B., Ashalatha, B. V., Indira, J. & Lobo, K. J. (2006). *J. Cryst. Growth*, **295**, 54–59.
- Sarojini, B. K., Yathirajan, H. S., Sreevidya, T. V., Narayana, B. & Bolte, M. (2007). *Acta Cryst.* **E63**, o2945.
- Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.
- Siemens (1989). *Stereochemical Workstation Operation Manual*. Siemens Analytical X-ray Instruments Inc., Madison, Wisconsin, USA.

supporting information

Acta Cryst. (2009). E65, o2856–o2857 [https://doi.org/10.1107/S1600536809043384]

(E)-3-(Biphenyl-4-yl)-1-(3-bromophenyl)prop-2-en-1-one**Grzegorz Dutkiewicz, C. S. Chidan Kumar, H. S. Yathirajan, B. Narayana and Maciej Kubicki****S1. Comment**

For such a structurally simple group of compounds, chalcones have displayed an impressive array of biological activities, among which antimalarial (Liu *et al.*, 2003), antiprotozoal (Nielson *et al.*, 1998), nitric oxide inhibition (Rajas *et al.*, 2002) and anticancer (Dinkova-Kostova *et al.*, 1998) activities have been cited in the literature. Also, among organic compounds reported for non-linear optical (NLO) properties, chalcone derivatives are notable materials for their excellent blue-light transmittance and good crystallizability. They provide the necessary configuration to show NLO properties, with two planar rings connected through a conjugated double bond (*e.g.*, Sarojini *et al.*, 2006). Substitution on either of the benzene rings greatly influences the non-centrosymmetric crystal packing. It is speculated that, in order to improve the activity, more bulky substituents should be introduced to increase the spontaneous polarization of non-centrosymmetric crystals (Fichou *et al.*, 1988). The molecular hyperpolarizability is strongly influenced, not only by the electronic effect, but also by the steric effect of the substituent (Cho *et al.*, 1996). Prompted by this, and in a continuation of our quest to synthesize new materials which can find use in the photonics industry, we have synthesized new chalcones and studied their SHG (second harmonic generation) efficiency.

(2E)-3-(biphenyl-4-yl)-1-(3-bromophenyl)prop-2-en-1-one (I) crystallizes in the non-centrosymmetric space group $Pca2_1$, which makes NLO activity possible. The overall conformation of the molecule can be described by the dihedral angles between the planar fragments: two rings of biphenyl system (A and B, *cf.* Fig. 1), the enone fragment (C) and the (bromo)phenyl ring (D). All these fragments are in a good approximation planar (maximum deviation from the least-squares plane is 0.018 (4) Å for the enone fragment). The biphenyl rings are almost coplanar, the dihedral angle between them is 4.44 (17)°; the enone fragment is significantly inclined with respect to both neighbouring rings, B/C angle is 30.74 (11)° and C/D - 16.34 (12)°.

The conformation for the ketone system is *s-cis*, as evidenced by the torsion angle O16—C15—C14—C13 of -21.7 (6)°. In general, the conformation of the molecule (I) is similar to the related compounds (*e.g.*, Fischer *et al.*, 2007a, b, c, Moorthi *et al.*, 2007).

The unit cell of (I) has a long *c* axis of 36.619 (2) Å, and the molecules pack head-to-tail along this direction (Fig. 2). Such a long unit-cell parameter is observed in a number of similar compounds, even though they crystallize in different space groups and even in different crystal classes. For instance, 4-bromo (Fischer *et al.*, 2007b), 4-chloro (Fischer *et al.*, 2007a) and 4-methoxyphenyl (Fischer *et al.*, 2007c) analogues crystallize all in the Cc space groups with the long parameter (*ca.* 36 Å) along *c*-direction, 4-fluoro derivative (Sarojini *et al.*, 2007) - in $P2_1$ space group ($Z' = 2$) with the long *b* direction *etc.* It might be also noted, that other unit-cell parameters in all these structures are also similar to those observed in (I), and the comparison of the packing modes shows a significant degree of isostructurality. This suggests that the same interactions are responsible for the crystal packing in these structures: these can be some relatively short and linear C—H⋯ π contacts, and van der Waals interactions.

S2. Experimental

5 ml 40% KOH solution was added to a thoroughly stirred solution of 3-bromoacetophenone (1.0 g, 5 m mol) and 4-biphenylcarboxaldehyde (1.0 g, 5.4 m mol) in 15 ml of methanol. The mixture was stirred overnight and filtered. The product formed was crystallized in methanol. X-ray quality crystals were grown from slow evaporation of ethyl acetate solution (m.p.: 378 – 380 K).

S3. Refinement

Hydrogen atoms were placed in idealized positions, and refined as riding. Their isotropic thermal parameters were set at 1.2 times U_{eq} 's of appropriate carrier atoms.

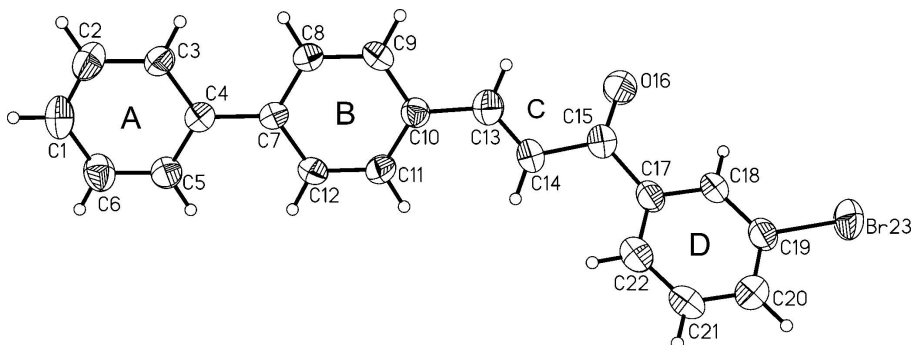


Figure 1

Anisotropic ellipsoid representation of the compound **I** together with atom labelling scheme. The ellipsoids are drawn at 50% probability level, hydrogen atoms are depicted as spheres with arbitrary radii.

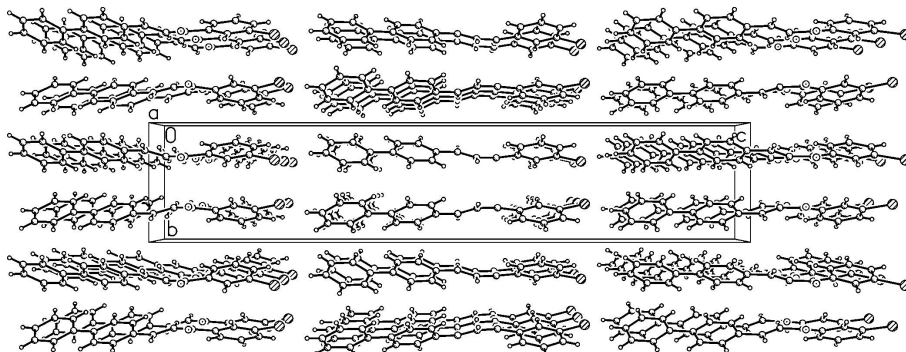


Figure 2

The crystal packing as seen along [100] direction.

(*E*)-3-(Biphenyl-4-yl)-1-(3-bromophenyl)prop-2-en-1-one

Crystal data

$C_{21}H_{15}BrO$

$M_r = 363.24$

Orthorhombic, $Pca2_1$

Hall symbol: $P\ 2c\ -2ac$

$a = 6.092\ (1)\ \text{\AA}$

$b = 7.295\ (1)\ \text{\AA}$

$c = 36.619\ (2)\ \text{\AA}$

$V = 1627.4\ (4)\ \text{\AA}^3$

$Z = 4$

$F(000) = 736$

$D_x = 1.483\ \text{Mg m}^{-3}$

Mo $K\alpha$ radiation, $\lambda = 0.71073\ \text{\AA}$

Cell parameters from 2900 reflections

$\theta = 2.2\text{--}26.8^\circ$

$\mu = 2.53\ \text{mm}^{-1}$

$T = 295\ \text{K}$

Prism, colourless

$0.4 \times 0.2 \times 0.2\ \text{mm}$

Data collection

Oxford Diffraction Xcalibur Sapphire2 (large Be window) diffractometer
 Radiation source: Enhance (Mo) X-ray Source Graphite monochromator
 Detector resolution: 8.1929 pixels mm⁻¹
 ω scans
 Absorption correction: multi-scan (CrysAlis PRO; Oxford Diffraction, 2006)

$T_{\min} = 0.632$, $T_{\max} = 1.000$
 5236 measured reflections
 2766 independent reflections
 2209 reflections with $I > 2\sigma(I)$
 $R_{\text{int}} = 0.022$
 $\theta_{\max} = 26.9^\circ$, $\theta_{\min} = 2.2^\circ$
 $h = -5 \rightarrow 7$
 $k = -5 \rightarrow 9$
 $l = -45 \rightarrow 41$

Refinement

Refinement on F^2
 Least-squares matrix: full
 $R[F^2 > 2\sigma(F^2)] = 0.035$
 $wR(F^2) = 0.085$
 $S = 1.05$
 2766 reflections
 208 parameters
 1 restraint
 Primary atom site location: structure-invariant direct methods
 Secondary atom site location: difference Fourier map

Hydrogen site location: inferred from neighbouring sites
 H-atom parameters constrained
 $w = 1/[\sigma^2(F_o^2) + (0.050P)^2]$
 where $P = (F_o^2 + 2F_c^2)/3$
 $(\Delta/\sigma)_{\max} = 0.001$
 $\Delta\rho_{\max} = 0.25 \text{ e } \text{\AA}^{-3}$
 $\Delta\rho_{\min} = -0.45 \text{ e } \text{\AA}^{-3}$
 Absolute structure: Flack (1983), 1133 Friedel pairs
 Absolute structure parameter: 0.059 (11)

Special details

Geometry. All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

Refinement. Refinement of F^2 against ALL reflections. The weighted R -factor wR and goodness of fit S are based on F^2 , conventional R -factors R are based on F , with F set to zero for negative F^2 . The threshold expression of $F^2 > \sigma(F^2)$ is used only for calculating R -factors(gt) etc. and is not relevant to the choice of reflections for refinement. R -factors based on F^2 are statistically about twice as large as those based on F , and R -factors based on ALL data will be even larger.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

| | x | y | z | $U_{\text{iso}}^*/U_{\text{eq}}$ |
|----|------------|------------|--------------|----------------------------------|
| C1 | 0.6509 (7) | 0.7425 (7) | 0.79823 (11) | 0.0516 (11) |
| H1 | 0.5927 | 0.7379 | 0.7748 | 0.062* |
| C2 | 0.8449 (7) | 0.8289 (5) | 0.80447 (11) | 0.0532 (10) |
| H2 | 0.9194 | 0.8847 | 0.7853 | 0.064* |
| C3 | 0.9320 (7) | 0.8337 (5) | 0.83967 (9) | 0.0430 (9) |
| H3 | 1.0645 | 0.8938 | 0.8437 | 0.052* |
| C4 | 0.8253 (6) | 0.7506 (5) | 0.86911 (10) | 0.0333 (7) |
| C5 | 0.6238 (6) | 0.6661 (4) | 0.86149 (11) | 0.0407 (9) |
| H5 | 0.5454 | 0.6120 | 0.8804 | 0.049* |
| C6 | 0.5403 (7) | 0.6612 (5) | 0.82712 (12) | 0.0504 (10) |
| H6 | 0.4072 | 0.6026 | 0.8229 | 0.061* |
| C7 | 0.9218 (6) | 0.7517 (5) | 0.90615 (9) | 0.0302 (7) |
| C8 | 1.1289 (5) | 0.8263 (5) | 0.91272 (10) | 0.0376 (8) |
| H8 | 1.2081 | 0.8759 | 0.8934 | 0.045* |

| | | | | |
|------|-------------|-------------|---------------|--------------|
| C9 | 1.2194 (6) | 0.8281 (5) | 0.94747 (11) | 0.0390 (8) |
| H9 | 1.3586 | 0.8776 | 0.9508 | 0.047* |
| C10 | 1.1075 (6) | 0.7580 (5) | 0.97729 (10) | 0.0364 (8) |
| C11 | 0.9024 (6) | 0.6836 (5) | 0.97075 (10) | 0.0424 (9) |
| H11 | 0.8234 | 0.6346 | 0.9902 | 0.051* |
| C12 | 0.8120 (6) | 0.6801 (5) | 0.93638 (11) | 0.0398 (8) |
| H12 | 0.6738 | 0.6284 | 0.9332 | 0.048* |
| C13 | 1.2154 (6) | 0.7575 (6) | 1.01312 (11) | 0.0449 (9) |
| H13 | 1.3613 | 0.7952 | 1.0136 | 0.054* |
| C14 | 1.1287 (7) | 0.7096 (6) | 1.04483 (11) | 0.0494 (10) |
| H14 | 0.9815 | 0.6761 | 1.0461 | 0.059* |
| C15 | 1.2648 (7) | 0.7089 (5) | 1.07855 (11) | 0.0476 (9) |
| O16 | 1.4619 (5) | 0.6988 (4) | 1.07694 (8) | 0.0696 (9) |
| C17 | 1.1481 (6) | 0.7302 (5) | 1.11410 (10) | 0.0412 (8) |
| C18 | 1.2662 (6) | 0.6895 (4) | 1.14615 (10) | 0.0380 (8) |
| H18 | 1.4069 | 0.6405 | 1.1447 | 0.046* |
| C19 | 1.1730 (6) | 0.7225 (5) | 1.17930 (11) | 0.0435 (8) |
| C20 | 0.9649 (8) | 0.7894 (5) | 1.18260 (12) | 0.0515 (10) |
| H20 | 0.9028 | 0.8092 | 1.2055 | 0.062* |
| C21 | 0.8486 (6) | 0.8273 (5) | 1.15093 (14) | 0.0487 (11) |
| H21 | 0.7074 | 0.8751 | 1.1526 | 0.058* |
| C22 | 0.9371 (7) | 0.7956 (5) | 1.11731 (11) | 0.0477 (9) |
| H22 | 0.8545 | 0.8183 | 1.0964 | 0.057* |
| Br23 | 1.33920 (7) | 0.67882 (6) | 1.222156 (16) | 0.06635 (16) |

Atomic displacement parameters (Å²)

| | U^{11} | U^{22} | U^{33} | U^{12} | U^{13} | U^{23} |
|-----|-------------|-------------|-------------|--------------|--------------|--------------|
| C1 | 0.071 (3) | 0.044 (2) | 0.040 (2) | 0.008 (2) | -0.014 (2) | -0.0040 (19) |
| C2 | 0.071 (3) | 0.054 (2) | 0.035 (2) | -0.006 (2) | 0.0032 (17) | 0.0005 (16) |
| C3 | 0.042 (2) | 0.054 (2) | 0.0327 (18) | -0.0073 (18) | 0.0040 (14) | -0.0016 (15) |
| C4 | 0.038 (2) | 0.0254 (16) | 0.0363 (17) | 0.0042 (15) | 0.0029 (14) | -0.0008 (13) |
| C5 | 0.044 (2) | 0.0343 (19) | 0.044 (2) | -0.0048 (15) | -0.0018 (15) | 0.0043 (15) |
| C6 | 0.057 (3) | 0.045 (2) | 0.049 (2) | -0.0094 (18) | -0.0123 (19) | 0.0004 (18) |
| C7 | 0.0334 (19) | 0.0240 (15) | 0.0332 (16) | 0.0007 (14) | 0.0039 (13) | 0.0004 (12) |
| C8 | 0.036 (2) | 0.040 (2) | 0.0362 (18) | -0.0046 (15) | 0.0024 (13) | 0.0039 (14) |
| C9 | 0.0300 (19) | 0.041 (2) | 0.046 (2) | -0.0043 (15) | -0.0044 (15) | -0.0022 (15) |
| C10 | 0.037 (2) | 0.0369 (18) | 0.0354 (18) | -0.0008 (15) | -0.0013 (13) | -0.0026 (15) |
| C11 | 0.043 (2) | 0.048 (2) | 0.036 (2) | -0.0089 (17) | 0.0034 (15) | 0.0064 (16) |
| C12 | 0.031 (2) | 0.048 (2) | 0.0408 (18) | -0.0061 (17) | -0.0008 (13) | -0.0014 (15) |
| C13 | 0.050 (2) | 0.042 (2) | 0.043 (2) | 0.0038 (18) | -0.0044 (18) | -0.0012 (17) |
| C14 | 0.043 (2) | 0.066 (3) | 0.038 (2) | -0.0047 (19) | -0.0095 (16) | -0.0006 (18) |
| C15 | 0.046 (2) | 0.056 (2) | 0.040 (2) | -0.0019 (19) | -0.0052 (17) | -0.0007 (17) |
| O16 | 0.0414 (18) | 0.118 (3) | 0.0490 (17) | 0.0122 (17) | -0.0012 (13) | -0.0013 (16) |
| C17 | 0.037 (2) | 0.046 (2) | 0.0412 (19) | -0.0037 (17) | -0.0081 (14) | -0.0013 (16) |
| C18 | 0.0331 (19) | 0.0402 (19) | 0.0406 (19) | -0.0016 (15) | -0.0073 (14) | -0.0010 (15) |
| C19 | 0.041 (2) | 0.048 (2) | 0.042 (2) | -0.0057 (18) | -0.0078 (15) | -0.0001 (16) |
| C20 | 0.051 (3) | 0.058 (2) | 0.045 (2) | -0.001 (2) | 0.0027 (17) | -0.0004 (18) |

| | | | | | | |
|------|------------|------------|--------------|--------------|--------------|-------------|
| C21 | 0.035 (2) | 0.051 (2) | 0.060 (3) | -0.0022 (18) | -0.0076 (17) | 0.000 (2) |
| C22 | 0.044 (2) | 0.047 (2) | 0.052 (2) | -0.0032 (18) | -0.0090 (18) | 0.0020 (16) |
| Br23 | 0.0653 (3) | 0.0941 (3) | 0.03960 (19) | 0.0043 (2) | -0.0142 (2) | 0.0021 (3) |

Geometric parameters (Å, °)

| | | | |
|-----------|-----------|--------------|-----------|
| C1—C2 | 1.358 (6) | C11—C12 | 1.374 (5) |
| C1—C6 | 1.387 (6) | C11—H11 | 0.9300 |
| C1—H1 | 0.9300 | C12—H12 | 0.9300 |
| C2—C3 | 1.394 (5) | C13—C14 | 1.323 (6) |
| C2—H2 | 0.9300 | C13—H13 | 0.9300 |
| C3—C4 | 1.397 (5) | C14—C15 | 1.487 (5) |
| C3—H3 | 0.9300 | C14—H14 | 0.9300 |
| C4—C5 | 1.401 (5) | C15—O16 | 1.204 (5) |
| C4—C7 | 1.478 (5) | C15—C17 | 1.492 (6) |
| C5—C6 | 1.358 (5) | C17—C22 | 1.376 (6) |
| C5—H5 | 0.9300 | C17—C18 | 1.408 (5) |
| C6—H6 | 0.9300 | C18—C19 | 1.361 (5) |
| C7—C12 | 1.395 (5) | C18—H18 | 0.9300 |
| C7—C8 | 1.395 (5) | C19—C20 | 1.364 (6) |
| C8—C9 | 1.387 (5) | C19—Br23 | 1.894 (4) |
| C8—H8 | 0.9300 | C20—C21 | 1.387 (6) |
| C9—C10 | 1.385 (5) | C20—H20 | 0.9300 |
| C9—H9 | 0.9300 | C21—C22 | 1.364 (6) |
| C10—C11 | 1.383 (5) | C21—H21 | 0.9300 |
| C10—C13 | 1.468 (5) | C22—H22 | 0.9300 |
| C2—C1—C6 | 119.5 (4) | C10—C11—H11 | 119.1 |
| C2—C1—H1 | 120.3 | C11—C12—C7 | 121.9 (3) |
| C6—C1—H1 | 120.2 | C11—C12—H12 | 119.1 |
| C1—C2—C3 | 119.9 (4) | C7—C12—H12 | 119.1 |
| C1—C2—H2 | 120.0 | C14—C13—C10 | 127.3 (4) |
| C3—C2—H2 | 120.1 | C14—C13—H13 | 116.3 |
| C2—C3—C4 | 121.7 (4) | C10—C13—H13 | 116.3 |
| C2—C3—H3 | 119.2 | C13—C14—C15 | 120.4 (4) |
| C4—C3—H3 | 119.2 | C13—C14—H14 | 119.8 |
| C3—C4—C5 | 116.4 (3) | C15—C14—H14 | 119.8 |
| C3—C4—C7 | 121.4 (3) | O16—C15—C14 | 121.0 (4) |
| C5—C4—C7 | 122.2 (3) | O16—C15—C17 | 121.6 (3) |
| C6—C5—C4 | 121.6 (4) | C14—C15—C17 | 117.3 (4) |
| C6—C5—H5 | 119.2 | C22—C17—C18 | 118.6 (4) |
| C4—C5—H5 | 119.2 | C22—C17—C15 | 123.8 (3) |
| C5—C6—C1 | 120.9 (4) | C18—C17—C15 | 117.5 (3) |
| C5—C6—H6 | 119.5 | C19—C18—C17 | 119.5 (4) |
| C1—C6—H6 | 119.5 | C19—C18—H18 | 120.2 |
| C12—C7—C8 | 116.3 (3) | C17—C18—H18 | 120.2 |
| C12—C7—C4 | 122.4 (3) | C18—C19—C20 | 122.0 (4) |
| C8—C7—C4 | 121.3 (3) | C18—C19—Br23 | 119.1 (3) |

| | | | |
|-----------------|------------|------------------|------------|
| C9—C8—C7 | 121.4 (3) | C20—C19—Br23 | 118.9 (3) |
| C9—C8—H8 | 119.3 | C19—C20—C21 | 118.2 (4) |
| C7—C8—H8 | 119.3 | C19—C20—H20 | 120.9 |
| C10—C9—C8 | 121.6 (3) | C21—C20—H20 | 120.9 |
| C10—C9—H9 | 119.2 | C22—C21—C20 | 121.2 (4) |
| C8—C9—H9 | 119.2 | C22—C21—H21 | 119.4 |
| C11—C10—C9 | 116.9 (3) | C20—C21—H21 | 119.4 |
| C11—C10—C13 | 124.0 (3) | C21—C22—C17 | 120.4 (4) |
| C9—C10—C13 | 119.0 (3) | C21—C22—H22 | 119.8 |
| C12—C11—C10 | 121.9 (3) | C17—C22—H22 | 119.8 |
| C12—C11—H11 | 119.1 | | |
| | | | |
| C6—C1—C2—C3 | 0.6 (6) | C4—C7—C12—C11 | -179.3 (3) |
| C1—C2—C3—C4 | 0.3 (6) | C11—C10—C13—C14 | -9.0 (7) |
| C2—C3—C4—C5 | -1.4 (5) | C9—C10—C13—C14 | 174.4 (4) |
| C2—C3—C4—C7 | 178.2 (4) | C10—C13—C14—C15 | 177.1 (4) |
| C3—C4—C5—C6 | 1.7 (5) | C13—C14—C15—O16 | -21.7 (6) |
| C7—C4—C5—C6 | -178.0 (3) | C13—C14—C15—C17 | 155.4 (4) |
| C4—C5—C6—C1 | -0.9 (6) | O16—C15—C17—C22 | 160.0 (4) |
| C2—C1—C6—C5 | -0.3 (6) | C14—C15—C17—C22 | -17.1 (5) |
| C3—C4—C7—C12 | 175.8 (3) | O16—C15—C17—C18 | -16.7 (6) |
| C5—C4—C7—C12 | -4.6 (5) | C14—C15—C17—C18 | 166.3 (3) |
| C3—C4—C7—C8 | -3.8 (5) | C22—C17—C18—C19 | -2.6 (5) |
| C5—C4—C7—C8 | 175.8 (3) | C15—C17—C18—C19 | 174.2 (3) |
| C12—C7—C8—C9 | 0.1 (5) | C17—C18—C19—C20 | 1.9 (6) |
| C4—C7—C8—C9 | 179.7 (3) | C17—C18—C19—Br23 | -176.8 (3) |
| C7—C8—C9—C10 | -0.7 (5) | C18—C19—C20—C21 | -1.1 (6) |
| C8—C9—C10—C11 | 0.9 (5) | Br23—C19—C20—C21 | 177.6 (3) |
| C8—C9—C10—C13 | 177.7 (4) | C19—C20—C21—C22 | 1.2 (6) |
| C9—C10—C11—C12 | -0.5 (5) | C20—C21—C22—C17 | -2.0 (6) |
| C13—C10—C11—C12 | -177.1 (4) | C18—C17—C22—C21 | 2.7 (6) |
| C10—C11—C12—C7 | -0.2 (6) | C15—C17—C22—C21 | -173.9 (3) |
| C8—C7—C12—C11 | 0.3 (5) | | |

Hydrogen-bond geometry (Å, °)

| <i>D</i> —H... <i>A</i> | <i>D</i> —H | H... <i>A</i> | <i>D</i> ... <i>A</i> | <i>D</i> —H... <i>A</i> |
|------------------------------|-------------|---------------|-----------------------|-------------------------|
| C3—H3...Cg1 ⁱ | 0.93 | 2.85 | 3.583 (5) | 137 |
| C6—H6...Cg1 ⁱⁱ | 0.93 | 2.78 | 3.516 (5) | 137 |
| C9—H9...Cg2 ⁱ | 0.93 | 2.87 | 3.544 (5) | 131 |
| C12—H12...Cg2 ⁱⁱ | 0.93 | 2.97 | 3.655 (5) | 131 |
| C21—H21...Cg3 ⁱⁱⁱ | 0.93 | 2.83 | 3.505 (5) | 131 |

Symmetry codes: (i) $x+1/2, -y+2, z$; (ii) $x-1/2, -y+1, z$; (iii) $x-1/2, -y+2, z$.