

Poly[1,4-bis(4-pyridylmethyl)piperazine-dium [[tetraaquacobaltate(II)]- μ -pyromellitato- $\kappa^2 O^1:O^4$] dihydrate]

 Laura K. Sposato^a and Robert L. LaDuca^{b*}

^aDepartment of Chemistry and Physics, King's College, Wilkes-Barre, PA 18711, USA, and ^bLyman Briggs College, Department of Chemistry, Michigan State University, East Lansing, MI 48825, USA
Correspondence e-mail: laduca@msu.edu


Received 22 November 2009; accepted 26 November 2009

Key indicators: single-crystal X-ray study; $T = 173$ K; mean $\sigma(\text{C}-\text{C}) = 0.004$ Å; R factor = 0.050; wR factor = 0.153; data-to-parameter ratio = 12.9.

In the title compound, $\{(\text{C}_{16}\text{H}_{22}\text{N}_4)[\text{Co}(\text{C}_{10}\text{H}_2\text{O}_8)(\text{H}_2\text{O})_4] \cdot 2\text{H}_2\text{O}\}_n$, the octahedrally coordinated Co^{II} atom is situated on an inversion center and possesses four aqua ligands. The Co atoms are linked into an anionic coordination polymer chain by bis-monodentate pyromellitate ligands. The chain motifs are connected into a supramolecular layer by hydrogen bonding mediated by uncoordinated water molecules. Charge balance is provided by doubly protonated bis(4-pyridylmethyl)piperazine units, which are anchored to the coordination polymer chain motifs by $\text{N}-\text{H} \cdots \text{O}$ hydrogen bonding.

Related literature

For some divalent cobalt pyromellitate coordination polymers containing dipyridyl ligands, see: Majumder *et al.* (2006). For the preparation of bis(4-pyridylmethyl)piperazine, see: Pocić *et al.* (2005).

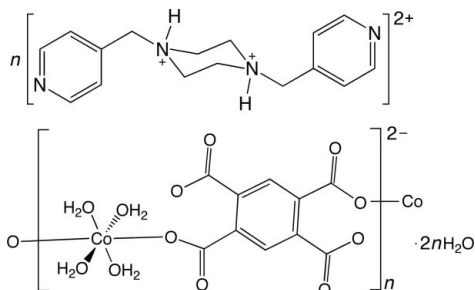

Experimental

Crystal data

 $(\text{C}_{16}\text{H}_{22}\text{N}_4)[\text{Co}(\text{C}_{10}\text{H}_2\text{O}_8)(\text{H}_2\text{O})_4] \cdot 2\text{H}_2\text{O}$
 $M_r = 687.52$
Triclinic, $P\bar{1}$
 $a = 7.278$ (2) Å
 $b = 9.752$ (3) Å
 $c = 11.257$ (3) Å
 $\alpha = 66.733$ (3)°
 $\beta = 75.168$ (3)°
 $\gamma = 83.359$ (3)°

 $V = 709.5$ (3) Å³
 $Z = 1$
Mo $K\alpha$ radiation
 $\mu = 0.69$ mm⁻¹
 $T = 173$ K
 $0.24 \times 0.14 \times 0.10$ mm

Data collection

 Bruker APEXII CCD diffractometer
Absorption correction: multi-scan (SADABS; Sheldrick, 1996)
 $T_{\text{min}} = 0.853$, $T_{\text{max}} = 0.933$

 11370 measured reflections
2908 independent reflections
2511 reflections with $I > 2\sigma(I)$
 $R_{\text{int}} = 0.058$

Refinement

 $R[F^2 > 2\sigma(F^2)] = 0.050$
 $wR(F^2) = 0.153$
 $S = 1.05$
2908 reflections
226 parameters
10 restraints

 H atoms treated by a mixture of independent and constrained refinement
 $\Delta\rho_{\text{max}} = 1.23$ e Å⁻³
 $\Delta\rho_{\text{min}} = -0.91$ e Å⁻³
Table 1

Hydrogen-bond geometry (Å, °).

$D-\text{H} \cdots A$	$D-\text{H}$	$\text{H} \cdots A$	$D \cdots A$	$D-\text{H} \cdots A$
$\text{O1W}-\text{H1WA} \cdots \text{O6}^{\text{i}}$	0.88 (2)	2.38 (3)	2.997 (3)	128 (3)
$\text{O1W}-\text{H1WB} \cdots \text{O1}^{\text{i}}$	0.89 (2)	1.88 (2)	2.764 (3)	174 (3)
$\text{O5}-\text{H5A} \cdots \text{N1}$	0.88 (2)	1.87 (2)	2.739 (3)	177 (3)
$\text{O5}-\text{H5B} \cdots \text{O4}$	0.85 (2)	1.87 (2)	2.697 (3)	163 (3)
$\text{O6}-\text{H6C} \cdots \text{O1W}$	0.86 (2)	1.92 (2)	2.753 (3)	165 (3)
$\text{O6}-\text{H6D} \cdots \text{O2}^{\text{ii}}$	0.86 (2)	1.81 (2)	2.624 (3)	158 (3)
$\text{N2}-\text{H2N} \cdots \text{O3}^{\text{iii}}$	0.91 (2)	1.73 (2)	2.630 (3)	171 (3)

Symmetry codes: (i) $-x + 1, -y, -z + 1$; (ii) $-x + 2, -y, -z + 1$; (iii) $-x + 1, -y - 1, -z + 2$.

Data collection: APEX2 (Bruker, 2007); cell refinement: SAINT (Bruker, 2007); data reduction: SAINT; program(s) used to solve structure: SHELXS97 (Sheldrick, 2008); program(s) used to refine structure: SHELXL97 (Sheldrick, 2008); molecular graphics: CrystalMaker (Palmer, 2007); software used to prepare material for publication: SHELXL97.

We gratefully acknowledge the donors of the American Chemical Society Petroleum Research Fund for funding this work.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: HY2258).

References

- Bruker (2007). APEX2 and SAINT. Bruker AXS Inc., Madison, Wisconsin, USA.
Majumder, A., Gramlich, V., Rosair, G. M., Batten, S. R., Masuda, J. D., El Fallah, M. S., Ribas, J., Sutter, J.-P., Desplanches, C. & Mitra, S. (2006). *Cryst. Growth Des.* **6**, 2355–2368.
Palmer, D. (2007). *CrystalMaker*. CrystalMaker Software, Bicester, England.
Pocić, D., Planeix, J.-M., Kyritsakas, N., Jouaiti, A., Abdelaziz, H. & Wais, M. (2005). *CrystEngComm*, **7**, 624–628.
Sheldrick, G. M. (1996). *SADABS*. University of Göttingen, Germany.
Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.

supporting information

Acta Cryst. (2009). E65, m1709 [doi:10.1107/S1600536809051101]

Poly[1,4-bis(4-pyridylmethyl)piperazinediium [[tetraaquacobaltate(II)]- μ -pyromellitato- $\kappa^2 O^1:O^4$] dihydrate]

Laura K. Sposato and Robert L. LaDuca

S1. Comment

The diverse possible binding modes of the pyromellitate ligand (1,2,4,5-benzenetetracarboxylate) has allowed formation of a wide variety of cobalt-containing coordination polymers, especially in the presence of dipyridyl neutral co-ligands (Majumder *et al.*, 2006). This chemistry was further developed by the synthesis of the title compound, which incorporates the long-spanning hydrogen-bonding capable dipyridyl ligand bis(4-pyridylmethyl)piperazine (bpmp).

The asymmetric unit of the title compound consists of a divalent Co^{II} atom on a crystallographic inversion center, one-half of a pyromellitate tetraanion situated across another crystallographic inversion center, one-half of a $(\text{H}_2\text{bpmp})^{2+}$ dication (protonated at each of the two piperazinyl N atoms) sited across another crystallographic inversion center, and one water molecule of crystallization. The local coordination and surrounding supramolecular environment is illustrated in Fig. 1.

Adjacent Co^{II} ions are linked into $[\text{Co}(\text{H}_2\text{O})_4(\text{pyromellitate})]_n^{2n-}$ anionic one-dimensional coordination polymer motifs, *via* symmetrically related monodentate carboxylate termini of the pyromellitate ligands. These chain motifs are oriented parallel to the $[1 \bar{1} 0]$ direction; the $\text{Co}\cdots\text{Co}$ distance along the chain is 11.474 (3) Å. Two of the pyromellitate carboxylate groups do not ligate to Co^{II} ions. Neighboring chain motifs aggregate into supramolecular layers coincident with the *ab* planes (Fig. 2), established by hydrogen-bonding patterns between the co-crystallized water molecules, aqua ligands, and ligated pyromellitate carboxylate O atoms (Table 1). In turn, the supramolecular layers stack in an *AAA* pattern along the *c* axis, with charge-balancing $(\text{H}_2\text{bpmp})^{2+}$ dications situated in the interlamellar regions (Fig. 3), thus forming the three-dimensional crystal structure of the title compound. The closest $\text{Co}\cdots\text{Co}$ contact distance between neighboring layers is 11.257 (3) Å, which defines the *c* lattice parameter.

S2. Experimental

All starting materials were obtained commercially, except for bpmp, which was prepared by a published procedure (Pocic *et al.*, 2005). A mixture of cobalt nitrate hexahydrate (108 mg, 0.37 mmol), pyromellitic acid (94 mg, 0.37 mmol), bpmp (99 mg, 0.37 mmol) and 10.0 g water (550 mmol) was placed into a 23 ml Teflon-lined Parr Acid Digestion bomb, which was then heated under autogenous pressure at 393 K for 48 h. After cooling to 293 K, orange blocks of the title compound were obtained along with a white powder.

S3. Refinement

All H atoms bound to C atoms were placed in calculated positions and refined in riding mode, with $\text{C}-\text{H} = 0.95$ and 0.99 Å, and with $U_{\text{iso}}(\text{H}) = 1.2U_{\text{eq}}(\text{C})$. The H atoms bound to the water molecule O atoms and to the piperazinyl N atoms were found in a difference Fourier map and refined with restraints of $\text{O}-\text{H} = 0.89$ (1) and $\text{N}-\text{H} = 0.92$ (1) Å and with $U_{\text{iso}}(\text{H}) = 1.2U_{\text{eq}}(\text{O,N})$. The maximum and minimum residual electron density peaks of 1.234 and $-0.908 \text{ e } \text{Å}^{-3}$ were located 0.98

and 0.68 Å from the Co1 and O1W atoms, respectively.

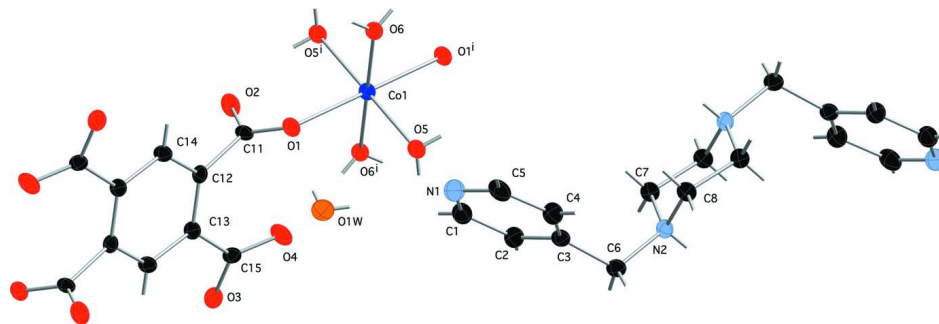


Figure 1

The coordination environment of the title compound, showing 50% probability ellipsoids. H atom positions are shown as grey sticks. [Color codes: dark blue Co; light blue N; red O; black C; orange O in uncoordinated water molecule.

Symmetry code: (i) $-x+2, -y, -z+1.$]

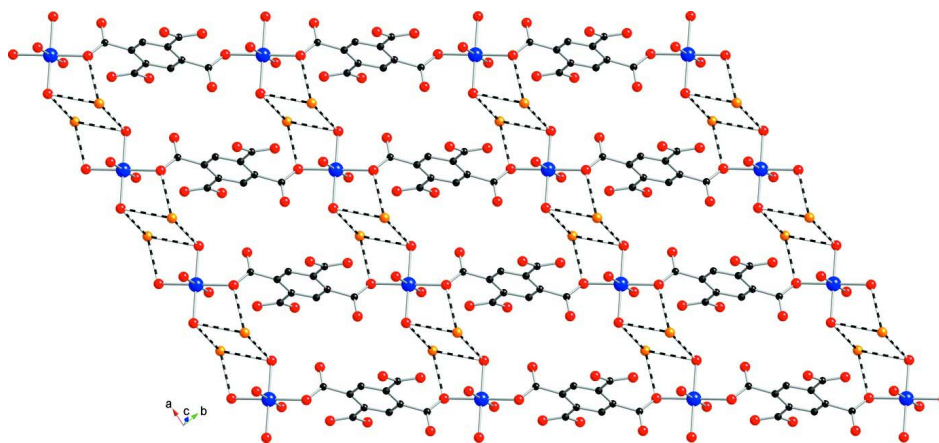


Figure 2

A view of the supramolecular layer in the title compound. Hydrogen bonding contacts are indicated as dashed bars.

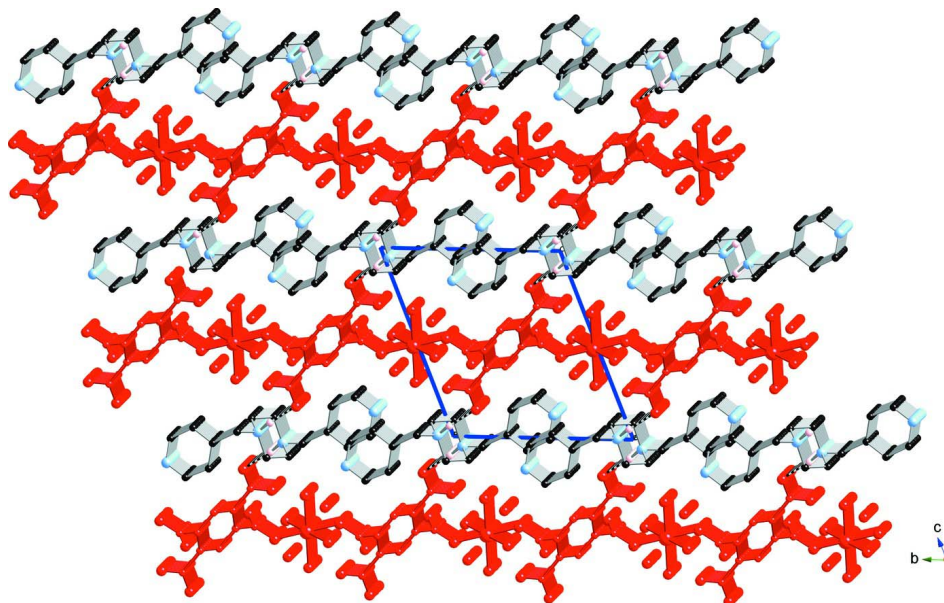


Figure 3

Stacking diagram for the title compound, viewed down the *a* axis. Hydrogen bonding contacts are indicated as dashed bars.

Poly[1,4-bis(4-pyridylmethyl)piperazinediium [[tetraaquacobaltate(II)]- μ -pyromellitato- κ^2 O¹:O⁴] dihydrate]

Crystal data

(C₁₆H₂₂N₄)[Co(C₁₀H₂O₈)(H₂O)₄] \cdot 2H₂O

M_r = 687.52

Triclinic, *P* $\bar{1}$

Hall symbol: -P 1

a = 7.278 (2) Å

b = 9.752 (3) Å

c = 11.257 (3) Å

α = 66.733 (3)°

β = 75.168 (3)°

γ = 83.359 (3)°

V = 709.5 (3) Å³

Z = 1

F(000) = 359

D_x = 1.609 Mg m⁻³

Mo *K* α radiation, λ = 0.71073 Å

Cell parameters from 11370 reflections

θ = 2.0–26.5°

μ = 0.69 mm⁻¹

T = 173 K

Block, pink

0.24 \times 0.14 \times 0.10 mm

Data collection

Bruker APEXII CCD

diffractometer

Radiation source: fine-focus sealed tube

Graphite monochromator

φ and ω scans

Absorption correction: multi-scan

(*SADABS*; Sheldrick, 1996)

T_{min} = 0.853, *T_{max}* = 0.933

11370 measured reflections

2908 independent reflections

2511 reflections with *I* > 2 σ (*I*)

R_{int} = 0.058

θ_{\max} = 26.5°, θ_{\min} = 2.0°

h = -9 \rightarrow 9

k = -12 \rightarrow 12

l = -14 \rightarrow 14

Refinement

Refinement on F^2

Least-squares matrix: full

$R[F^2 > 2\sigma(F^2)] = 0.050$

$wR(F^2) = 0.153$

$S = 1.05$

2908 reflections

226 parameters

10 restraints

Primary atom site location: structure-invariant
direct methods

Secondary atom site location: difference Fourier
map

Hydrogen site location: inferred from
neighbouring sites

H atoms treated by a mixture of independent
and constrained refinement

$w = 1/[\sigma^2(F_o^2) + (0.1134P)^2]$

where $P = (F_o^2 + 2F_c^2)/3$

$(\Delta/\sigma)_{\max} < 0.001$

$\Delta\rho_{\max} = 1.23 \text{ e } \text{\AA}^{-3}$

$\Delta\rho_{\min} = -0.91 \text{ e } \text{\AA}^{-3}$

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	<i>x</i>	<i>y</i>	<i>z</i>	$U_{\text{iso}}^*/U_{\text{eq}}$
Co1	1.0000	0.0000	0.5000	0.0155 (2)
O1	0.8311 (2)	0.19744 (19)	0.45730 (18)	0.0192 (4)
O1W	0.4690 (3)	-0.1576 (2)	0.6340 (2)	0.0255 (4)
H1WA	0.437 (4)	-0.070 (3)	0.639 (3)	0.031*
H1WB	0.375 (4)	-0.178 (4)	0.607 (3)	0.031*
O2	0.9191 (3)	0.2866 (2)	0.58976 (19)	0.0235 (4)
O3	0.3143 (3)	0.2159 (2)	0.82962 (18)	0.0236 (4)
O4	0.5304 (3)	0.1042 (2)	0.7189 (2)	0.0332 (5)
O5	0.8431 (3)	-0.0690 (2)	0.69373 (18)	0.0183 (4)
H5A	0.829 (4)	-0.163 (2)	0.748 (3)	0.022*
H5B	0.742 (3)	-0.024 (3)	0.718 (3)	0.022*
O6	0.8063 (3)	-0.0969 (2)	0.44473 (18)	0.0193 (4)
H6C	0.705 (3)	-0.132 (3)	0.504 (3)	0.023*
H6D	0.876 (4)	-0.166 (3)	0.425 (3)	0.023*
N1	0.7991 (3)	-0.3648 (3)	0.8552 (2)	0.0284 (6)
N2	0.8089 (3)	-0.9425 (2)	1.0284 (2)	0.0170 (5)
H2N	0.755 (4)	-1.033 (2)	1.080 (3)	0.020*
C1	0.7611 (4)	-0.4408 (3)	0.9870 (3)	0.0258 (6)
H1	0.7635	-0.3891	1.0426	0.031*
C2	0.7185 (4)	-0.5911 (3)	1.0460 (3)	0.0224 (6)
H2	0.6933	-0.6409	1.1399	0.027*
C3	0.7131 (4)	-0.6683 (3)	0.9661 (3)	0.0187 (5)
C4	0.7549 (4)	-0.5898 (3)	0.8292 (3)	0.0242 (6)
H4	0.7544	-0.6384	0.7709	0.029*
C5	0.7970 (4)	-0.4404 (3)	0.7793 (3)	0.0275 (6)
H5	0.8261	-0.3883	0.6856	0.033*
C6	0.6512 (4)	-0.8286 (3)	1.0280 (3)	0.0204 (6)
H6A	0.5805	-0.8497	1.1210	0.024*
H6B	0.5619	-0.8407	0.9798	0.024*
C7	0.9515 (4)	-0.9366 (3)	1.1004 (3)	0.0192 (5)
H7A	0.8864	-0.9431	1.1912	0.023*
H7B	1.0192	-0.8407	1.0532	0.023*
C8	0.9075 (4)	-0.9347 (3)	0.8919 (3)	0.0196 (5)

H8A	0.9749	-0.8389	0.8415	0.024*
H8B	0.8124	-0.9387	0.8443	0.024*
C11	0.8099 (3)	0.2813 (3)	0.5227 (2)	0.0170 (5)
C12	0.6437 (3)	0.3901 (3)	0.5118 (2)	0.0161 (5)
C13	0.4741 (4)	0.3639 (3)	0.6092 (2)	0.0172 (5)
C14	0.6677 (4)	0.5255 (3)	0.4034 (3)	0.0178 (5)
H14	0.7827	0.5429	0.3367	0.021*
C15	0.4396 (3)	0.2173 (3)	0.7278 (3)	0.0176 (5)

Atomic displacement parameters (Å²)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Co1	0.0153 (3)	0.0153 (3)	0.0161 (3)	0.00250 (18)	-0.0074 (2)	-0.0044 (2)
O1	0.0192 (9)	0.0174 (9)	0.0221 (9)	0.0051 (7)	-0.0094 (8)	-0.0073 (8)
O1W	0.0222 (10)	0.0262 (11)	0.0285 (10)	0.0026 (8)	-0.0124 (9)	-0.0074 (9)
O2	0.0238 (10)	0.0250 (10)	0.0270 (10)	0.0084 (8)	-0.0149 (8)	-0.0123 (8)
O3	0.0281 (10)	0.0165 (9)	0.0198 (10)	-0.0002 (8)	-0.0011 (8)	-0.0031 (8)
O4	0.0277 (11)	0.0174 (10)	0.0351 (12)	0.0074 (8)	0.0045 (9)	0.0008 (9)
O5	0.0186 (9)	0.0162 (9)	0.0184 (9)	0.0007 (7)	-0.0045 (8)	-0.0049 (7)
O6	0.0165 (9)	0.0201 (10)	0.0232 (10)	0.0033 (7)	-0.0082 (8)	-0.0090 (8)
N1	0.0265 (13)	0.0193 (12)	0.0329 (14)	0.0013 (9)	-0.0061 (11)	-0.0042 (10)
N2	0.0187 (11)	0.0141 (10)	0.0169 (10)	0.0003 (8)	-0.0062 (9)	-0.0033 (8)
C1	0.0251 (14)	0.0242 (14)	0.0303 (15)	0.0026 (11)	-0.0081 (12)	-0.0125 (12)
C2	0.0236 (14)	0.0207 (14)	0.0211 (13)	0.0019 (11)	-0.0074 (11)	-0.0052 (11)
C3	0.0156 (12)	0.0184 (13)	0.0207 (13)	0.0023 (9)	-0.0067 (10)	-0.0051 (10)
C4	0.0260 (14)	0.0226 (14)	0.0211 (13)	0.0030 (11)	-0.0072 (11)	-0.0049 (11)
C5	0.0297 (15)	0.0211 (14)	0.0216 (14)	0.0035 (11)	-0.0048 (12)	0.0004 (11)
C6	0.0181 (13)	0.0189 (13)	0.0212 (13)	0.0013 (10)	-0.0060 (11)	-0.0040 (10)
C7	0.0216 (13)	0.0195 (13)	0.0175 (12)	0.0017 (10)	-0.0089 (10)	-0.0060 (10)
C8	0.0204 (13)	0.0207 (13)	0.0176 (12)	0.0027 (10)	-0.0080 (10)	-0.0058 (10)
C11	0.0149 (12)	0.0135 (12)	0.0155 (12)	0.0013 (9)	-0.0016 (10)	0.0002 (9)
C12	0.0167 (12)	0.0132 (12)	0.0172 (12)	0.0022 (9)	-0.0070 (10)	-0.0034 (10)
C13	0.0178 (12)	0.0137 (12)	0.0177 (12)	0.0020 (9)	-0.0063 (10)	-0.0026 (10)
C14	0.0163 (12)	0.0160 (12)	0.0179 (12)	0.0013 (9)	-0.0052 (10)	-0.0027 (10)
C15	0.0142 (12)	0.0165 (12)	0.0196 (13)	0.0008 (9)	-0.0063 (10)	-0.0032 (10)

Geometric parameters (Å, °)

Co1—O5	2.0631 (18)	C2—H2	0.9500
Co1—O1	2.1150 (17)	C3—C4	1.392 (4)
Co1—O6	2.1184 (18)	C3—C6	1.507 (4)
O1—C11	1.274 (3)	C4—C5	1.379 (4)
O1W—H1WA	0.881 (18)	C4—H4	0.9500
O1W—H1WB	0.885 (17)	C5—H5	0.9500
O2—C11	1.246 (3)	C6—H6A	0.9900
O3—C15	1.266 (3)	C6—H6B	0.9900
O4—C15	1.244 (3)	C7—C8 ⁱ	1.517 (4)
O5—H5A	0.875 (17)	C7—H7A	0.9900

O5—H5B	0.852 (17)	C7—H7B	0.9900
O6—H6C	0.857 (17)	C8—C7 ⁱ	1.517 (4)
O6—H6D	0.863 (17)	C8—H8A	0.9900
N1—C5	1.334 (4)	C8—H8B	0.9900
N1—C1	1.340 (4)	C11—C12	1.510 (3)
N2—C7	1.490 (3)	C12—C14	1.391 (3)
N2—C8	1.495 (3)	C12—C13	1.397 (3)
N2—C6	1.502 (3)	C13—C14 ⁱⁱ	1.395 (3)
N2—H2N	0.906 (18)	C13—C15	1.514 (3)
C1—C2	1.384 (4)	C14—C13 ⁱⁱ	1.394 (3)
C1—H1	0.9500	C14—H14	0.9500
C2—C3	1.393 (4)		
O5—Co1—O5 ⁱⁱⁱ	180.0	C5—C4—C3	119.0 (3)
O5—Co1—O1	88.13 (7)	C5—C4—H4	120.5
O5 ⁱⁱⁱ —Co1—O1	91.87 (7)	C3—C4—H4	120.5
O5—Co1—O1 ⁱⁱⁱ	91.87 (7)	N1—C5—C4	123.7 (3)
O5 ⁱⁱⁱ —Co1—O1 ⁱⁱⁱ	88.13 (7)	N1—C5—H5	118.2
O1—Co1—O1 ⁱⁱⁱ	180.000 (1)	C4—C5—H5	118.2
O5—Co1—O6	91.72 (7)	N2—C6—C3	115.3 (2)
O5 ⁱⁱⁱ —Co1—O6	88.28 (7)	N2—C6—H6A	108.4
O1—Co1—O6	88.61 (7)	C3—C6—H6A	108.4
O1 ⁱⁱⁱ —Co1—O6	91.39 (7)	N2—C6—H6B	108.4
O5—Co1—O6 ⁱⁱⁱ	88.28 (7)	C3—C6—H6B	108.4
O5 ⁱⁱⁱ —Co1—O6 ⁱⁱⁱ	91.72 (7)	H6A—C6—H6B	107.5
O1—Co1—O6 ⁱⁱⁱ	91.39 (7)	N2—C7—C8 ⁱ	109.5 (2)
O1 ⁱⁱⁱ —Co1—O6 ⁱⁱⁱ	88.61 (7)	N2—C7—H7A	109.8
O6—Co1—O6 ⁱⁱⁱ	180.000 (1)	C8 ⁱ —C7—H7A	109.8
C11—O1—Co1	122.61 (16)	N2—C7—H7B	109.8
H1WA—O1W—H1WB	104 (3)	C8 ⁱ —C7—H7B	109.8
Co1—O5—H5A	123.9 (19)	H7A—C7—H7B	108.2
Co1—O5—H5B	123 (2)	N2—C8—C7 ⁱ	110.4 (2)
H5A—O5—H5B	105 (2)	N2—C8—H8A	109.6
Co1—O6—H6C	116 (2)	C7 ⁱ —C8—H8A	109.6
Co1—O6—H6D	102 (2)	N2—C8—H8B	109.6
H6C—O6—H6D	112 (3)	C7 ⁱ —C8—H8B	109.6
C5—N1—C1	117.3 (2)	H8A—C8—H8B	108.1
C7—N2—C8	109.8 (2)	O2—C11—O1	125.8 (2)
C7—N2—C6	113.4 (2)	O2—C11—C12	117.0 (2)
C8—N2—C6	112.9 (2)	O1—C11—C12	117.1 (2)
C7—N2—H2N	102 (2)	C14—C12—C13	119.4 (2)
C8—N2—H2N	111.8 (19)	C14—C12—C11	117.6 (2)
C6—N2—H2N	106.2 (19)	C13—C12—C11	122.9 (2)
N1—C1—C2	123.1 (3)	C14 ⁱⁱ —C13—C12	119.4 (2)
N1—C1—H1	118.5	C14 ⁱⁱ —C13—C15	119.1 (2)
C2—C1—H1	118.5	C12—C13—C15	121.4 (2)
C1—C2—C3	119.2 (3)	C12—C14—C13 ⁱⁱ	121.1 (2)
C1—C2—H2	120.4	C12—C14—H14	119.4

C3—C2—H2	120.4	C13 ⁱⁱ —C14—H14	119.4
C4—C3—C2	117.7 (2)	O4—C15—O3	123.5 (2)
C4—C3—C6	121.9 (2)	O4—C15—C13	118.8 (2)
C2—C3—C6	120.3 (2)	O3—C15—C13	117.7 (2)
O5—Co1—O1—C11	54.13 (19)	C7—N2—C8—C7 ⁱ	59.2 (3)
O5 ⁱⁱⁱ —Co1—O1—C11	-125.86 (19)	C6—N2—C8—C7 ⁱ	-173.3 (2)
O6—Co1—O1—C11	145.90 (19)	Co1—O1—C11—O2	21.7 (3)
O6 ⁱⁱⁱ —Co1—O1—C11	-34.10 (19)	Co1—O1—C11—C12	-161.93 (16)
C5—N1—C1—C2	-0.8 (4)	O2—C11—C12—C14	93.1 (3)
N1—C1—C2—C3	-0.4 (4)	O1—C11—C12—C14	-83.6 (3)
C1—C2—C3—C4	1.2 (4)	O2—C11—C12—C13	-82.8 (3)
C1—C2—C3—C6	-174.9 (2)	O1—C11—C12—C13	100.5 (3)
C2—C3—C4—C5	-0.8 (4)	C14—C12—C13—C14 ⁱⁱ	-0.5 (4)
C6—C3—C4—C5	175.2 (2)	C11—C12—C13—C14 ⁱⁱ	175.3 (2)
C1—N1—C5—C4	1.2 (4)	C14—C12—C13—C15	178.9 (2)
C3—C4—C5—N1	-0.4 (4)	C11—C12—C13—C15	-5.3 (4)
C7—N2—C6—C3	59.1 (3)	C13—C12—C14—C13 ⁱⁱ	0.5 (4)
C8—N2—C6—C3	-66.5 (3)	C11—C12—C14—C13 ⁱⁱ	-175.6 (2)
C4—C3—C6—N2	81.0 (3)	C14 ⁱⁱ —C13—C15—O4	156.2 (3)
C2—C3—C6—N2	-103.2 (3)	C12—C13—C15—O4	-23.2 (4)
C8—N2—C7—C8 ⁱ	-58.7 (3)	C14 ⁱⁱ —C13—C15—O3	-21.5 (4)
C6—N2—C7—C8 ⁱ	174.0 (2)	C12—C13—C15—O3	159.2 (2)

Symmetry codes: (i) $-x+2, -y-2, -z+2$; (ii) $-x+1, -y+1, -z+1$; (iii) $-x+2, -y, -z+1$.

Hydrogen-bond geometry ($\text{\AA}, ^\circ$)

<i>D</i> —H \cdots <i>A</i>	<i>D</i> —H	H \cdots <i>A</i>	<i>D</i> \cdots <i>A</i>	<i>D</i> —H \cdots <i>A</i>
O1 <i>W</i> —H1 <i>WA</i> \cdots O6 ^{iv}	0.88 (2)	2.38 (3)	2.997 (3)	128 (3)
O1 <i>W</i> —H1 <i>WB</i> \cdots O1 ^{iv}	0.89 (2)	1.88 (2)	2.764 (3)	174 (3)
O5—H5 <i>A</i> \cdots N1	0.88 (2)	1.87 (2)	2.739 (3)	177 (3)
O5—H5 <i>B</i> \cdots O4	0.85 (2)	1.87 (2)	2.697 (3)	163 (3)
O6—H6 <i>C</i> \cdots O1 <i>W</i>	0.86 (2)	1.92 (2)	2.753 (3)	165 (3)
O6—H6 <i>D</i> \cdots O2 ⁱⁱⁱ	0.86 (2)	1.81 (2)	2.624 (3)	158 (3)
N2—H2 <i>N</i> \cdots O3 ^v	0.91 (2)	1.73 (2)	2.630 (3)	171 (3)

Symmetry codes: (iii) $-x+2, -y, -z+1$; (iv) $-x+1, -y, -z+1$; (v) $-x+1, -y-1, -z+2$.