

Poly[bis[μ -1,3-bis(imidazol-1-ylmethyl)-benzene- $\kappa^2N^3:N^3'$]bis(nitrato- κO)-cadmium]

Xi-Ying Hu,* Guang-Rui Yang and Wen-Wen Shan

Institute of Environmental and Municipal Engineering, North China University of Water Conservancy and Electric Power, Zhengzhou 450011, People's Republic of China

Correspondence e-mail: hbsyhy@163.com

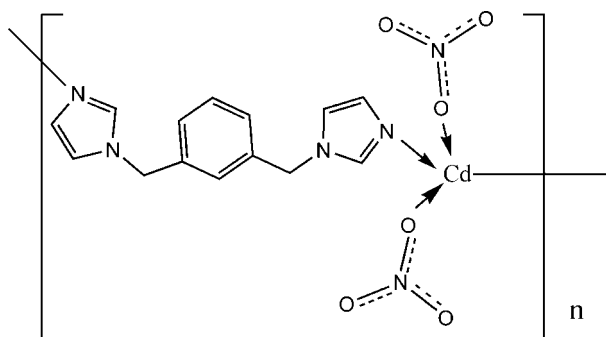
Received 10 May 2011; accepted 31 May 2011

 Key indicators: single-crystal X-ray study; $T = 296$ K; mean $\sigma(C-C) = 0.006$ Å; R factor = 0.044; wR factor = 0.123; data-to-parameter ratio = 13.0.

A novel metal-organic framework based on 1,3-bis(imidazol-1-ylmethyl)benzene (1,3-bimb), $[Cd(NO_3)_2(C_{14}H_{14}N_4)_2]_n$, has been synthesized hydrothermally. The structure exhibits a two-dimensional metal-organic (4,4)-net composed of Cd^{II} atoms and bimb ligands, and such layers are further joined through interlayer $C-H \cdots O$ hydrogen bonds to generate a three-dimensional supramolecular structure.

Related literature

For background to the network topologies and applications of coordination polymers, see: Maspoeh *et al.* (2007); Ockwig *et al.* (2005); Zang *et al.* (2006); Zhang *et al.* (2009). For synthesis and related structures with the bimb ligand, see: Hoskins *et al.* (1997). For $C-H \cdots O$ hydrogen bonds, see: Desiraju (1996); Broder *et al.* (2002).



Experimental

Crystal data

$[Cd(NO_3)_2(C_{14}H_{14}N_4)_2]$
 $M_r = 713.00$
 Monoclinic, $P2_1/c$

$a = 8.4542$ (8) Å
 $b = 19.3910$ (18) Å
 $c = 9.2222$ (8) Å

$\beta = 102.415$ (10)°
 $V = 1476.5$ (2) Å³
 $Z = 2$
 Mo $K\alpha$ radiation

$\mu = 0.80$ mm⁻¹
 $T = 296$ K
 $0.21 \times 0.20 \times 0.19$ mm

Data collection

Bruker SMART APEXII CCD
 area-detector diffractometer
 Absorption correction: multi-scan
 (SADABS; Bruker, 2005)
 $T_{min} = 0.850$, $T_{max} = 0.863$

5606 measured reflections
 2578 independent reflections
 2253 reflections with $I > 2\sigma(I)$
 $R_{int} = 0.017$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.044$
 $wR(F^2) = 0.123$
 $S = 1.06$
 2578 reflections
 199 parameters

1 restraint
 H-atom parameters constrained
 $\Delta\rho_{max} = 1.95$ e Å⁻³
 $\Delta\rho_{min} = -0.86$ e Å⁻³

Table 1

Hydrogen-bond geometry (Å, °).

$D-H \cdots A$	$D-H$	$H \cdots A$	$D \cdots A$	$D-H \cdots A$
$C3-H3 \cdots O2^i$	0.93	2.71	3.525 (8)	147
$C4-H4B \cdots O1^i$	0.97	2.67	3.525 (6)	148
$C4-H4B \cdots O2^i$	0.97	2.83	3.633 (9)	141
$C10-H10 \cdots O2^i$	0.93	2.63	3.506 (9)	158
$C11-H11A \cdots O1^{ii}$	0.97	2.70	3.518 (7)	142
$C12-H12 \cdots O1^{ii}$	0.93	2.37	3.210 (6)	151

 Symmetry codes: (i) $x - 1, y, z$; (ii) $-x + 1, y + \frac{1}{2}, -z + \frac{1}{2}$.

Data collection: APEX2 (Bruker, 2005); cell refinement: SAINT (Bruker, 2005); data reduction: SAINT; program(s) used to solve structure: SHELXS97 (Sheldrick, 2008); program(s) used to refine structure: SHELXL97 (Sheldrick, 2008); molecular graphics: DIAMOND (Brandenburg, 2010); software used to prepare material for publication: SHELXTL (Sheldrick, 2008).

This work was supported financially by the Natural Science Foundation of Henan Province (grant No. 2010A140009) and the International Technology Cooperation Project of the Science and Technology Department of Henan Province of China (grant No. 104300510044).

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: HP2007).

References

- Brandenburg, K. (2010). DIAMOND. Crystal Impact GbR, Bonn, Germany.
- Broder, C. K., Davidson, M. G., Trevor Forsyth, V., Howard, J. A. K., Lamb, S. & Mason, S. A. (2002). *Cryst. Growth Des.* **2**, 163–169.
- Bruker (2005). APEX2, SAINT and SADABS. Bruker AXS Inc., Madison, Wisconsin, USA.
- Desiraju, G. R. (1996). *Acc. Chem. Res.* **29**, 441–449.
- Hoskins, B. F., Robson, R. & Slizys, D. A. (1997). *J. Am. Chem. Soc.* **119**, 2952–2953.
- Maspoeh, D., Ruiz-Molina, D. & Veciana, J. (2007). *Chem. Soc. Rev.* **36**, 770–818.
- Ockwig, N. W., Delgado-Friedrichs, O., O'Keeffe, M. & Yaghi, O. M. (2005). *Acc. Chem. Res.* **38**, 176–182.
- Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.
- Zang, S.-Q., Su, Y., Li, Y.-Z., Ni, Z.-P. & Meng, Q.-J. (2006). *Inorg. Chem.* **45**, 174–180.
- Zhang, Y.-B., Zhang, W.-X., Feng, F.-Y., Zhang, J.-P. & Chen, X.-M. (2009). *Angew. Chem. Int. Ed.* **48**, 5287–5290.

supporting information

Acta Cryst. (2011). E67, m899 [doi:10.1107/S1600536811021027]

Poly[bis[μ -1,3-bis(imidazol-1-ylmethyl)benzene- $\kappa^2N^3:N^{3'}$]bis(nitrato- κO)cadmium]

Xi-Ying Hu, Guang-Rui Yang and Wen-Wen Shan

S1. Comment

Extensive research has been focused on the supramolecular coordination assemblies not only for their variety of architectures but also for the potential applications as functional materials (Maspoth *et al.*, 2007; Ockwig *et al.*, 2005). Many imidazole-containing ligands have been successfully employed in the generation of many interesting systems in possession of multidimensional networks and properties (Zang *et al.*, 2006; Zhang *et al.*, 2009). To further explore various factors that influence the formation of result structures in the assembly reactions, we undertake synthetic and structural studies on one novel Cd^{II} coordination polymers based on the highly flexible bidentate ligand 1,3-bis-(imidazol-1-ylmethyl)-benzene (1,3-bimb): [Cd(bimb)₂(NO₃)₂]_n (**1**).

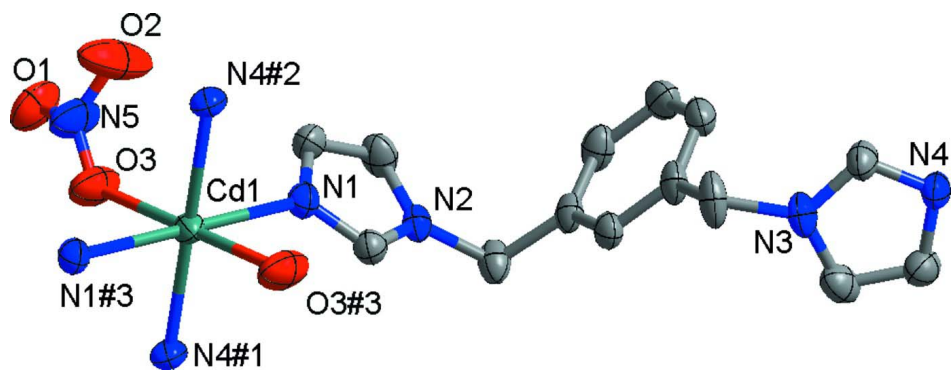
X-ray crystallographic analysis revealed that **1** crystallizes in monoclinic space group $P2_1/c$. As depicted in Fig. 1, the asymmetric unit consists of a half Cd^{II} atom, one bimb ligand and one nitrate ion. Each Cd ion is in a slightly elongated octahedral coordination environment and coordinated by four N atoms from different bimb ligands and two O atoms from two nitrate ions. Four N atoms comprise the equatorial plane, while two O atoms occupy the axial positions. Each bimb ligand acts as a μ_2 -bridge in *trans*-conformation with the dihedral angle of the two imidazole rings being *ca* 68.40 (16)°. Adjacent metal atoms are bridged by bimb ligands from two directions which are almost mutually perpendicular to form a (4,4)-net with the Cd...Cd distances of *ca* 14.2654 (10) Å (Fig. 2). The coordinated nitrate ions hang from the layer. Neighboring layers are arranged parallel with the uncoordinated O atoms closed to some H atoms from adjacent layer, and a number of interlayer C—H...O hydrogen bonds can be detected which contribute to the formation of the three-dimensional supromolecular structure, as shown in Fig. 3. The hydrogen-bonding geometry is listed in Table 1.

S2. Experimental

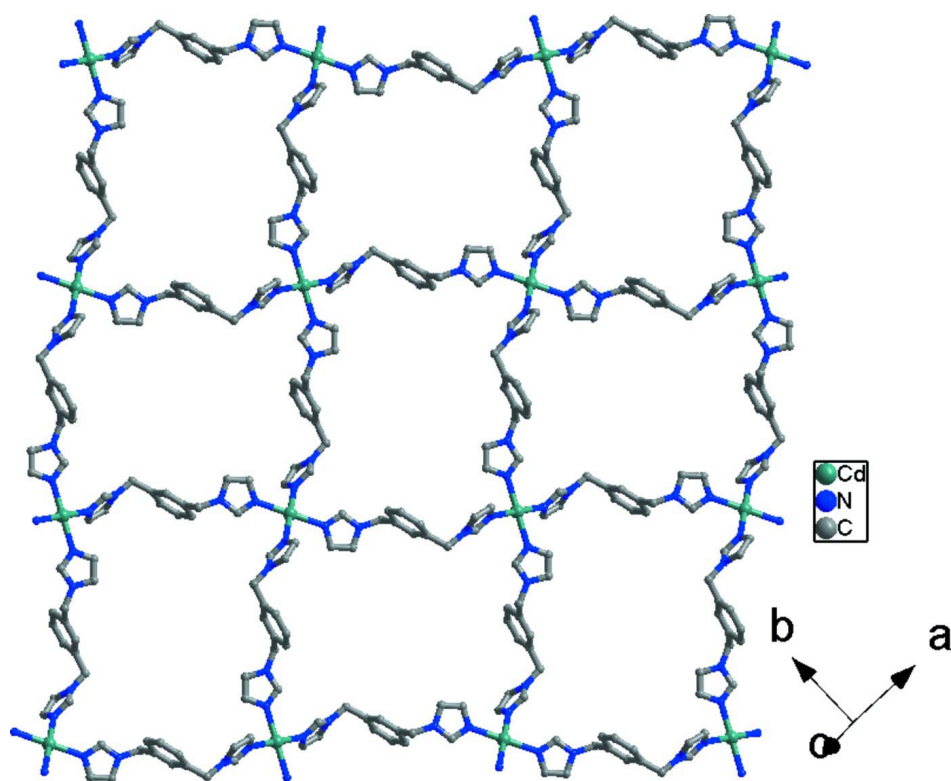
1,3-bis(imidazol-1-ylmethyl)-benzene (bimb) was prepared according to the literature (Hoskins *et al.*, 1997), all other starting materials were of analytical grade and obtained from commercial sources without further purification. Compound **1** was synthesized hydrothermally in a Teflon-lined stainless steel container by heating a mixture of 1,3-bis(imidazol-1-ylmethyl)-benzene (bimb) (0.0119 g, 0.05 mmol), Cd(NO₃)₂·4H₂O (0.0154 g, 0.05 mmol) and KOH (0.0056 g, 0.1 mmol) in 7 ml of distilled water at 120°C for 3 d, and then cooled to room temperature. Colorless rectangular crystals of **1** were obtained in 79% yield based on Cd.

S3. Refinement

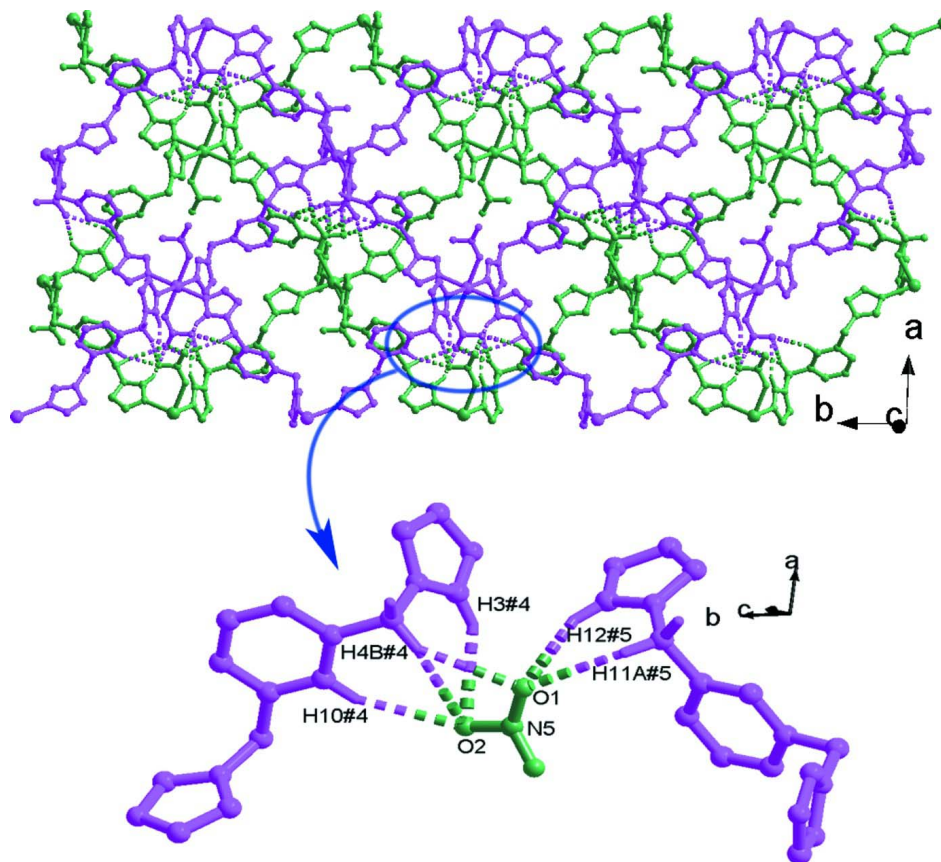
H atoms were positioned geometrically and refined using a riding model, with C—H = 0.93 Å, $U_{iso}(H) = 1.2U_{eq}(C)$ for aromatic H, and C—H = 0.97 Å, $U_{iso}(H) = 1.2U_{eq}(C)$ for CH₂.

**Figure 1**

Metal coordination and atom labeling in title compound (thermal ellipsoids at 50% probability level). All H atoms are omitted for clarity.

**Figure 2**

A view of the layer structure in compound **1**. Cd atoms are drawn as polyhedra.


Figure 3

The three-dimensional supramolecular structure connected by interlayer C—H···O hydrogen bonds. Dotted lines represent C—H···O bonds. Symmetry codes: #4 $x + 1, y, z$; #5 $-x + 1, y - 1/2, -z + 1/2$.

Poly[bis(μ -1,3-bis(imidazol-1-ylmethyl)benzene- $\kappa^2N^3:N^3'$)]bis(nitrato- κO)cadmium]
Crystal data

[Cd(NO₃)₂(C₁₄H₁₄N₄)₂]

$M_r = 713.00$

Monoclinic, $P2_1/c$

Hall symbol: -P 2ybc

$a = 8.4542(8) \text{ \AA}$

$b = 19.3910(18) \text{ \AA}$

$c = 9.2222(8) \text{ \AA}$

$\beta = 102.415(10)^\circ$

$V = 1476.5(2) \text{ \AA}^3$

$Z = 2$

$F(000) = 724$

$D_x = 1.604 \text{ Mg m}^{-3}$

Mo $K\alpha$ radiation, $\lambda = 0.71073 \text{ \AA}$

Cell parameters from 3957 reflections

$\theta = 3.1\text{--}29.1^\circ$

$\mu = 0.80 \text{ mm}^{-1}$

$T = 296 \text{ K}$

Needle, colourless

$0.21 \times 0.20 \times 0.19 \text{ mm}$

Data collection

Bruker SMART APEXII CCD area-detector diffractometer

Radiation source: fine-focus sealed tube

Graphite monochromator

ω scans

Absorption correction: multi-scan (*SADABS*; Bruker, 2005)

$T_{\min} = 0.850, T_{\max} = 0.863$

5606 measured reflections

2578 independent reflections

2253 reflections with $I > 2\sigma(I)$

$R_{\text{int}} = 0.017$
 $\theta_{\text{max}} = 25.0^\circ$, $\theta_{\text{min}} = 3.1^\circ$
 $h = -10 \rightarrow 6$

$k = -21 \rightarrow 23$
 $l = -10 \rightarrow 10$

Refinement

Refinement on F^2
 Least-squares matrix: full
 $R[F^2 > 2\sigma(F^2)] = 0.044$
 $wR(F^2) = 0.123$
 $S = 1.06$
 2578 reflections
 199 parameters
 1 restraint
 Primary atom site location: structure-invariant
 direct methods

Secondary atom site location: difference Fourier
 map
 Hydrogen site location: inferred from
 neighbouring sites
 H-atom parameters constrained
 $w = 1/[\sigma^2(F_o^2) + (0.0689P)^2 + 2.589P]$
 where $P = (F_o^2 + 2F_c^2)/3$
 $(\Delta/\sigma)_{\text{max}} < 0.001$
 $\Delta\rho_{\text{max}} = 1.95 \text{ e } \text{\AA}^{-3}$
 $\Delta\rho_{\text{min}} = -0.86 \text{ e } \text{\AA}^{-3}$

Special details

Geometry. All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

Refinement. Refinement of F^2 against ALL reflections. The weighted R -factor wR and goodness of fit S are based on F^2 , conventional R -factors R are based on F , with F set to zero for negative F^2 . The threshold expression of $F^2 > \sigma(F^2)$ is used only for calculating R -factors(gt) *etc.* and is not relevant to the choice of reflections for refinement. R -factors based on F^2 are statistically about twice as large as those based on F , and R -factors based on ALL data will be even larger.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	<i>x</i>	<i>y</i>	<i>z</i>	$U_{\text{iso}}^*/U_{\text{eq}}$
Cd1	0.5000	0.5000	0.0000	0.03330 (18)
O1	0.9948 (4)	0.4485 (2)	0.2556 (4)	0.0657 (10)
O2	0.8878 (9)	0.5415 (3)	0.1617 (11)	0.183 (4)
O3	0.7504 (4)	0.45152 (19)	0.1259 (4)	0.0626 (7)
N1	0.4529 (4)	0.55084 (17)	0.2160 (4)	0.0364 (7)
N2	0.3328 (4)	0.57252 (16)	0.4000 (3)	0.0322 (7)
N3	-0.2702 (4)	0.81383 (18)	0.3469 (4)	0.0401 (8)
N4	-0.4073 (4)	0.89430 (17)	0.4339 (4)	0.0379 (8)
N5	0.8818 (5)	0.4775 (3)	0.1699 (6)	0.0626 (7)
C1	0.5664 (5)	0.5731 (2)	0.3353 (5)	0.0419 (10)
H1	0.6763	0.5781	0.3374	0.050*
C2	0.4946 (5)	0.5868 (2)	0.4507 (5)	0.0463 (11)
H2	0.5446	0.6026	0.5446	0.056*
C3	0.3138 (5)	0.5521 (2)	0.2602 (4)	0.0342 (8)
H3	0.2145	0.5400	0.2002	0.041*
C4	0.2053 (6)	0.5788 (2)	0.4856 (5)	0.0414 (10)
H4A	0.2443	0.5598	0.5841	0.050*
H4B	0.1116	0.5521	0.4373	0.050*
C5	0.1556 (5)	0.6528 (2)	0.4988 (4)	0.0335 (8)
C6	0.2395 (5)	0.6941 (2)	0.6119 (5)	0.0436 (10)
H6	0.3224	0.6753	0.6839	0.052*
C7	0.2009 (5)	0.7630 (2)	0.6186 (5)	0.0469 (11)

H7	0.2587	0.7904	0.6947	0.056*
C8	0.0777 (6)	0.7914 (2)	0.5137 (5)	0.0440 (10)
H8	0.0538	0.8381	0.5178	0.053*
C9	-0.0113 (5)	0.7503 (2)	0.4012 (4)	0.0379 (9)
C10	0.0285 (5)	0.6813 (2)	0.3951 (4)	0.0348 (8)
H10	-0.0307	0.6535	0.3206	0.042*
C11	-0.1437 (6)	0.7816 (3)	0.2829 (5)	0.0509 (12)
H11A	-0.0969	0.8160	0.2283	0.061*
H11B	-0.1919	0.7459	0.2136	0.061*
C12	-0.2881 (5)	0.8817 (2)	0.3668 (5)	0.0410 (10)
H12	-0.2241	0.9155	0.3368	0.049*
C13	-0.4682 (5)	0.8310 (2)	0.4589 (5)	0.0430 (10)
H13	-0.5539	0.8236	0.5056	0.052*
C14	-0.3855 (5)	0.7810 (2)	0.4059 (5)	0.0469 (11)
H14	-0.4031	0.7337	0.4088	0.056*

Atomic displacement parameters (Å²)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Cd1	0.0367 (3)	0.0294 (3)	0.0390 (3)	-0.00351 (15)	0.01983 (19)	-0.00143 (16)
O1	0.0330 (16)	0.089 (3)	0.072 (2)	0.0071 (17)	0.0045 (16)	0.018 (2)
O2	0.124 (5)	0.077 (2)	0.302 (10)	-0.021 (4)	-0.058 (6)	0.044 (5)
O3	0.0348 (12)	0.0655 (16)	0.082 (2)	-0.0069 (12)	0.0001 (13)	0.0074 (15)
N1	0.0393 (18)	0.0353 (17)	0.0387 (18)	0.0008 (15)	0.0175 (15)	-0.0031 (15)
N2	0.0369 (17)	0.0287 (16)	0.0330 (17)	0.0082 (14)	0.0121 (14)	0.0015 (13)
N3	0.0437 (19)	0.0371 (18)	0.0404 (19)	0.0151 (16)	0.0112 (16)	-0.0011 (15)
N4	0.0347 (17)	0.0343 (18)	0.049 (2)	0.0069 (14)	0.0172 (15)	-0.0008 (15)
N5	0.0348 (12)	0.0655 (16)	0.082 (2)	-0.0069 (12)	0.0001 (13)	0.0074 (15)
C1	0.031 (2)	0.040 (2)	0.056 (3)	0.0006 (18)	0.0114 (19)	-0.007 (2)
C2	0.045 (3)	0.051 (3)	0.039 (2)	0.005 (2)	0.0020 (19)	-0.013 (2)
C3	0.035 (2)	0.032 (2)	0.037 (2)	0.0019 (16)	0.0102 (16)	0.0000 (16)
C4	0.054 (3)	0.037 (2)	0.040 (2)	0.0109 (19)	0.025 (2)	0.0086 (18)
C5	0.037 (2)	0.037 (2)	0.032 (2)	0.0080 (17)	0.0188 (16)	0.0031 (16)
C6	0.039 (2)	0.060 (3)	0.033 (2)	0.011 (2)	0.0090 (18)	-0.0037 (19)
C7	0.043 (2)	0.050 (3)	0.049 (3)	-0.003 (2)	0.013 (2)	-0.018 (2)
C8	0.049 (3)	0.033 (2)	0.056 (3)	0.0035 (19)	0.025 (2)	-0.0064 (19)
C9	0.042 (2)	0.041 (2)	0.035 (2)	0.0125 (18)	0.0183 (18)	-0.0013 (18)
C10	0.038 (2)	0.035 (2)	0.035 (2)	0.0029 (17)	0.0160 (17)	-0.0055 (17)
C11	0.062 (3)	0.055 (3)	0.039 (2)	0.031 (2)	0.018 (2)	-0.001 (2)
C12	0.042 (2)	0.033 (2)	0.054 (3)	0.0082 (18)	0.022 (2)	0.0057 (19)
C13	0.036 (2)	0.041 (2)	0.054 (3)	0.0010 (18)	0.0125 (19)	0.004 (2)
C14	0.047 (2)	0.033 (2)	0.057 (3)	0.0044 (19)	0.004 (2)	0.001 (2)

Geometric parameters (Å, °)

Cd1—N4 ⁱ	2.322 (3)	C2—H2	0.9300
Cd1—N4 ⁱⁱ	2.322 (3)	C3—H3	0.9300
Cd1—N1 ⁱⁱⁱ	2.332 (3)	C4—C5	1.508 (5)

Cd1—N1	2.332 (3)	C4—H4A	0.9700
Cd1—O3	2.378 (3)	C4—H4B	0.9700
Cd1—O3 ⁱⁱⁱ	2.378 (3)	C5—C6	1.384 (6)
O1—N5	1.236 (6)	C5—C10	1.389 (6)
O2—N5	1.247 (8)	C6—C7	1.379 (6)
O3—N5	1.207 (5)	C6—H6	0.9300
N1—C3	1.326 (5)	C7—C8	1.376 (7)
N1—C1	1.365 (5)	C7—H7	0.9300
N2—C3	1.326 (5)	C8—C9	1.394 (6)
N2—C2	1.375 (5)	C8—H8	0.9300
N2—C4	1.472 (5)	C9—C10	1.384 (6)
N3—C12	1.341 (5)	C9—C11	1.512 (6)
N3—C14	1.371 (6)	C10—H10	0.9300
N3—C11	1.468 (5)	C11—H11A	0.9700
N4—C12	1.314 (5)	C11—H11B	0.9700
N4—C13	1.369 (6)	C12—H12	0.9300
N4—Cd1 ^{iv}	2.322 (3)	C13—C14	1.347 (6)
C1—C2	1.360 (6)	C13—H13	0.9300
C1—H1	0.9300	C14—H14	0.9300
N4 ⁱ —Cd1—N4 ⁱⁱ	180.0	N2—C4—C5	111.8 (3)
N4 ⁱ —Cd1—N1 ⁱⁱⁱ	91.13 (12)	N2—C4—H4A	109.3
N4 ⁱⁱ —Cd1—N1 ⁱⁱⁱ	88.87 (12)	C5—C4—H4A	109.3
N4 ⁱ —Cd1—N1	88.87 (12)	N2—C4—H4B	109.3
N4 ⁱⁱ —Cd1—N1	91.13 (12)	C5—C4—H4B	109.3
N1 ⁱⁱⁱ —Cd1—N1	180.00 (15)	H4A—C4—H4B	107.9
N4 ⁱ —Cd1—O3	99.31 (12)	C6—C5—C10	118.9 (4)
N4 ⁱⁱ —Cd1—O3	80.69 (12)	C6—C5—C4	120.4 (4)
N1 ⁱⁱⁱ —Cd1—O3	87.27 (13)	C10—C5—C4	120.7 (4)
N1—Cd1—O3	92.73 (13)	C7—C6—C5	120.5 (4)
N4 ⁱ —Cd1—O3 ⁱⁱⁱ	80.69 (12)	C7—C6—H6	119.8
N4 ⁱⁱ —Cd1—O3 ⁱⁱⁱ	99.31 (12)	C5—C6—H6	119.8
N1 ⁱⁱⁱ —Cd1—O3 ⁱⁱⁱ	92.73 (13)	C8—C7—C6	120.5 (4)
N1—Cd1—O3 ⁱⁱⁱ	87.27 (13)	C8—C7—H7	119.8
O3—Cd1—O3 ⁱⁱⁱ	180.0	C6—C7—H7	119.8
N5—O3—Cd1	131.1 (3)	C7—C8—C9	120.0 (4)
C3—N1—C1	105.2 (3)	C7—C8—H8	120.0
C3—N1—Cd1	126.6 (3)	C9—C8—H8	120.0
C1—N1—Cd1	127.1 (3)	C10—C9—C8	119.1 (4)
C3—N2—C2	107.2 (3)	C10—C9—C11	120.5 (4)
C3—N2—C4	126.6 (4)	C8—C9—C11	120.3 (4)
C2—N2—C4	126.2 (4)	C9—C10—C5	121.0 (4)
C12—N3—C14	106.9 (3)	C9—C10—H10	119.5
C12—N3—C11	125.9 (4)	C5—C10—H10	119.5
C14—N3—C11	127.1 (4)	N3—C11—C9	111.8 (3)
C12—N4—C13	105.4 (3)	N3—C11—H11A	109.3
C12—N4—Cd1 ^{iv}	128.7 (3)	C9—C11—H11A	109.3
C13—N4—Cd1 ^{iv}	125.9 (3)	N3—C11—H11B	109.3

O3—N5—O1	123.7 (5)	C9—C11—H11B	109.3
O3—N5—O2	116.2 (5)	H11A—C11—H11B	107.9
O1—N5—O2	117.1 (5)	N4—C12—N3	111.6 (4)
C2—C1—N1	109.8 (4)	N4—C12—H12	124.2
C2—C1—H1	125.1	N3—C12—H12	124.2
N1—C1—H1	125.1	C14—C13—N4	109.9 (4)
C1—C2—N2	105.9 (4)	C14—C13—H13	125.0
C1—C2—H2	127.1	N4—C13—H13	125.0
N2—C2—H2	127.1	C13—C14—N3	106.2 (4)
N1—C3—N2	112.0 (4)	C13—C14—H14	126.9
N1—C3—H3	124.0	N3—C14—H14	126.9
N2—C3—H3	124.0		
N4 ⁱ —Cd1—O3—N5	13.2 (5)	N2—C4—C5—C6	-86.3 (5)
N4 ⁱⁱ —Cd1—O3—N5	-166.8 (5)	N2—C4—C5—C10	91.6 (5)
N1 ⁱⁱⁱ —Cd1—O3—N5	103.9 (5)	C10—C5—C6—C7	-2.1 (6)
N1—Cd1—O3—N5	-76.1 (5)	C4—C5—C6—C7	175.8 (4)
N4 ⁱ —Cd1—N1—C3	124.0 (3)	C5—C6—C7—C8	0.5 (7)
N4 ⁱⁱ —Cd1—N1—C3	-56.0 (3)	C6—C7—C8—C9	1.3 (7)
O3—Cd1—N1—C3	-136.7 (3)	C7—C8—C9—C10	-1.4 (6)
O3 ⁱⁱⁱ —Cd1—N1—C3	43.3 (3)	C7—C8—C9—C11	-178.2 (4)
N4 ⁱ —Cd1—N1—C1	-69.9 (3)	C8—C9—C10—C5	-0.2 (6)
N4 ⁱⁱ —Cd1—N1—C1	110.1 (3)	C11—C9—C10—C5	176.6 (4)
O3—Cd1—N1—C1	29.4 (3)	C6—C5—C10—C9	2.0 (6)
O3 ⁱⁱⁱ —Cd1—N1—C1	-150.6 (3)	C4—C5—C10—C9	-175.9 (4)
Cd1—O3—N5—O1	167.3 (4)	C12—N3—C11—C9	102.7 (5)
Cd1—O3—N5—O2	7.5 (9)	C14—N3—C11—C9	-72.9 (6)
C3—N1—C1—C2	0.6 (5)	C10—C9—C11—N3	123.7 (4)
Cd1—N1—C1—C2	-167.8 (3)	C8—C9—C11—N3	-59.5 (6)
N1—C1—C2—N2	0.0 (5)	C13—N4—C12—N3	0.3 (5)
C3—N2—C2—C1	-0.6 (5)	Cd1 ^{iv} —N4—C12—N3	-179.9 (3)
C4—N2—C2—C1	179.4 (4)	C14—N3—C12—N4	-0.2 (5)
C1—N1—C3—N2	-1.0 (4)	C11—N3—C12—N4	-176.6 (4)
Cd1—N1—C3—N2	167.5 (2)	C12—N4—C13—C14	-0.3 (5)
C2—N2—C3—N1	1.0 (5)	Cd1 ^{iv} —N4—C13—C14	179.9 (3)
C4—N2—C3—N1	-178.9 (3)	N4—C13—C14—N3	0.2 (5)
C3—N2—C4—C5	-102.7 (5)	C12—N3—C14—C13	0.0 (5)
C2—N2—C4—C5	77.3 (5)	C11—N3—C14—C13	176.3 (4)

Symmetry codes: (i) $x+1, -y+3/2, z-1/2$; (ii) $-x, y-1/2, -z+1/2$; (iii) $-x+1, -y+1, -z$; (iv) $-x, y+1/2, -z+1/2$.

Hydrogen-bond geometry ($\text{\AA}, ^\circ$)

$D-H\cdots A$	$D-H$	$H\cdots A$	$D\cdots A$	$D-H\cdots A$
C3—H3 \cdots O2 ^v	0.93	2.71	3.525 (8)	147
C4—H4B \cdots O1 ^v	0.97	2.67	3.525 (6)	148
C4—H4B \cdots O2 ^v	0.97	2.83	3.633 (9)	141
C10—H10 \cdots O2 ^v	0.93	2.63	3.506 (9)	158

C11—H11A···O1 ^{vi}	0.97	2.70	3.518 (7)	142
C12—H12···O1 ^{vi}	0.93	2.37	3.210 (6)	151

Symmetry codes: (v) $x-1, y, z$; (vi) $-x+1, y+1/2, -z+1/2$.