

Received 2 September 2017
Accepted 26 September 2017

Edited by T. J. Prior, University of Hull, England

Keywords: crystal structure; Cd^{II}–Na^I bimetallic; three-dimensional framework.

CCDC reference: 1576543

Supporting information: this article has supporting information at journals.iucr.org/e

Crystal structure of poly[diaquabis(μ_5 -benzene-1,3-dicarboxylato)(*N,N*-dimethylformamide)-cadmium(II)disodium(I)]


Matimon Sangsawang,^a Kittipong Chainok^b and Nanthawat Wannarit^{a*}

^aDepartment of Chemistry, Faculty of Science and Technology, Thammasat University, Khlong Laung, Pathumthani 12121, Thailand, and ^bMaterials and Textile Technology, Faculty of Science and Technology, Thammasat University, Khlong Laung, Pathumthani 12121, Thailand. *Correspondence e-mail: nwan0110@tu.ac.th

The title compound, $[CdNa_2(C_8H_4O_4)_2(C_3H_7NO)(H_2O)_2]_n$ or $[CdNa_2(1,3-bdc)_2(DMF)(H_2O)_2]_n$, is a new Cd^{II}–Na^I heterobimetallic coordination polymer. The asymmetric unit consists of one Cd^{II} atom, two Na^I atoms, two 1,3-bdc ligands, two coordinated water molecules and one coordinated DMF molecule. The Cd^{II} atom exhibits a seven-coordinate geometry, while the Na^I atoms can be considered to be pentacoordinate. The metal ions and their symmetry-related equivalents are connected via chelating–bridging carboxylate groups of the 1,3-bdc ligands to generate a three-dimensional framework. In the crystal, there are classical O–H···O hydrogen bonds involving the coordinated water molecules and the 1,3-bdc carboxylate groups and π – π stacking between the benzene rings of the 1,3-bdc ligands present within the frameworks.


1. Chemical context

Porous coordination polymers or metal–organic frameworks (MOFs) constructed from d^{10} transition metals and benzene polycarboxylate bridging ligands have been widely studied (Yaghi *et al.*, 1999; Lin *et al.*, 2008; Seco *et al.*, 2017) due to the varieties of coordination framework topologies and also potential applications in gas adsorption (Suh *et al.*, 2012), photoluminescence (Wang *et al.*, 2012) and photocatalysis (Wu *et al.*, 2017). Among the most common ligands in this class, the rigid and planar backbone of benzene dicarboxylates such as benzene-1,3-dicarboxylic acid (1,3-H₂bdc) and benzene-1,4-dicarboxylic acid (1,4-H₂bdc) are widely employed in the construction of these solids owing to their rich coordination modes. Studies incorporating alkaline metal ions into d^{10} -MOFs with one type of bridging ligand to construct novel heterobimetallic d^{10} -alkaline metal ion MOFs have been undertaken (Lin *et al.*, 2010*a,b*). The alkali metal ions could provide an unpredictable coordination number and pH-dependent self-assembly in the construction of coordination frameworks with various types of topology and dimensionality (Borah *et al.*, 2011; Chen *et al.*, 2011). However, the members of three-dimensional coordination framework heterobimetallic Zn^{II} or Cd^{II}/Na^I MOFs with benzenopolycarboxylate ligands are still limited; previous reports include [ZnNa(1,2,4-btc)] where 1,2,4-btc = benzene-1,2,4-tricarboxylate (Wang *et al.*, 2004), [Zn₂Na₂(1,4-bdc)₃·(DMF)₂·(m-H₂O)₂] where 1,4-bdcH₂ = benzene-1,4-dicarboxylic acid (Xu *et al.*, 2004), {[CdNa(1,3-bdc)₂]·[NH₂(CH₃)₂]}) where 1,3-bdcH₂ = benzene-1,3-dicarboxylic acid (Che *et al.*, 2007), [CdNa(OH-1,3-bdc)₂(H₂O)₂]·2H₂O where OH-1,3-bdcH₂ = 5-hydroxy-

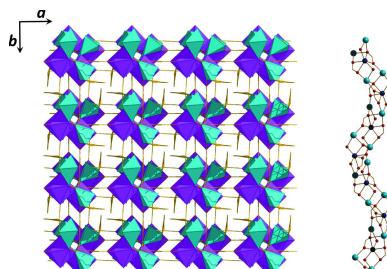

OPEN ACCESS

benzene-1,3-dicarboxylic acid (Du *et al.*, 2013) and $[Cd_8Na(ntc)_6(H_2O)_8]$ where $ntcH_3 = 5$ -nitrobenzene-1,2,3-tricarboxylic acid (Yang *et al.*, 2014). With the aim of searching for new members of this heterobimetallic MOFs system containing benzene-1,3-dicarboxylic acid ($1,3\text{-bdcH}_2$), we explored mixed sources of $Zn^{II}/Cd^{II}\text{-Na}^I$ with this ligand. The expected products are prepared by using a direct synthetic method, mixing metal nitrate salts, $1,3\text{-bdcH}_2$ and NaOH (mole ratio 1:1:2) in water, methanol and DMF solvents. However, only the $Cd^{II}\text{-Na}^I$ MOF product has been successfully synthesized. As part of our ongoing studies on this complex, we describe here the synthesis and crystal structure of a novel three-dimensional heterobimetallic $Cd^{II}\text{-Na}^I$ MOF, $[CdNa_2(1,3\text{-bdc})_2(DMF)(H_2O)_2]_n$ (**I**).

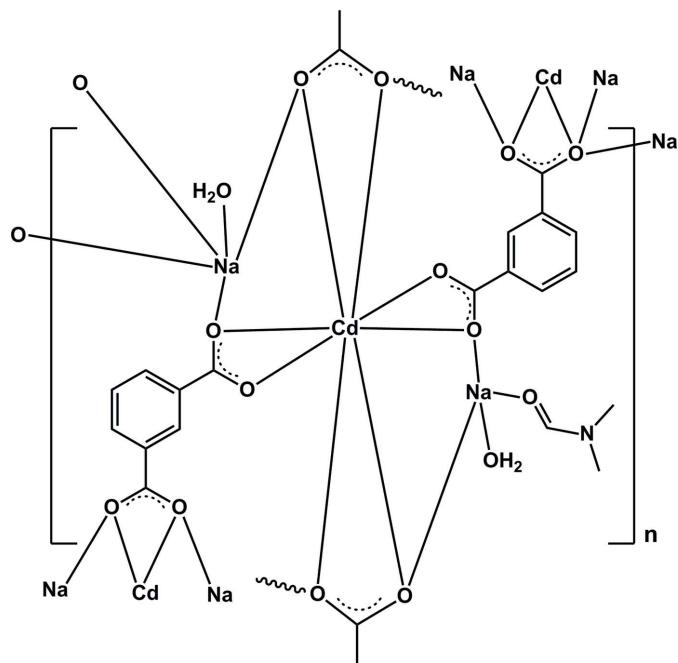

2. Structural commentary

The title compound (**I**) crystallizes in the tetragonal crystal system with polar $P4_3$ space group. The asymmetric unit of (**I**) consists of one Cd^{II} ion, two crystallographically independent $Na(I)$ ions, two 1,3-bdc ligands, two coordinated water molecules and one DMF molecules, as shown in Fig. 1. Each Cd^{II} ion is coordinated by seven carboxylate oxygen atoms from four different 1,3-bdc ligands with the $Cd-O$ bond distances range between 2.301 (3) and 2.555 (3) Å (Table 1). The $Na1$ ion is surrounded by three carboxylate oxygen atoms of three different 1,3-bdc ligands, one oxygen atom from a water molecule, and one DMF molecule with the $Na-O$ bond distances ranging between 2.304 (7) and 2.498 (11) Å, while the $Na2$ ion adopts a five-coordinate [4 + 1] coordination with four oxygen atoms from three different 1,3-bdc ligands and one oxygen atom from a water molecule. The $Na-O$ bond distances are in the range 2.275 (5) to 2.354 (8) Å. Fig. 2 shows the coordination modes of the 1,3-bdc ligand in compound (**I**). The 1,3-bdc molecule is fully deprotonated and coordinated to

Table 1
Selected geometric parameters (Å, °).

$Cd1-O1$	2.301 (3)	$Na1-O4^i$	2.441 (5)
$Cd1-O2$	2.555 (3)	$Na1-O9$	2.304 (7)
$Cd1-O3^i$	2.496 (3)	$Na1-O11B$	2.498 (11)
$Cd1-O4^i$	2.385 (3)	$Na1-O11A$	2.475 (18)
$Cd1-O5$	2.284 (4)	$Na2-O4^{iv}$	2.655 (5)
$Cd1-O7^{ii}$	2.396 (3)	$Na2-O5$	2.277 (5)
$Cd1-O8^{ii}$	2.472 (3)	$Na2-O7^{ii}$	2.282 (4)
$Na1-O1$	2.368 (5)	$Na2-O8^v$	2.275 (5)
$Na1-O3^{iii}$	2.339 (5)	$Na2-O10$	2.354 (8)
$O1-Cd1-O2$	53.12 (15)	$O1-Na1-O4^i$	77.84 (17)
$O1-Cd1-O3^i$	131.59 (15)	$O1-Na1-O11B$	104.1 (3)
$O1-Cd1-O4^i$	80.31 (12)	$O3^{iii}-Na1-O1$	151.1 (2)
$O1-Cd1-O7^{ii}$	125.91 (12)	$O3^{iii}-Na1-O4^i$	94.59 (15)
$O1-Cd1-O8^{ii}$	92.04 (13)	$O3^{iii}-Na1-O11B$	82.9 (3)
$O3^i-Cd1-O2$	173.00 (16)	$O4^i-Na1-O11B$	177.4 (3)
$O4^i-Cd1-O2$	132.60 (15)	$O9-Na1-O1$	95.8 (2)
$O4^i-Cd1-O3^i$	53.37 (13)	$O9-Na1-O3^{iii}$	112.0 (2)
$O4^i-Cd1-O7^{ii}$	122.40 (12)	$O9-Na1-O4^i$	88.3 (2)
$O4^i-Cd1-O8^{ii}$	78.81 (13)	$O9-Na1-O11B$	93.2 (4)
$O5-Cd1-O1$	125.67 (14)	$O5-Na2-O4^{iv}$	95.45 (19)
$O5-Cd1-O2$	90.36 (16)	$O5-Na2-O7^{ii}$	83.03 (18)
$O5-Cd1-O3^i$	82.65 (15)	$O5-Na2-O10$	104.5 (2)
$O5-Cd1-O4^i$	128.83 (14)	$O7^{ii}-Na2-O4^{iv}$	94.98 (14)
$O5-Cd1-O7^{ii}$	80.41 (12)	$O7^{ii}-Na2-O10$	80.5 (2)
$O5-Cd1-O8^{ii}$	133.24 (16)	$O8^v-Na2-O4^{iv}$	77.02 (13)
$O7^{ii}-Cd1-O2$	85.03 (15)	$O8^v-Na2-O5$	110.18 (16)
$O7^{ii}-Cd1-O3^i$	94.01 (14)	$O8^v-Na2-O7^{ii}$	164.93 (18)
$O7^{ii}-Cd1-O8^{ii}$	53.55 (14)	$O8^v-Na2-O10$	102.3 (2)
$O8^{ii}-Cd1-O2$	93.07 (11)	$O10-Na2-O4^{iv}$	158.8 (2)
$O8^{ii}-Cd1-O3^i$	91.92 (10)		

Symmetry codes: (i) $x, y - 1, z$; (ii) $x - 1, y, z$; (iii) $-y + 1, x, z - \frac{1}{4}$; (iv) $y - 1, -x, z + \frac{1}{4}$; (v) $y, -x + 1, z + \frac{1}{4}$.

the Cd^{II} and Na^I ions in a μ_5 -coordination mode, creating a one-dimensional heterobimetallic chain running parallel to the c axis, Fig. 3. Adjacent chains are further connected

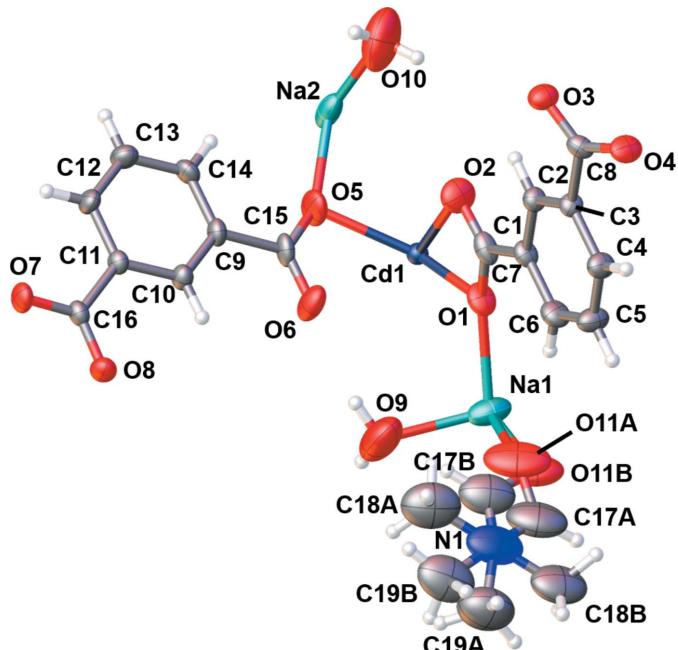


Figure 1
Asymmetric unit of (**I**) with the atomic-numbering scheme. Displacement ellipsoids are drawn at the 50% probability level.

Table 2
Hydrogen-bond geometry (\AA , $^\circ$).

$D-\text{H}\cdots A$	$D-\text{H}$	$\text{H}\cdots A$	$D\cdots A$	$D-\text{H}\cdots A$
O9—H9B \cdots O6	0.90	2.22	3.074 (8)	159
O10—H10B \cdots O6 ^y	0.86	2.29	3.073 (8)	152

Symmetry code: (v) $y, -x + 1, z + \frac{1}{4}$.

through the 1,3-bdc ligands in the a - and b -axis directions, generating a three-dimensional framework structure as shown in Fig. 4. The coordinated water and DMF molecules adopt a monodentate coordination mode and serve as a terminal pendant ligand pointing inside the channels.

3. Supramolecular features

In the crystal of (I), classical O—H \cdots O hydrogen bonds and aromatic π — π stacking interactions are observed and these interactions presumably help to stabilize the frameworks. All water molecules are shown to act as O—H \cdots O hydrogen-bond donors towards the carboxylate groups of the 1,3-bdc ligands (Table 2). The π — π stacking interactions are between symmetry-related aromatic rings of the 1,3-bdc ligands with a $Cg1\cdots Cg2^1$ distance of 3.588 (3) \AA and a dihedral angle of 3.8 (4) $^\circ$ [$Cg1$ and $Cg2$ are the centroids of the C1—C6 and C9—C14 rings, respectively; symmetry code: (i) $-y, x, z - 1/4$].

4. Database survey

To the best of our knowledge of structures closely related to (I), only the three-dimensional coordination framework $\{[\text{CdNa}(1,3-\text{bdc})_2]\cdot[\text{NH}_2(\text{CH}_3)_2]\}$ has been reported (Che *et al.*, 2007). This compound crystallized in the centrosymmetric space group $C2/c$. The Cd^{II} and Na^I centers are linked by a 1,3-bdc ligand in a μ_4 -coordination mode. The DMF solvent decomposes under solvothermal synthesis, with the construction of a 3D coordination framework with open channels containing $\text{NH}_2(\text{CH}_3)_2$ molecules. In comparison, compound

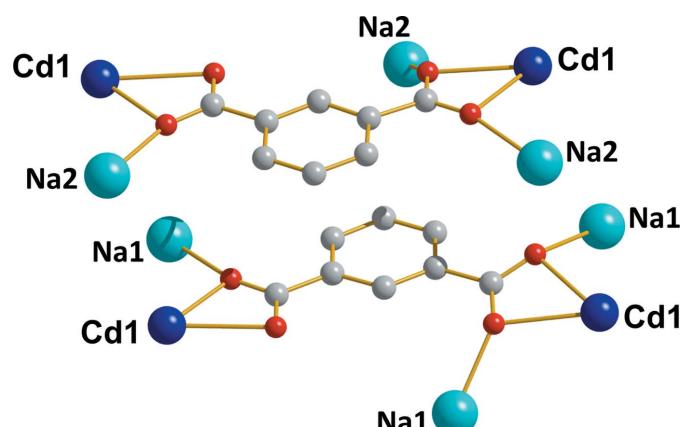


Figure 2
Coordination mode of the μ_5 -1,3-bdc bridging ligands found in (I). All hydrogen atoms are omitted for clarity.

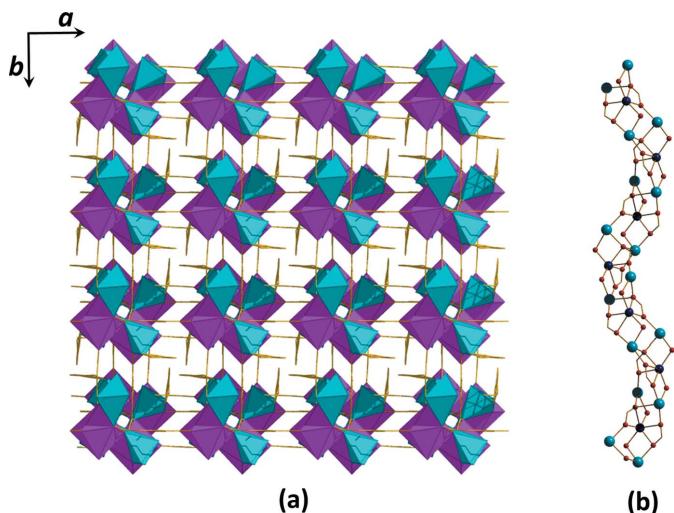


Figure 3
Perspective view along the crystallographic c axis of (a) the three-dimensional framework of (I) (the coordination polyhedra for Cd^{II} and Na^I are pink and green, respectively) and (b) helical chain-like structure of the Cd—Na clusters (dark blue = Cd, blue = Na and red = O).

(I) contains coordinated H₂O and DMF molecules projecting into the framework channels. Other related three-dimensional heterobimetallic d^{10} —Na^I coordination frameworks containing benzenepolycarboxylate ligands have been published, such as $[\text{CdNa}(\text{OH}-1,3-\text{bdc})_2(\text{H}_2\text{O})_2]\cdot2\text{H}_2\text{O}$ where OH-1,3-bdcH₂ = 5-hydroxy-benzene-1,3-dicarboxylic acid (Du *et al.*, 2013), $[\text{Zn}_2\text{Na}_2(1,4-\text{bdc})_3\cdot(\text{DMF})_2\cdot(m\text{-H}_2\text{O})_2]$ where 1,4-bdcH₂ = benzene-1,4-dicarboxylic acid (Xu *et al.*, 2004), $[\text{ZnNa}(1,2,4-\text{btc})]$ where 1,2,4-btc = 1,2,4-benzenetricarboxylate (Wang *et al.*, 2004), and $[\text{Cd}_8\text{Na}(\text{ntc})_6(\text{H}_2\text{O})_8]$ where ntcH₃ = 5-nitrobenzene-1,2,3-tricarboxylic acid (Yang *et al.*, 2014). The three-dimensional coordination framework topologies of these compounds are the result of the construction of different types of metal centers, geometries and carboxylate ligand derivatives. It is found that the carboxylate ligand derivatives in the structure of these related compounds exhibit a μ_4 -coordination mode.

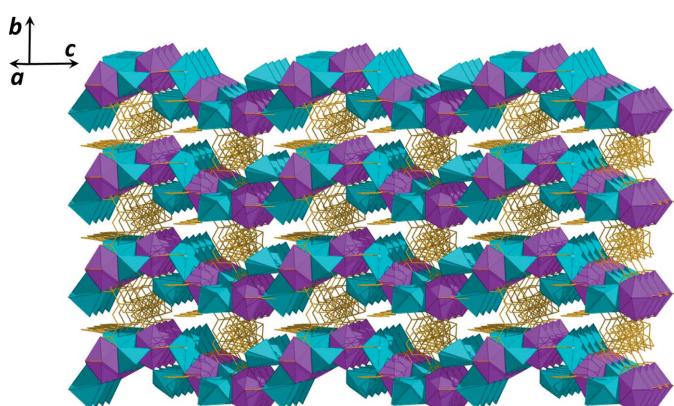


Figure 4
Perspective view of the three-dimensional framework of (I) (the coordination polyhedra for Cd^{II} and Na^I are pink and green, respectively). All hydrogen atoms are omitted for clarity.

Table 3
Experimental details.

Crystal data	
Chemical formula	[CdNa ₂ (C ₈ H ₄ O ₄) ₂ (C ₃ H ₇ NO)(H ₂ O) ₂]
<i>M</i> _r	595.73
Crystal system, space group	Tetragonal, <i>P</i> 4 ₃
Temperature (K)	296
<i>a</i> , <i>c</i> (Å)	10.1437 (8), 21.4664 (15)
<i>V</i> (Å ³)	2208.8 (4)
<i>Z</i>	4
Radiation type	Mo <i>K</i> α
μ (mm ⁻¹)	1.09
Crystal size (mm)	0.35 × 0.21 × 0.16
Data collection	Bruker APEXII D8 QUEST CMOS
Diffractometer	Multi-scan (<i>SADABS</i> , Bruker, 2013)
Absorption correction	
<i>T</i> _{min} , <i>T</i> _{max}	0.647, 0.704
No. of measured, independent and observed [<i>I</i> > 2σ(<i>I</i>)] reflections	56814, 5708, 5301
<i>R</i> _{int}	0.074
(sin θ/λ) _{max} (Å ⁻¹)	0.676
Refinement	
<i>R</i> [<i>F</i> ² > 2σ(<i>F</i> ²)], <i>wR</i> (<i>F</i> ²), <i>S</i>	0.028, 0.068, 1.03
No. of reflections	5708
No. of parameters	351
No. of restraints	160
H-atom treatment	H-atom parameters constrained
Δρ _{max} , Δρ _{min} (e Å ⁻³)	0.52, -0.45
Absolute structure	Flack <i>x</i> determined using 2427 quotients [(<i>I</i> ⁺) - (<i>I</i> ⁻)]/[(<i>I</i> ⁺) + (<i>I</i> ⁻)] (Parsons <i>et al.</i> , 2013)
Absolute structure parameter	0.081 (13)

Computer programs: *APEX2* and *SAINT* (Bruker, 2013), *SHELXT* (Sheldrick, 2015a), *SHELXL* (Sheldrick, 2015b) and *OLEX2* (Dolomanov *et al.*, 2009).

5. Synthesis and crystallization

A mixture solution of 1,3-bdcH₂ (1.0 mmol) and NaOH (2.0 mmol) in 10 mL of distilled water was slowly dropped to a methanolic solution (10 ml) of Cd(NO₃)₂·4H₂O (1.0 mmol). The reaction mixture was stirred at 333 K for 30 min and allowed to cool to room temperature and then filtered. The filtrate was allowed to stand to slowly evaporate at ambient temperature. Colorless block-shaped crystals suitable for single crystal X-ray diffraction were obtained after three days (76% yield based on Cd).

6. Refinement

Crystal data, data collection and structure refinement details are summarized in Table 3. All hydrogen atoms except those

of water molecules were generated geometrically and refined isotropically using a riding model, with C—H = 0.93 Å and *U*_{iso}(H) = 1.2*U*_{eq}(C). The coordinated DMF molecule was found to be disordered with two sets of sites with a refined occupancy ratio of 0.382 (10) and 0.618 (10).

Acknowledgements

The authors acknowledge the Department of Chemistry, Faculty of Science and Technology, Thammasat University, Thailand, for financial support and the Central Scientific Instrument Center (CSIC) for funds to purchase the X-ray diffractometer at the Faculty of Science and Technology, Thammasat University, Thailand.

References

- Borah, B. M., Dey, S. K. & Das, G. (2011). *Cryst. Growth Des.* **11**, 2773–2779.
- Bruker (2013). *APEX2*, *SAINT* and *SADABS*. Bruker AXS Inc., Madison, Wisconsin, USA.
- Che, G.-B., Liu, C.-B., Wang, L. & Cui, Y.-C. (2007). *J. Coord. Chem.* **60**, 1997–2007.
- Chen, Y., Zheng, L., She, S., Chen, Z., Hu, B. & Li, Y. (2011). *Dalton Trans.* **40**, 4970–4975.
- Dolomanov, O. V., Bourhis, L. J., Gildea, R. J., Howard, J. A. K. & Puschmann, H. (2009). *J. Appl. Cryst.* **42**, 339–341.
- Du, F., Zhang, H., Tian, C. & Du, S. (2013). *Cryst. Growth Des.* **13**, 1736–1742.
- Lin, J.-D., Cheng, J.-W. & Du, S.-W. (2008). *Cryst. Growth Des.* **8**, 3345–3353.
- Lin, J.-D., Long, X. F., Lin, P. & Du, S.-W. (2010). *Cryst. Growth Des.* **10**, 146–157.
- Lin, J.-D., Wu, S. T., Li, Z. H. & Du, S.-W. (2010). *Dalton Trans.* **39**, 10719–10728.
- Parsons, S., Flack, H. D. & Wagner, T. (2013). *Acta Cryst. B* **69**, 249–259.
- Seco, J. M., Pérez-Yáñez, S., Briones, D., García, J.Á., Cepeda, J. & Rodríguez-Díéguez, A. (2017). *Cryst. Growth Des.* **17**, 3893–3906.
- Sheldrick, G. M. (2015a). *Acta Cryst. A* **71**, 3–8.
- Sheldrick, G. M. (2015b). *Acta Cryst. C* **71**, 3–8.
- Suh, M. P., Park, H. J., Prasad, T. K. & Lim, D.-W. (2012). *Chem. Rev.* **112**, 782–835.
- Wang, X.-L., Mu, B., Lin, H.-Y., Yang, S., Liu, G.-C., Tian, A.-X. & Zhang, J.-W. (2012). *Dalton Trans.* **41**, 11074–11084.
- Wang, L., Shi, Z., Li, G., Fan, Y., Fu, W. & Feng, S. (2004). *Solid State Sci.* **6**, 85–90.
- Wu, Z., Yuan, X., Zhang, J., Wang, H., Jiang, L. & Zeng, G. (2017). *ChemCatChem*, **9**, 41–64.
- Xu, H., Wang, R. & Li, Y. (2004). *J. Mol. Struct.* **688**, 1–3.
- Yaghi, O. M., Li, H., Eddaoudi, M. & O'Keeffe, M. (1999). *Nature*, **402**, 276–279.
- Yang, Y.-T., Zhao, Q., Tu, C.-Z., Cheng, F. X. & Wang, F. (2014). *Inorg. Chem. Commun.* **40**, 43–46.

supporting information

Acta Cryst. (2017). E73, 1599–1602 [https://doi.org/10.1107/S2056989017013871]

Crystal structure of poly[diaquabis(μ_5 -benzene-1,3-dicarboxylato)(N,N-dimethylformamide)cadmium(II)disodium(I)]


Matimon Sangsawang, Kittipong Chainok and Nanthawat Wannarit

Computing details

Data collection: *APEX2* (Bruker, 2013); cell refinement: *SAINT* (Bruker, 2013); data reduction: *SAINT* (Bruker, 2013); program(s) used to solve structure: *SHELXT* (Sheldrick, 2015a); program(s) used to refine structure: *SHELXL* (Sheldrick, 2015b); molecular graphics: *OLEX2* (Dolomanov *et al.*, 2009); software used to prepare material for publication: *OLEX2* (Dolomanov *et al.*, 2009).

Poly[diaquabis(μ_5 -benzene-1,3-dicarboxylato)(N,N-dimethylformamide)cadmium(II)disodium(I)]

Crystal data



$M_r = 595.73$

Tetragonal, $P4_3$

$a = 10.1437(8)$ Å

$c = 21.4664(15)$ Å

$V = 2208.8(4)$ Å³

$Z = 4$

$F(000) = 1192$

$D_x = 1.791$ Mg m⁻³

Mo $K\alpha$ radiation, $\lambda = 0.71073$ Å

Cell parameters from 9769 reflections

$\theta = 2.7\text{--}28.3^\circ$

$\mu = 1.09$ mm⁻¹

$T = 296$ K

Block, colourless

$0.35 \times 0.21 \times 0.16$ mm

Data collection

Bruker APEXII D8 QUEST CMOS
diffractometer

Detector resolution: 10.5 pixels mm⁻¹

ω and φ scans

Absorption correction: multi-scan
(SADABS, Bruker, 2013)

$T_{\min} = 0.647$, $T_{\max} = 0.704$

56814 measured reflections

5708 independent reflections

5301 reflections with $I > 2\sigma(I)$

$R_{\text{int}} = 0.074$

$\theta_{\max} = 28.7^\circ$, $\theta_{\min} = 2.8^\circ$

$h = -13 \rightarrow 13$

$k = -12 \rightarrow 13$

$l = -28 \rightarrow 29$

Refinement

Refinement on F^2

Least-squares matrix: full

$R[F^2 > 2\sigma(F^2)] = 0.028$

$wR(F^2) = 0.068$

$S = 1.03$

5708 reflections

351 parameters

160 restraints

Hydrogen site location: mixed

H-atom parameters constrained

$$w = 1/[\sigma^2(F_o^2) + (0.0375P)^2 + 0.6193P]$$

$$\text{where } P = (F_o^2 + 2F_c^2)/3$$

$(\Delta/\sigma)_{\max} < 0.001$

$\Delta\rho_{\max} = 0.52$ e Å⁻³

$\Delta\rho_{\min} = -0.45$ e Å⁻³

Extinction correction: *SHELXL*,

$$Fc^* = kFc[1 + 0.001xFc^2\lambda^3/\sin(2\theta)]^{-1/4}$$

Extinction coefficient: 0.0050 (7)

Absolute structure: Flack x determined using

2427 quotients $[(I^+)-(I^-)]/[(I^+)+(I^-)]$ (Parsons *et al.*, 2013)

Absolute structure parameter: 0.081 (13)

Special details

Geometry. All esds (except the esd in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell esds are taken into account individually in the estimation of esds in distances, angles and torsion angles; correlations between esds in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell esds is used for estimating esds involving l.s. planes.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	<i>x</i>	<i>y</i>	<i>z</i>	$U_{\text{iso}}^*/U_{\text{eq}}$	Occ. (<1)
Cd1	0.08591 (2)	0.23028 (2)	0.49814 (3)	0.02155 (9)	
Na1	0.1091 (4)	0.2329 (2)	0.33008 (17)	0.0575 (9)	
Na2	0.1037 (2)	0.2125 (3)	0.66027 (15)	0.0510 (8)	
O1	0.0894 (3)	0.3769 (3)	0.41640 (17)	0.0357 (8)	
O2	0.0886 (4)	0.4817 (3)	0.5052 (3)	0.0458 (10)	
O3	0.1045 (3)	0.9851 (3)	0.5013 (2)	0.0349 (6)	
O4	0.0482 (4)	1.0819 (3)	0.41384 (15)	0.0354 (8)	
O5	0.2394 (3)	0.2174 (5)	0.57576 (19)	0.0502 (10)	
O6	0.3488 (3)	0.2217 (4)	0.4890 (2)	0.0490 (10)	
O7	0.9433 (3)	0.2411 (4)	0.58696 (16)	0.0337 (7)	
O8	0.8424 (3)	0.2200 (3)	0.4971 (2)	0.0319 (6)	
O9	0.3263 (6)	0.1781 (9)	0.3477 (3)	0.111 (2)	
H9A	0.3381	0.0906	0.3450	0.166*	
H9B	0.3540	0.2025	0.3857	0.166*	
O10	0.0517 (7)	0.4353 (7)	0.6789 (3)	0.118 (2)	
H10A	0.0182	0.4694	0.6461	0.178*	
H10B	0.1218	0.4773	0.6885	0.178*	
C1	0.0879 (4)	0.6114 (4)	0.4125 (2)	0.0251 (8)	
C2	0.0830 (4)	0.7316 (4)	0.4438 (2)	0.0236 (8)	
H2	0.0798	0.7328	0.4871	0.028*	
C3	0.0829 (4)	0.8496 (4)	0.4111 (2)	0.0225 (8)	
C4	0.0860 (5)	0.8478 (4)	0.3463 (2)	0.0312 (10)	
H4	0.0847	0.9267	0.3242	0.037*	
C5	0.0909 (5)	0.7295 (4)	0.3148 (2)	0.0364 (12)	
H5	0.0935	0.7284	0.2715	0.044*	
C6	0.0918 (5)	0.6114 (4)	0.3481 (2)	0.0335 (10)	
H6	0.0951	0.5317	0.3268	0.040*	
C7	0.0881 (4)	0.4829 (4)	0.4476 (3)	0.0314 (10)	
C8	0.0788 (4)	0.9796 (4)	0.4444 (2)	0.0249 (8)	
C9	0.4717 (4)	0.2316 (4)	0.5837 (2)	0.0257 (8)	
C10	0.5928 (4)	0.2363 (4)	0.5534 (2)	0.0245 (9)	
H10	0.5962	0.2377	0.5101	0.029*	
C11	0.7089 (4)	0.2390 (4)	0.58795 (19)	0.0220 (8)	
C12	0.7034 (4)	0.2399 (5)	0.6526 (2)	0.0286 (9)	
H12	0.7809	0.2424	0.6758	0.034*	
C13	0.5834 (4)	0.2370 (4)	0.6825 (2)	0.0327 (10)	
H13	0.5802	0.2389	0.7258	0.039*	
C14	0.4674 (4)	0.2313 (4)	0.6486 (2)	0.0285 (9)	
H14	0.3867	0.2273	0.6691	0.034*	

C15	0.3461 (4)	0.2229 (4)	0.5460 (2)	0.0300 (9)	
C16	0.8396 (4)	0.2330 (4)	0.5549 (2)	0.0227 (8)	
O11B	0.1647 (14)	0.3817 (14)	0.2412 (5)	0.082 (3)	0.618 (10)
N1	0.3469 (8)	0.4165 (5)	0.1823 (3)	0.0859 (17)	
C17B	0.2980 (15)	0.3983 (11)	0.2335 (6)	0.088 (3)	0.618 (10)
H17B	0.3526	0.3957	0.2683	0.106*	0.618 (10)
C18B	0.2609 (14)	0.4209 (11)	0.1244 (7)	0.093 (3)	0.618 (10)
H18A	0.2369	0.3328	0.1127	0.140*	0.618 (10)
H18B	0.3088	0.4617	0.0910	0.140*	0.618 (10)
H18C	0.1828	0.4711	0.1330	0.140*	0.618 (10)
C19B	0.4849 (13)	0.4221 (13)	0.1669 (8)	0.099 (3)	0.618 (10)
H19A	0.5354	0.4346	0.2043	0.149*	0.618 (10)
H19B	0.5005	0.4943	0.1390	0.149*	0.618 (10)
H19C	0.5109	0.3411	0.1473	0.149*	0.618 (10)
C18A	0.439 (2)	0.424 (2)	0.2384 (9)	0.105 (5)	0.382 (10)
H18D	0.3884	0.4164	0.2760	0.157*	0.382 (10)
H18E	0.4851	0.5063	0.2380	0.157*	0.382 (10)
H18F	0.5015	0.3527	0.2364	0.157*	0.382 (10)
C19A	0.433 (3)	0.417 (3)	0.1269 (10)	0.110 (6)	0.382 (10)
H19D	0.4565	0.5063	0.1169	0.165*	0.382 (10)
H19E	0.3865	0.3786	0.0923	0.165*	0.382 (10)
H19F	0.5109	0.3670	0.1353	0.165*	0.382 (10)
C17A	0.2249 (19)	0.401 (2)	0.1936 (11)	0.098 (4)	0.382 (10)
H17A	0.1610	0.3926	0.1628	0.117*	0.382 (10)
O11A	0.198 (3)	0.396 (2)	0.2554 (10)	0.102 (5)	0.382 (10)

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Cd1	0.02087 (14)	0.02266 (15)	0.02112 (12)	0.00064 (10)	-0.00023 (11)	-0.00002 (11)
Na1	0.096 (2)	0.0428 (14)	0.0337 (16)	-0.0075 (12)	0.0048 (15)	-0.0055 (8)
Na2	0.0289 (10)	0.0944 (19)	0.0298 (14)	-0.0066 (10)	-0.0059 (9)	0.0114 (12)
O1	0.0375 (18)	0.0144 (13)	0.055 (2)	-0.0009 (11)	-0.0018 (15)	0.0020 (13)
O2	0.062 (2)	0.0262 (15)	0.049 (3)	-0.0022 (14)	-0.001 (2)	0.0105 (18)
O3	0.0471 (16)	0.0271 (13)	0.0305 (15)	0.0009 (12)	-0.0002 (19)	-0.0023 (17)
O4	0.055 (2)	0.0144 (13)	0.0365 (18)	0.0024 (13)	0.0009 (15)	0.0005 (12)
O5	0.0156 (15)	0.083 (3)	0.052 (2)	-0.0012 (16)	-0.0008 (14)	0.005 (2)
O6	0.0319 (17)	0.079 (3)	0.036 (3)	-0.0123 (16)	-0.0103 (17)	0.007 (2)
O7	0.0159 (13)	0.048 (2)	0.0369 (17)	-0.0016 (13)	-0.0045 (12)	0.0016 (15)
O8	0.0263 (13)	0.0429 (15)	0.0265 (13)	0.0009 (11)	0.0044 (17)	0.0006 (18)
O9	0.087 (4)	0.193 (8)	0.052 (3)	0.004 (5)	-0.013 (3)	0.003 (4)
O10	0.113 (5)	0.122 (5)	0.120 (6)	-0.002 (4)	-0.047 (4)	0.049 (4)
C1	0.025 (2)	0.0149 (17)	0.035 (2)	-0.0004 (15)	0.0015 (16)	0.0031 (16)
C2	0.025 (2)	0.0183 (19)	0.027 (2)	-0.0009 (15)	-0.0013 (15)	0.0021 (14)
C3	0.026 (2)	0.0151 (18)	0.026 (2)	-0.0021 (14)	-0.0009 (16)	0.0006 (15)
C4	0.041 (3)	0.022 (2)	0.030 (2)	0.0029 (18)	0.0003 (19)	0.0024 (17)
C5	0.055 (3)	0.028 (2)	0.027 (2)	0.002 (2)	0.0015 (19)	-0.0009 (16)
C6	0.038 (3)	0.020 (2)	0.042 (3)	0.0019 (18)	0.001 (2)	-0.0050 (18)

C7	0.022 (2)	0.0180 (19)	0.054 (3)	-0.0016 (15)	-0.0008 (19)	0.0063 (19)
C8	0.0244 (19)	0.0190 (19)	0.031 (2)	-0.0021 (15)	0.0077 (16)	-0.0011 (16)
C9	0.0167 (18)	0.027 (2)	0.033 (2)	-0.0001 (15)	-0.0045 (16)	0.0025 (17)
C10	0.0184 (19)	0.030 (2)	0.026 (2)	-0.0022 (16)	-0.0008 (14)	0.0035 (15)
C11	0.0165 (17)	0.0230 (19)	0.0265 (19)	-0.0025 (14)	-0.0009 (15)	0.0003 (15)
C12	0.023 (2)	0.039 (2)	0.024 (2)	-0.0001 (17)	-0.0057 (16)	-0.0027 (18)
C13	0.032 (2)	0.041 (3)	0.024 (2)	-0.002 (2)	0.0034 (16)	-0.0011 (17)
C14	0.019 (2)	0.034 (2)	0.032 (2)	0.0019 (17)	0.0061 (16)	-0.0008 (18)
C15	0.0143 (18)	0.029 (2)	0.046 (3)	-0.0017 (15)	-0.0069 (18)	0.0079 (19)
C16	0.0159 (17)	0.0210 (18)	0.031 (2)	-0.0006 (14)	0.0001 (15)	0.0015 (15)
O11B	0.125 (6)	0.051 (6)	0.068 (6)	-0.015 (4)	0.025 (4)	-0.027 (5)
N1	0.135 (5)	0.030 (2)	0.093 (3)	0.000 (3)	0.035 (3)	-0.001 (2)
C17B	0.127 (6)	0.047 (5)	0.091 (4)	-0.012 (4)	0.028 (3)	-0.004 (3)
C18B	0.143 (6)	0.041 (6)	0.095 (5)	0.012 (5)	0.029 (4)	-0.008 (4)
C19B	0.135 (5)	0.048 (6)	0.115 (7)	0.001 (4)	0.036 (4)	0.017 (6)
C18A	0.144 (7)	0.073 (12)	0.098 (5)	-0.018 (7)	0.030 (5)	0.008 (6)
C19A	0.136 (8)	0.099 (18)	0.095 (5)	0.006 (9)	0.035 (5)	0.005 (7)
C17A	0.137 (5)	0.057 (10)	0.100 (6)	-0.008 (4)	0.040 (4)	-0.029 (6)
O11A	0.155 (10)	0.052 (9)	0.100 (6)	-0.039 (9)	0.046 (6)	-0.037 (7)

Geometric parameters (\AA , $^{\circ}$)

Cd1—O1	2.301 (3)	C1—C7	1.505 (6)
Cd1—O2	2.555 (3)	C2—H2	0.9300
Cd1—O3 ⁱ	2.496 (3)	C2—C3	1.388 (5)
Cd1—O4 ⁱ	2.385 (3)	C3—C4	1.391 (6)
Cd1—O5	2.284 (4)	C3—C8	1.501 (5)
Cd1—O7 ⁱⁱ	2.396 (3)	C4—H4	0.9300
Cd1—O8 ⁱⁱ	2.472 (3)	C4—C5	1.379 (6)
Na1—Na2 ⁱⁱⁱ	3.914 (6)	C5—H5	0.9300
Na1—O1	2.368 (5)	C5—C6	1.395 (7)
Na1—O3 ^{iv}	2.339 (5)	C6—H6	0.9300
Na1—O4 ⁱ	2.441 (5)	C9—C10	1.390 (6)
Na1—O9	2.304 (7)	C9—C14	1.395 (6)
Na1—O11B	2.498 (11)	C9—C15	1.511 (6)
Na1—O11A	2.475 (18)	C10—H10	0.9300
Na2—Cd1 ^v	3.791 (3)	C10—C11	1.392 (5)
Na2—Na1 ^v	3.914 (6)	C11—C12	1.390 (6)
Na2—O4 ^{vi}	2.655 (5)	C11—C16	1.505 (5)
Na2—O5	2.277 (5)	C12—H12	0.9300
Na2—O7 ⁱⁱ	2.282 (4)	C12—C13	1.376 (6)
Na2—O8 ^{vii}	2.275 (5)	C13—H13	0.9300
Na2—O10	2.354 (8)	C13—C14	1.385 (6)
O1—C7	1.266 (6)	C14—H14	0.9300
O2—C7	1.237 (8)	O11B—C17B	1.373 (18)
O3—Cd1 ^{viii}	2.495 (3)	N1—C17B	1.221 (13)
O3—Na1 ^{vii}	2.339 (5)	N1—C18B	1.517 (15)
O3—C8	1.250 (6)	N1—C19B	1.439 (14)

O4—Cd1 ^{viii}	2.385 (3)	N1—C18A	1.526 (18)
O4—Na1 ^{viii}	2.442 (5)	N1—C19A	1.473 (17)
O4—Na2 ^{ix}	2.655 (5)	N1—C17A	1.271 (19)
O4—C8	1.266 (5)	C17B—H17B	0.9300
O5—C15	1.259 (6)	C18B—H18A	0.9600
O6—C15	1.224 (7)	C18B—H18B	0.9600
O7—Cd1 ^x	2.396 (3)	C18B—H18C	0.9600
O7—Na2 ^x	2.282 (4)	C19B—H19A	0.9600
O7—C16	1.259 (5)	C19B—H19B	0.9600
O8—Cd1 ^x	2.472 (3)	C19B—H19C	0.9600
O8—Na2 ^{iv}	2.275 (5)	C18A—H18D	0.9600
O8—C16	1.248 (6)	C18A—H18E	0.9600
O9—H9A	0.8971	C18A—H18F	0.9600
O9—H9B	0.8991	C19A—H19D	0.9600
O10—H10A	0.8544	C19A—H19E	0.9600
O10—H10B	0.8548	C19A—H19F	0.9600
C1—C2	1.393 (6)	C17A—H17A	0.9300
C1—C6	1.383 (7)	C17A—O11A	1.36 (2)
O1—Cd1—O2	53.12 (15)	Na2—O10—H10B	109.5
O1—Cd1—O3 ⁱ	131.59 (15)	H10A—O10—H10B	109.2
O1—Cd1—O4 ⁱ	80.31 (12)	C2—C1—C7	121.2 (4)
O1—Cd1—O7 ⁱⁱ	125.91 (12)	C6—C1—C2	118.9 (4)
O1—Cd1—O8 ⁱⁱ	92.04 (13)	C6—C1—C7	120.0 (4)
O3 ⁱ —Cd1—O2	173.00 (16)	C1—C2—H2	119.6
O4 ⁱ —Cd1—O2	132.60 (15)	C3—C2—C1	120.7 (4)
O4 ⁱ —Cd1—O3 ⁱ	53.37 (13)	C3—C2—H2	119.6
O4 ⁱ —Cd1—O7 ⁱⁱ	122.40 (12)	C2—C3—C4	119.7 (4)
O4 ⁱ —Cd1—O8 ⁱⁱ	78.81 (13)	C2—C3—C8	121.1 (4)
O5—Cd1—O1	125.67 (14)	C4—C3—C8	119.2 (3)
O5—Cd1—O2	90.36 (16)	C3—C4—H4	119.9
O5—Cd1—O3 ⁱ	82.65 (15)	C5—C4—C3	120.2 (4)
O5—Cd1—O4 ⁱ	128.83 (14)	C5—C4—H4	119.9
O5—Cd1—O7 ⁱⁱ	80.41 (12)	C4—C5—H5	120.1
O5—Cd1—O8 ⁱⁱ	133.24 (16)	C4—C5—C6	119.8 (5)
O7 ⁱⁱ —Cd1—O2	85.03 (15)	C6—C5—H5	120.1
O7 ⁱⁱ —Cd1—O3 ⁱ	94.01 (14)	C1—C6—C5	120.8 (4)
O7 ⁱⁱ —Cd1—O8 ⁱⁱ	53.55 (14)	C1—C6—H6	119.6
O8 ⁱⁱ —Cd1—O2	93.07 (11)	C5—C6—H6	119.6
O8 ⁱⁱ —Cd1—O3 ⁱ	91.92 (10)	O1—C7—C1	118.1 (5)
O1—Na1—Na2 ⁱⁱⁱ	77.99 (11)	O2—C7—O1	121.4 (4)
O1—Na1—O4 ⁱ	77.84 (17)	O2—C7—C1	120.5 (4)
O1—Na1—O11B	104.1 (3)	O3—C8—O4	121.4 (4)
O1—Na1—O11A	97.1 (6)	O3—C8—C3	119.9 (4)
O3 ^{iv} —Na1—Na2 ⁱⁱⁱ	77.96 (14)	O4—C8—C3	118.7 (4)
O3 ^{iv} —Na1—O1	151.1 (2)	C10—C9—C14	119.7 (4)
O3 ^{iv} —Na1—O4 ⁱ	94.59 (15)	C10—C9—C15	119.8 (4)
O3 ^{iv} —Na1—O11B	82.9 (3)	C14—C9—C15	120.5 (4)

O3 ^{iv} —Na1—O11A	93.0 (6)	C9—C10—H10	120.0
O4 ⁱ —Na1—Na2 ⁱⁱⁱ	41.86 (11)	C9—C10—C11	120.0 (4)
O4 ⁱ —Na1—O11B	177.4 (3)	C11—C10—H10	120.0
O4 ⁱ —Na1—O11A	171.5 (7)	C10—C11—C16	119.6 (4)
O9—Na1—Na2 ⁱⁱⁱ	130.1 (2)	C12—C11—C10	119.9 (4)
O9—Na1—O1	95.8 (2)	C12—C11—C16	120.4 (4)
O9—Na1—O3 ^{iv}	112.0 (2)	C11—C12—H12	120.0
O9—Na1—O4 ⁱ	88.3 (2)	C13—C12—C11	120.1 (4)
O9—Na1—O11B	93.2 (4)	C13—C12—H12	120.0
O9—Na1—O11A	85.4 (8)	C12—C13—H13	119.7
O11B—Na1—Na2 ⁱⁱⁱ	136.6 (4)	C12—C13—C14	120.5 (4)
O11A—Na1—Na2 ⁱⁱⁱ	144.3 (8)	C14—C13—H13	119.7
Cd1 ^v —Na2—Na1 ^v	55.94 (8)	C9—C14—H14	120.1
O4 ^{vi} —Na2—Cd1 ^v	38.59 (8)	C13—C14—C9	119.9 (4)
O4 ^{vi} —Na2—Na1 ^v	37.86 (11)	C13—C14—H14	120.1
O5—Na2—Cd1 ^v	102.07 (15)	O5—C15—C9	117.2 (4)
O5—Na2—Na1 ^v	57.70 (14)	O6—C15—O5	121.7 (4)
O5—Na2—O4 ^{vi}	95.45 (19)	O6—C15—C9	121.1 (4)
O5—Na2—O7 ⁱⁱ	83.03 (18)	O7—C16—C11	118.4 (4)
O5—Na2—O10	104.5 (2)	O8—C16—O7	122.1 (4)
O7 ⁱⁱ —Na2—Cd1 ^v	133.31 (13)	O8—C16—C11	119.5 (3)
O7 ⁱⁱ —Na2—Na1 ^v	92.36 (13)	C17B—O11B—Na1	112.8 (9)
O7 ⁱⁱ —Na2—O4 ^{vi}	94.98 (14)	C17B—N1—C18B	120.6 (10)
O7 ⁱⁱ —Na2—O10	80.5 (2)	C17B—N1—C19B	127.4 (12)
O8 ^{vii} —Na2—Cd1 ^v	38.84 (9)	C19B—N1—C18B	111.8 (9)
O8 ^{vii} —Na2—Na1 ^v	89.00 (13)	C19A—N1—C18A	106.0 (13)
O8 ^{vii} —Na2—O4 ^{vi}	77.02 (13)	C17A—N1—C18A	116.8 (12)
O8 ^{vii} —Na2—O5	110.18 (16)	C17A—N1—C19A	136.9 (17)
O8 ^{vii} —Na2—O7 ⁱⁱ	164.93 (18)	O11B—C17B—H17B	119.1
O8 ^{vii} —Na2—O10	102.3 (2)	N1—C17B—O11B	121.8 (13)
O10—Na2—Cd1 ^v	139.3 (2)	N1—C17B—H17B	119.1
O10—Na2—Na1 ^v	161.7 (2)	N1—C18B—H18A	109.5
O10—Na2—O4 ^{vi}	158.8 (2)	N1—C18B—H18B	109.5
Cd1—O1—Na1	101.49 (13)	N1—C18B—H18C	109.5
C7—O1—Cd1	98.4 (3)	H18A—C18B—H18B	109.5
C7—O1—Na1	159.7 (3)	H18A—C18B—H18C	109.5
C7—O2—Cd1	87.1 (3)	H18B—C18B—H18C	109.5
Na1 ^{vii} —O3—Cd1 ^{viii}	117.93 (19)	N1—C19B—H19A	109.5
C8—O3—Cd1 ^{viii}	90.1 (3)	N1—C19B—H19B	109.5
C8—O3—Na1 ^{vii}	143.6 (3)	N1—C19B—H19C	109.5
Cd1 ^{viii} —O4—Na1 ^{viii}	97.02 (13)	H19A—C19B—H19B	109.5
Cd1 ^{viii} —O4—Na2 ^{ix}	97.42 (13)	H19A—C19B—H19C	109.5
Na1 ^{viii} —O4—Na2 ^{ix}	100.28 (18)	H19B—C19B—H19C	109.5
C8—O4—Cd1 ^{viii}	94.9 (3)	N1—C18A—H18D	109.5
C8—O4—Na1 ^{viii}	146.5 (3)	N1—C18A—H18E	109.5
C8—O4—Na2 ^{ix}	109.1 (3)	N1—C18A—H18F	109.5
Na2—O5—Cd1	99.83 (14)	H18D—C18A—H18E	109.5
C15—O5—Cd1	102.4 (3)	H18D—C18A—H18F	109.5

C15—O5—Na2	157.7 (3)	H18E—C18A—H18F	109.5
Na2 ^x —O7—Cd1 ^x	96.46 (14)	N1—C19A—H19D	109.5
C16—O7—Cd1 ^x	93.8 (3)	N1—C19A—H19E	109.5
C16—O7—Na2 ^x	164.5 (3)	N1—C19A—H19F	109.5
Na2 ^{iv} —O8—Cd1 ^x	105.91 (16)	H19D—C19A—H19E	109.5
C16—O8—Cd1 ^x	90.5 (2)	H19D—C19A—H19F	109.5
C16—O8—Na2 ^{iv}	149.8 (3)	H19E—C19A—H19F	109.5
Na1—O9—H9A	110.8	N1—C17A—H17A	123.6
Na1—O9—H9B	112.4	N1—C17A—O11A	113 (2)
H9A—O9—H9B	106.7	O11A—C17A—H17A	123.6
Na2—O10—H10A	109.8	C17A—O11A—Na1	136.8 (17)
Cd1—O1—C7—O2	1.6 (5)	C4—C3—C8—O3	-164.6 (4)
Cd1—O1—C7—C1	-179.3 (3)	C4—C3—C8—O4	15.9 (6)
Cd1—O2—C7—O1	-1.5 (4)	C4—C5—C6—C1	0.0 (7)
Cd1—O2—C7—C1	179.5 (4)	C6—C1—C2—C3	-0.5 (6)
Cd1 ^{viii} —O3—C8—O4	-5.0 (4)	C6—C1—C7—O1	-1.3 (6)
Cd1 ^{viii} —O3—C8—C3	175.5 (3)	C6—C1—C7—O2	177.8 (5)
Cd1 ^{viii} —O4—C8—O3	5.2 (4)	C7—C1—C2—C3	180.0 (4)
Cd1 ^{viii} —O4—C8—C3	-175.2 (3)	C7—C1—C6—C5	179.6 (4)
Cd1—O5—C15—O6	-6.1 (6)	C8—C3—C4—C5	179.5 (4)
Cd1—O5—C15—C9	173.6 (3)	C9—C10—C11—C12	-1.4 (6)
Cd1 ^x —O7—C16—O8	1.9 (4)	C9—C10—C11—C16	175.0 (4)
Cd1 ^x —O7—C16—C11	-178.2 (3)	C10—C9—C14—C13	0.6 (7)
Cd1 ^x —O8—C16—O7	-1.9 (4)	C10—C9—C15—O5	179.3 (4)
Cd1 ^x —O8—C16—C11	178.3 (3)	C10—C9—C15—O6	-1.0 (7)
Na1—O1—C7—O2	-166.8 (7)	C10—C11—C12—C13	0.5 (7)
Na1—O1—C7—C1	12.2 (11)	C10—C11—C16—O7	177.1 (4)
Na1 ^{vii} —O3—C8—O4	-147.3 (4)	C10—C11—C16—O8	-3.1 (6)
Na1 ^{vii} —O3—C8—C3	33.1 (7)	C11—C12—C13—C14	1.0 (7)
Na1 ^{viii} —O4—C8—O3	115.7 (5)	C12—C11—C16—O7	-6.5 (6)
Na1 ^{viii} —O4—C8—C3	-64.7 (7)	C12—C11—C16—O8	173.4 (4)
Na1—O11B—C17B—N1	148.4 (9)	C12—C13—C14—C9	-1.5 (7)
Na2 ^{ix} —O4—C8—O3	-94.4 (4)	C14—C9—C10—C11	0.8 (6)
Na2 ^{ix} —O4—C8—C3	85.2 (4)	C14—C9—C15—O5	1.0 (6)
Na2—O5—C15—O6	-179.4 (8)	C14—C9—C15—O6	-179.2 (5)
Na2—O5—C15—C9	0.4 (13)	C15—C9—C10—C11	-177.4 (4)
Na2 ^x —O7—C16—O8	-129.6 (10)	C15—C9—C14—C13	178.9 (4)
Na2 ^x —O7—C16—C11	50.2 (13)	C16—C11—C12—C13	-175.9 (4)
Na2 ^{iv} —O8—C16—O7	122.2 (5)	N1—C17A—O11A—Na1	-116 (3)
Na2 ^{iv} —O8—C16—C11	-57.7 (7)	C17B—N1—C17A—O11A	6.5 (16)
C1—C2—C3—C4	0.9 (6)	C18B—N1—C17B—O11B	-0.2 (17)
C1—C2—C3—C8	-179.5 (4)	C18B—N1—C17A—O11A	-174 (2)
C2—C1—C6—C5	0.0 (7)	C19B—N1—C17B—O11B	-173.3 (11)
C2—C1—C7—O1	178.3 (4)	C18A—N1—C17B—O11B	175.3 (18)
C2—C1—C7—O2	-2.6 (6)	C18A—N1—C17A—O11A	2 (3)
C2—C3—C4—C5	-0.9 (7)	C19A—N1—C17B—O11B	-142 (6)
C2—C3—C8—O3	15.8 (6)	C19A—N1—C17A—O11A	174 (2)

C2—C3—C8—O4	−163.7 (4)	C17A—N1—C17B—O11B	0.1 (14)
C3—C4—C5—C6	0.5 (7)		

Symmetry codes: (i) $x, y-1, z$; (ii) $x-1, y, z$; (iii) $-y, x, z-1/4$; (iv) $-y+1, x, z-1/4$; (v) $y, -x, z+1/4$; (vi) $y-1, -x, z+1/4$; (vii) $y, -x+1, z+1/4$; (viii) $x, y+1, z$; (ix) $-y, x+1, z-1/4$; (x) $x+1, y, z$.

Hydrogen-bond geometry (\AA , °)

$D-\text{H}\cdots A$	$D-\text{H}$	$\text{H}\cdots A$	$D\cdots A$	$D-\text{H}\cdots A$
O9—H9B···O6	0.90	2.22	3.074 (8)	159
O10—H10B···O6 ^{vii}	0.86	2.29	3.073 (8)	152
C4—H4···O3 ^{xi}	0.93	2.49	3.385 (6)	161
C6—H6···O11B	0.93	2.48	2.791 (5)	100
C6—H6···O11B	0.93	2.48	3.347 (14)	155
C10—H10···O10 ^{iv}	0.93	2.59	3.277 (8)	131
C14—H14···O8 ^{vii}	0.93	2.48	3.366 (5)	159
C18B—H18A···Cg3 ^{iv}	-	2.54	3.387 (11)	148
C19B—H19B···Cg4 ^{xii}	-	2.93	3.696 (15)	138
C19A—H19D···Cg4 ^{xii}	-	2.67	3.53 (4)	151

Symmetry codes: (iv) $-y+1, x, z-1/4$; (vii) $y, -x+1, z+1/4$; (xi) $-y+1, x+1, z-1/4$; (xii) $-x+1, -y+1, z-1/2$.